

Journal Publication

**Influence of the oxygen partial pressure
on the phase evolution during Bi-2212
wire melt processing**

C. Scheuerlein (CERN) *et al*

04 September 2015



The EuCARD-2 Enhanced European Coordination for Accelerator Research & Development project is co-funded by the partners and the European Commission under Capacities 7th Framework Programme, Grant Agreement 312453.

This work is part of EuCARD-2 Work Package **10: Future Magnets (MAG)**.

The electronic version of this EuCARD-2 Publication is available via the EuCARD-2 web site <http://eucard2.web.cern.ch/> or on the CERN Document Server at the following URL:
<http://cds.cern.ch/search?p=CERN-ACC-2016-0034>

Influence of the oxygen partial pressure on the phase evolution during Bi-2212 wire melt processing

C. Scheuerlein, J. Andrieux, M.O. Rikel, J. Kadar, C. Doerrer, M. Di Michiel, A. Ballarino, L. Bottura, J. Jiang, F. Kametani, E.E. Hellstrom, D.C. Larbalestier

Abstract—We have studied the influence of the oxygen partial pressure pO_2 up to 5.5 bar on the phase changes that occur during melt processing of a state-of-the-art Bi-2212 multifilamentary wire. Phase changes have been monitored *in situ* by high energy synchrotron X-ray diffraction (XRD). We found that the stability of Bi-2212 phase is reduced with increasing pO_2 . For $pO_2 > 1$ bar a significant amount of Bi-2212 phase decomposes upon heating in the range 400 to 650 °C. The extent of decomposition strongly increases with increasing pO_2 , and at $pO_2 = 5.5$ bar Bi-2212 decomposes completely in the solid state. Textured Bi-2212 can be formed during solidification when pO_2 is reduced to 0.45 bar when the precursor is molten. Since the formation of current limiting second phases is very sensitive to pO_2 when it exceeds 1 bar, we recommend to reduce the oxygen partial pressure below the commonly used $pO_2 = 1$ bar, in order to increase the pO_2 margins and to make the overpressure process more robust.

Index Terms—Bi-2212, melt processing, XRD.

I. INTRODUCTION

HIGH critical current (J_c) densities in Powder-in-Tube (PIT) Bi-2212 wires are achieved after a heat treatment (HT) cycle that melts the precursor and leads to Bi-2212 recrystallization [1]. This enables the wind and react approach that can produce Bi-2212 conductors, cables and coils in more complex shapes than is possible with any other High Temperature Superconductor (HTS) material. Indeed, Bi-2212 is up to now the only HTS that can be produced in twisted multifilamentary round wire form, from which Rutherford cables can be made, making Bi-2212 particularly attractive for high energy physics applications [2].

It is well known that during the Bi-2212 processing heat treatment (HT) an external oxygen supply through the oxygen permeable Ag wire matrix is needed in order to form Bi-2212. Oxygen is most conveniently supplied when the HT is performed in air at ambient pressure with an oxygen partial pressure (pO_2) of 0.21 bar. However, substantially higher critical current densities can be achieved when the same heat cycle is performed in a $pO_2 = 1$ bar.

Overpressure (OP) processing is a key for achieving

homogeneous high critical currents in long lengths of Bi-2212 wires [3]. OP processing also enables varying pO_2 in a wide range above 1 bar. For the optimization of the processing procedure, as well as for the establishment of acceptable temperature and pressure margins, it is of interest to verify how pO_2 influences the phase sequence and the Bi-2212 precursor melting and recrystallization behaviors.

Since the development of high energy synchrotron beam lines it has become possible to directly observe the phase changes inside a superconducting wire that is placed inside a furnace. This enables non-destructive and time resolved *in situ* process studies with various experimental techniques [4]. High energy synchrotron X-ray diffraction is particularly useful to monitor phase changes during the processing of superconducting wires [5].

Previously we have reported on the formation of porosity and the phase changes occurring in a Bi-2212 wire during processing in $pO_2 = 0.21$ bar [6]. In this article we report for the first time the direct observation of the phase changes during heat cycles at $pO_2 \geq 1$ bar.

II. EXPERIMENTAL DETAILS

A. The samples

All experiments have been performed with 5 cm-long PIT type Bi-2212/Ag wires, which were produced by Oxford Superconducting Technology (OST) using Nexans precursor powder of $Bi_{2.17}Sr_{1.94}Ca_{0.89}Cu_{2.00}O_{8+\delta}$ composition (OST billet number PMM 100610, in the following referred to as W13). The as-drawn wire, with a nominal diameter of $\varnothing = 0.8$ mm, has a 37×18 filament architecture and a Bi-2212 volume fraction of 25.8%. After standard overpressure HT with a total pressure of 100 bar and $pO_2 = 1$ bar, the volume fraction of Bi-2212 is 23.6%, and J_c at 4.2 K and 20 T of a W13 wire exceeds 2500 A/mm² using the densified cross section area [3]. The samples are identical to the straight Bi-2212/Ag wire samples that are often used for critical current (J_c) measurements.

M.O. Rikel is with Nexans Superconductors GmbH, Germany.

J. Kadar is with Friedrich-Alexander-Universität Erlangen-Nürnberg, 91054 Erlangen, Germany.

M. Di Michiel is with The European Synchrotron, ESRF, 71 avenue des Martyrs, 38000 Grenoble, France.

J. Jiang, F. Kametani, E.E. Hellstrom and D.C. Larbalestier are with National High Magnetic Field Laboratory, Florida State University, Tallahassee, FL 32310, USA.

Manuscript received September 4, 2015.

This work has been performed in the frame of the EuCARD-2 Future Magnets project (WP10). EuCARD-2 is co-funded by the partners and the European Commission under Capacities 7th Framework Programme, Grant Agreement 312453.

C. Scheuerlein, C. Doerrer, A. Ballarino and L. Bottura are with CERN, CH-1211 Geneva 23, Switzerland, (corresponding author phone: ++41 (0)22 767 8829, e-mail: Christian.Scheuerlein@cern.ch).

J. Andrieux is with Université Claude Bernard Lyon 1, LMI-UMR CNRS No. 5615, 69622 Villeurbanne, France.

B. X-ray diffraction

High energy synchrotron X-ray diffraction measurements were performed in the ID15B beamline of the European Synchrotron (ESRF). Diffraction patterns were acquired in transmission geometry using a high-efficiency high-readout-speed area detector. During the *in situ* HTs one pattern was acquired every 5 minutes. More details about the diffraction experiment can be found in [5] and [6].

For phase identification at a given temperature T , we have used room temperature XRD patterns (Table I) with shifts of d -spacing values estimated as $d(T) = d(RT) \times (1 + \alpha T)$ with the isotropic thermal expansion coefficients either taken from the literature (for Ag, Bi-2212) or assumed to be $\alpha = 10^{-5} \text{ K}^{-1}$ for other compounds.

TABLE I
CRYSTALLOGRAPHIC DATA OF BI-SR-CA-CU-O COMPOUNDS USED IN THIS STUDY

Compound ^a	Space group	RT Lattice parameters (Å)	Sr/Ca
Bi-2212 [7]	<i>Pmmm</i>	a=b=5.405; c=30.805	1.94/0.89
Bi-2201 [8]	<i>Pnam</i>	a=b=5.385; c=24.547	1.8/0.4
2:4CF-HT [9]	<i>Pc</i>	a=11.209; b=5.915; c=19.943; $\beta=101.64^\circ$	3:1
2:4CF-LT [10]	<i>P2/n</i>	a=8.397; b=5.999; c=5.900; $\beta=89.99^\circ$	3:1
14:24AEC [11]	<i>CCC2</i>	a=11.395; b=13.055; c=27.413	10:4
1:1AEC	<i>Cmcm</i>	a=3.493; b=16.204; c=3.886	0.6/0.4
CuO [12]	<i>C12/C1</i>	a=4.685; b=3.426; c=5.130; $\beta=99.55^\circ$	

^a 2:4CF=Bi₂(Sr_{4-y}Ca_y)O₇ (CF=Copper-Free; LT and HT stand for low- and high-temperature modifications); 14:24AEC=Sr_{14-z}Ca_zCu₂₄O₃₈; 1:1AEC = Sr_{1-x}Ca_xO₂ (AEC = Alkaline Earth Cuprate).

C. Temperature and oxygen partial pressure control

Two furnaces have been used for the *in situ* XRD experiments. The HTs in ambient air have been performed under a continuous gas flow at ambient pressure in the ID15 tomography furnace, as described in [6].

HTs in $pO_2 > 0.21$ bar have been performed using a set-up that has been developed for combined *in situ* high energy XRD and mass spectrometry investigations during catalyzed gas/solid or liquid/solid reactions [13]. This set-up consists of a high pressure cell made of a single crystal sapphire tube, which is heated by a dedicated furnace. For the study of Bi-2212/Ag superconductors, the set-up was modified so that an S-type (Pt-Rh/Pt) thermocouple can be spot-welded onto the Ag matrix of the Bi-2212 wire for the temperature control up to 900 °C. The thermocouple is welded onto the wire about 2 mm from the X-ray beam position during XRD measurements. The estimated accuracy of the temperature measurement is better than ± 10 °C. The temperature ramp rates during heating were 160 °C/h up to 820 °C, and then 50 °C/h up to the maximum temperature, similar to the rate during a typical Bi-2212 melt processing HT [6]. The wires were cooled from the peak temperature to room temperature within few hours, much faster than during a standard HT that lasts typically 3 days.

The partial pressure of O₂ was changed by changing the total

pressure of industrial Air (Zero Air from Air Products Analytical Gases) from 1 bar to 100 bar. A small leak was added to the high pressure cell in order to have gas exchange during the HT cycle.

III. RESULTS

Below we present the phase sequences during Bi-2212 HT at different pO_2 ranging from $pO_2=0.21$ bar up to $pO_2=5.5$ bar.

A. Phase sequence during HT at $pO_2=0.21$ and 1.05 bar

Fig. 1 shows the evolution with temperature of XRD patterns that have been recorded during the $pO_2=0.21$ bar HT in ambient air. No major phase changes are observed prior to the Bi-2212 melting decomposition.

A phase with prominent diffractions peaks at $Q=2.047, 2.078$ and 2.108 \AA^{-1} , tentatively identified as 2:4CF-HT, is formed when Bi-2212 melts around 880 °C. Minor diffraction peaks that occur at the same temperature could be characteristic for 1:1AEC phase. The Bi-2212 recrystallization and simultaneous 2:4CF-HT decomposition are detected on cooling at about 17 °C below the Bi-2212 decomposition and 2:4CF-HT crystallization temperatures. The Bi-2212 texture development can be seen by the increase of the Bi-2212 (020)(200) peak intensity with respect to that of the (117), (113) and (115) peaks.

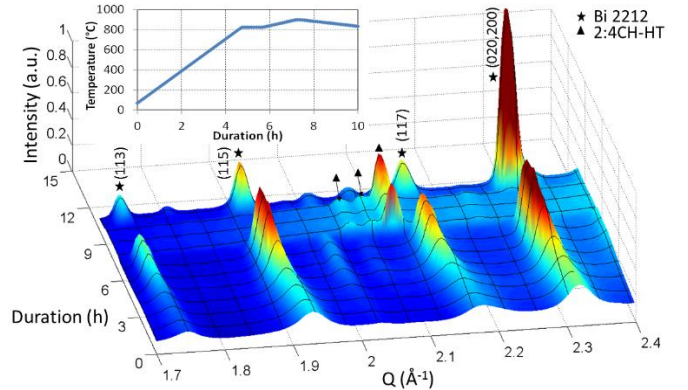


Fig. 1. Sequence of XRD patterns acquired during the HT in a flow of ambient air ($pO_2=0.21$ bar) with indexing of the major peaks. The temperature cycle is shown in the insert.

The appearance of a minor diffraction peak at $Q \approx 2.11 \text{ \AA}^{-1}$, probably characteristic of 2:4CF-LT, on heating at around 650 °C, may be an indication of some Bi-2212 phase instability.

XRD patterns upon heating in $pO_2=1.05$ bar are similar to those observed in $pO_2=0.21$ bar. Changes in the patterns that can be related to precipitation of a small amount of Bi-2201 and presumably 2:4CF-LT+CuO with subsequent reformation of Bi-2212 phase were observed on heating from 550 to 770 °C. In $pO_2=1.05$ bar, the $Q \approx 2.11 \text{ \AA}^{-1}$ peak (likely the $21\bar{1}$ peak of 2:4CF-LT) to Bi-2212 (115) peak area ratio was roughly three times larger than it was in $pO_2=0.21$ bar.

B. Phase sequence in $pO_2=5.5$ bar (heating) and $pO_2=0.45$ bar (cooling)

In this experiment the oxygen partial pressure was kept constant at $pO_2=5.5$ bar during heating. At 869 °C, when the precursor was already molten it was reduced to $pO_2=0.45$ bar.

The change in pO_2 during processing was introduced because our preliminary temperature dependent XRD experiments had shown that Bi-2212 did not form during cooling when the HT cycle is performed at constant $pO_2 = 5.5$ bar. The goal was to verify whether Bi-2212 can re-crystallize after prior Bi-2212 to Bi-2201 transformation. The sequence of XRD patterns acquired during this pressure and heat cycle are shown in Fig. 2.

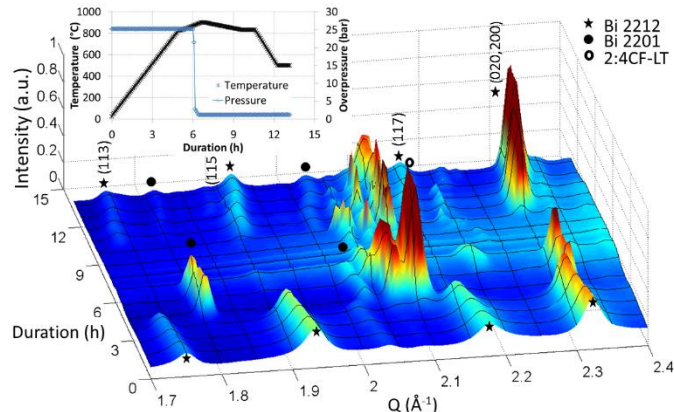


Fig. 2. Sequence of XRD patterns recorded during heating up at $pO_2=5.5$ bar and cooling down at $pO_2=0.45$ bar. The temperature and pressure cycles are shown in the inset.

In $pO_2=5.5$ bar Bi-2212 starts to decompose in the solid state above 450°C , and disappears at 650°C . As illustrated in Fig. 3, the Bi-2212 decomposition reaction has been identified as $\text{Bi-2212} \Rightarrow \text{Bi-2201} + 2:4\text{CF-LT} + \text{CuO}$. This phase assemblage remains until about 780°C above which small amounts of new phases start to form, probably 2:4CF-HT and 14:24AEC.

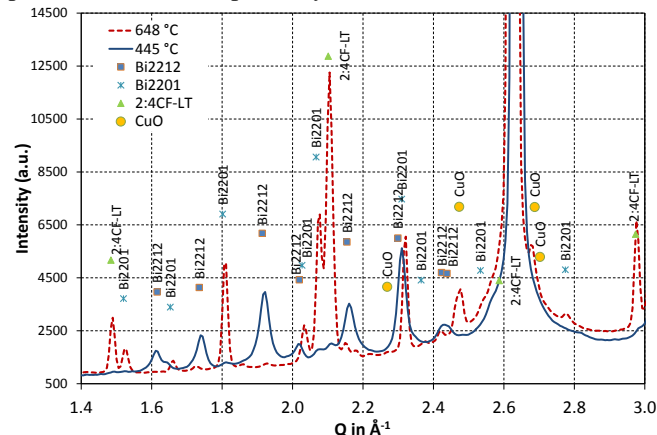


Fig. 3. Comparison of XRD patterns acquired at 445 and 648°C upon heating in $pO_2=5.5$ bar with Bi-2212, Bi-2201, CuO and 2:4CF peaks from reference pattern (see Table I).

As it can be seen in Fig. 2, cooling in 0.45 bar O_2 resulted in recrystallization of the Bi-2212 phase starting at about 850°C . The relatively stronger Bi-2212 (020)(200) peak intensity after recrystallization is due to the texturing of the Bi-2212 during recrystallization.

C. Influence of pO_2 on the Bi-2212 decomposition reaction

The Bi-2212 peak area evolutions during heating at different pO_2 are compared in Fig. 4. It is immediately obvious from the Bi-2212 area evolution that a large amount of Bi-2212 is transformed prior to precursor melting when heating is

performed in $pO_2=1.5$ bar and 5.5 bar. We assume that the increase of the Bi-2212 peak area when the HT is performed at lower pO_2 is due to the crystallization of Bi-2212 from powder that was amorphous after the wire drawing process.

At $pO_2=0.21$ and 1.05 bar, Bi-2212 melting is completed at approximately 880°C and at $pO_2=1.5$ bar precursor melting is completed at 860°C . At $pO_2=5.5$ bar the Bi-2212 solid state transformation to $\text{Bi-2201} + 2:4\text{CF-LT} + \text{CuO}$ is completed at 650°C .

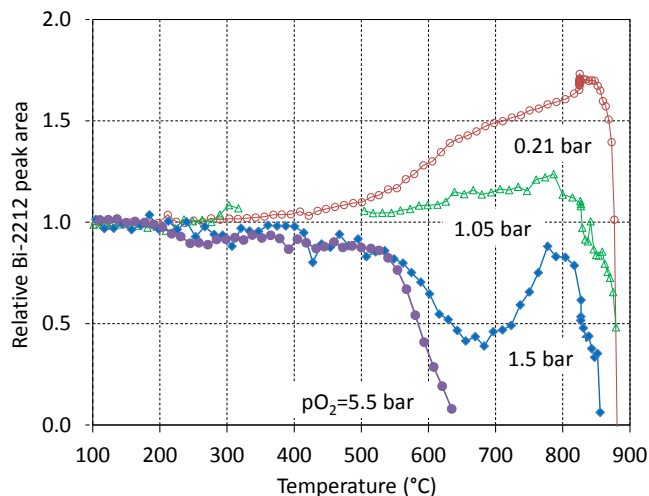


Fig. 4. Relative Bi-2212 peak area evolution during heating at different pO_2 .

Only a tiny amount of Bi-2212 transforms into second phases when the HT is done in $pO_2=0.21$ bar. During heating at $pO_2=1.05$ bar, a slightly larger amount of second phase is formed. Increasing pO_2 further increases Bi-2212 instability.

In $pO_2=1.5$ bar Bi-2212 is unstable above 350°C , and a significant amount of Bi-2212 decomposes to $\text{Bi-2201} + 2:4\text{CF-LT} + \text{CuO}$, but partly reforms again from 670 to 820°C . The strong influence of pO_2 changes above 1 bar on the amount of second phases formed is clearly seen in Fig. 5, which compares the evolution of prominent diffraction peaks of the main secondary phases, Bi-2201 and presumably 2:4CF-LT, during heating at $pO_2=1.05$, 1.5 and 5.5 bar.

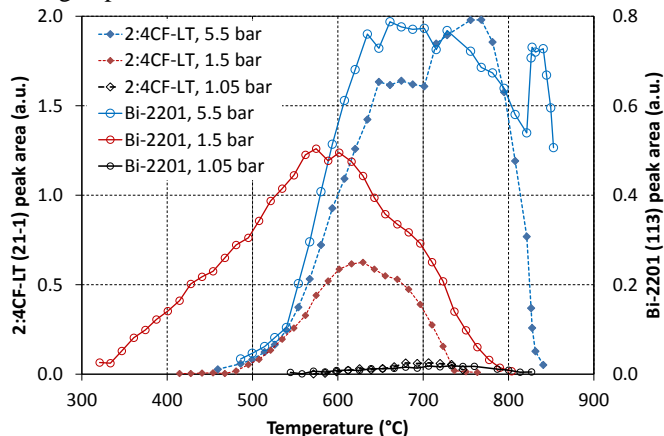


Fig. 5. Relative Bi-2201 and 2:4CF-LT peak area evolution during heating at $pO_2=1.05$, 1.5 and 5.5 bar.

IV. DISCUSSION AND CONCLUSION

Current limiting mechanisms in Bi-2212 PIT wires include

obstructions of the current path by porosity [14] and second phase inclusions. An important goal of the Bi-2212 melt processing is therefore to minimize the formation of second phases while forming well-connected and textured Bi-2212 filaments.

Here we report for the first time a direct observation of the phase changes inside Bi-2212 round wires during processing at different oxygen partial pressures above ambient pressure. The 5 cm-long wire samples with closed ends that have been used in this XRD study are identical to the samples used for critical current measurements that are representative for long wires in magnet coils [15].

We found that in the range $pO_2=0.21$ -1.05 bar only a small amount of Bi-2212 decomposes in the solid state prior to precursor melting, and there is only a relatively small influence of pO_2 on the phase sequence. However, further increasing pO_2 strongly changes the phase sequence. At $pO_2=1.5$ bar Bi-2212 decomposes partly prior to melting, and the precursor decomposition temperature is about 20 °C lower than it is at $pO_2=1.05$ bar. At $pO_2=5.5$ bar Bi-2212 decomposes at the very low temperature of about 630 °C. A similar decrease of the Bi-2212 decomposition temperature with increasing pO_2 has also been reported in [16,17]. In the study of thick Bi-2212 films the solid state Bi-2212 decomposition at $pO_2=5$ bar occurred at about 730 °C [16], which is about 100 °C higher than the temperature at which we observed the decomposition in the state-of-the-art multifilament Bi-2212 wire.

Since the stability boundary above which substantial Bi-2212 decomposition occurs prior to the precursor melting is close to $pO_2=1$ bar, reducing pO_2 below 1 bar, which is the commonly used oxygen partial pressure in Bi-2212 melt processing, would increase the pO_2 margin and could make the process more robust.

ACKNOWLEDGMENTS

We acknowledge the ESRF for beam time on ID15. The work at the National High Magnetic Field Laboratory (NHMFL) was supported by the US Department of Energy (DOE) Office of High Energy Physics under grant number DE-SC0010421, by the National Science Foundation under NSF/DMR-1157490, and by the State of Florida.

REFERENCES

- [1] K. Heine, J. Tenbrink M. Thoner, "High field critical current densities in $Bi_2Sr_2CaCu_2O_8$ -/Ag wires", *Appl. Phys. Lett.* 55, 2441-2443 (1989).
- [2] L. Rossi, "LHC upgrade plans: options and strategy Proc." IPAC11, <http://www.jacow.org/> (2011).
- [3] D.C. Larbalestier, J. Jiang, U.P. Trociewitz, F. Kametani, C. Scheuerlein, M. Dalban-Canassy, M. Matras, P. Chen, N.C. Craig, P.J. Lee, E.E. Hellstrom, "Isotropic round wire multifilament cuprate superconductor for generation of magnetic fields above 30 T", *Nature Materials*, Vol. 13 (2014), 10.1038/nmat3887
- [4] C. Scheuerlein, M. Di Michiel, F. Buta, "Synchrotron radiation techniques for the characterisation of Nb_3Sn superconductors", *IEEE Trans. Appl. Supercond.* 19(3), (2009), 2653-2656
- [5] M. Di Michiel, C. Scheuerlein, "Phase transformations during the reaction heat treatment of powder-in-tube Nb_3Sn superconductors", *Supercond. Sci. Technol.* 20, (2007) L55-L58
- [6] C. Scheuerlein, M. Di Michiel, M. Scheel, J. Jiang, F. Kametani, A. Malagoli, E.E. Hellstrom, D.C. Larbalestier, "Void and phase evolution

- during the processing of Bi-2212 superconducting wires monitored by combined fast synchrotron micro-tomography and X-ray diffraction" *Supercond. Sci. Technol.* 24 (2011) 115004
- [7] D. P. Matheis and R. L. Snyder, X-ray powder diffraction analysis of the incommensurate modulated structure of $Bi_2Sr_2CaCu_2O_8$, 1994
- [8] Bi-2201 reference pattern, ICSD PDF# 46-0041 ICSD 69883
- [9] 2:4CF-HT reference pattern PDF00-049-0864
- [10] W Wong Ng, J A Kaduk, Q Huang, R S Roth, "Crystal Structure of the monoclinic perovskite $Sr_{3.94}Ca_{1.32}Bi_{2.70}O_{12}$ ", *Powder Diffraction* Vol. 15 (2000), 727-733
- [11] 14:24AEC reference pattern ICSD 39680
- [12] N.E. Brese et al, "Low-temperature structures of CuO and AgO and their relationships to those of MgO and PdO", *Journal of Solid State Chemistry JSSCB* 89 (1990) 184-190 (ICSD 69094)
- [13] J. Andrieux, C. Chabert, A. Mauro, H. Vitoux, B. Gorges, T. Buslaps, V. Honkimäki, "A high pressure and high temperature gas loading system for the study of conventional to real industrial sized samples in catalyzed gas/solid and liquid/solid reactions", *J. Appl. Cryst.* 47, (2014), 245-255
- [14] F. Kametani, T. Shen, J. Jiang, A. Malagoli, C. Scheuerlein, M. Di Michiel, Y. Huang, H. Miao, J. A. Parrell, E. E. Hellstrom, D. C. Larbalestier, "Bubble formation within filaments of melt-processed Bi2212 wires and its strongly negative effect on the critical current density", *Supercond. Sci. Technol.* 24 (2011) 075009
- [15] A. Malagoli, P.J. Lee, A. Ghosh, C. Scheuerlein, M. Di Michiel, J. Jiang, U.P. Trociewitz, E.E. Hellstrom, D.C. Larbalestier, "Evidence of length-dependent wire expansion, filament dedensification and consequent degradation of critical current density in Ag-alloy sheathed Bi-2212 wires", *Supercond. Sci. Technol.*, 26, (2013), 055018
- [16] J.J. Gannon Jr., K.H. Sandhage, "Solid-State High-Oxygen-Fugacity Processing of BSCCO-2212 Superconductors", *IEEE Trans. Appl. Supercond.* 7(2), (1997), 1533-1536
- [17] D. H. Chmielewski, K. H. Sandhage, "Stability of $Bi_2Sr_2Ca_1Cu_2O_{8.6}$ Thick Films at Elevated Oxygen Pressures and Temperatures", *J. Am. Ceram. Soc.*, 78 (9), (1995), 2504-2512