

STRENGTH AND SHAPE OF THE MAGNETIC FIELD OF THE FERMILAB MAIN INJECTOR DIPOLES*

D.J. Harding[#], B.C. Brown, J. Dimarco, H.D. Glass, P.S. Martin, P.O. Mazur, C.S. Mishra, D.F. Orris, J.W. Sim, J.C. Tompkins, K. Trombley-Freytag, D.G.C. Walbridge, Fermi National Accelerator Laboratory, P.O. Box 500, Batavia, IL 60510 USA

Abstract

Measurements of 230 6-meter and 136 4-meter dipoles constructed for the Fermilab Main Injector were carried out as part of the magnet production effort. An automated measurement system provided data on magnetic field strength and shape using several partially redundant systems. Results of these measurements are available for each individual magnet for use in accelerator modelling. In this report we will summarise the results on all of the magnets to characterise the properties which will govern accelerator operation.

1 INTRODUCTION

Over the last decade the Fermilab Main Injector and its magnets have been planned [1,2], designed [3,4,5,6] prototyped [7,8,9,10], produced [11,12], measured [13,14,15,16,17,18], installed [19], and commissioned [20,21]. Every dipole has been measured thoroughly, providing a rich set of data that is used for magnet assignments and beam modeling. Here we present an overview to give a flavor of the Main Injector dipoles.

In all, 230 6-meter and 136 4-meter dipoles were built and measured, including spares. These may be divided into several groups whose behavior differs for well-understood reasons: 1) Six 6-m R&D dipoles, 2) Six 4-m R&D dipoles, 3) the first 46 6-m dipoles, 4) the balance of the 6-m dipoles, and 5) the balance of the 4-m dipoles. Groups 1 and 2 were built with steel from Vendor A. Group 2 was built too long by 2.5-mm. Group 3 was built all or in part from steel from Vendor B's first production run. Groups 4 and 5 were built entirely with steel from Vendor B's later runs.

The integrated strength and the harmonic composition of the magnetic field was measured at multiple currents using a rotating tangential probe that extended through the magnet following the path of the beam. Field strength and shape were also measured using an integrating coil that could be held on center as the current ramped or moved transversely at a fixed current. A sample of magnets was further measured with an NMR and Hall probe package that scanned the magnet longitudinally.

* Work supported by the United States Department of Energy under contract No. DE-AC02-76CH03000.

Email: harding@fnal.gov

2 MAGNET STRENGTH

Groups 4 and 5 define our nominal magnet strength at each current. The mean strength, including the 4-m magnets weighted at 2/3 of the 6-m magnets, was calculated for each current. Deviations from that strength (for the 6-m magnets) or from 2/3 of that strength (for the 4-m magnets) are normalized to the nominal strength of the 6-m magnets. These deviations are quoted here in "units" of parts in 10^4 .

Figure 1 shows the distribution of deviations of magnet strength from nominal for all magnets as a function of magnetic field. The profile is dominated by a narrow peak around the nominal strength composed primarily of Groups 4 and 5. The standard deviation of the distribution, due to variations in magnet length, magnet gap, steel properties, and random measurement errors, is in the range of 2 to 4 units.

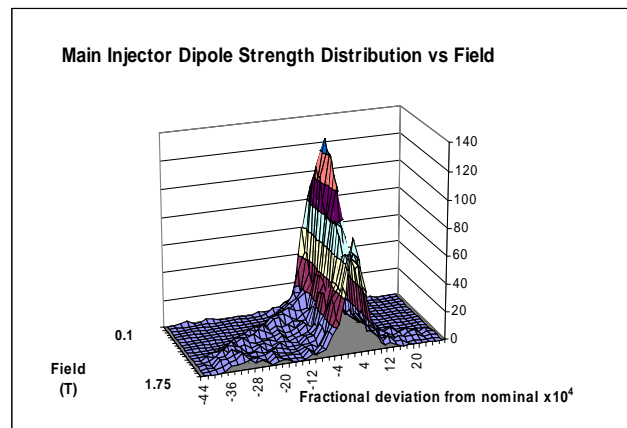


Figure 1: Main Injector dipole magnet strength distribution as a function of field. The field ranges from the injection value of 0.1 T to its peak of 1.75 T.

A second, lower ridge branches from the main stem at about 0.3 T and diverges to lower strength roughly linearly. These are Group 3 magnets with early steel from vendor B. [22] A handful of magnets appear below the nominal peak at 0.1 T, and the same magnets appear above the peak around 1.5 to 1.6 T. These are Groups 1 and 2 showing first a lower remanent field and then slower saturation. A modification to the back leg has allowed us to match the nominal field at 1.4 T and at 1.7 T, though it runs high in between.[23] The identity of

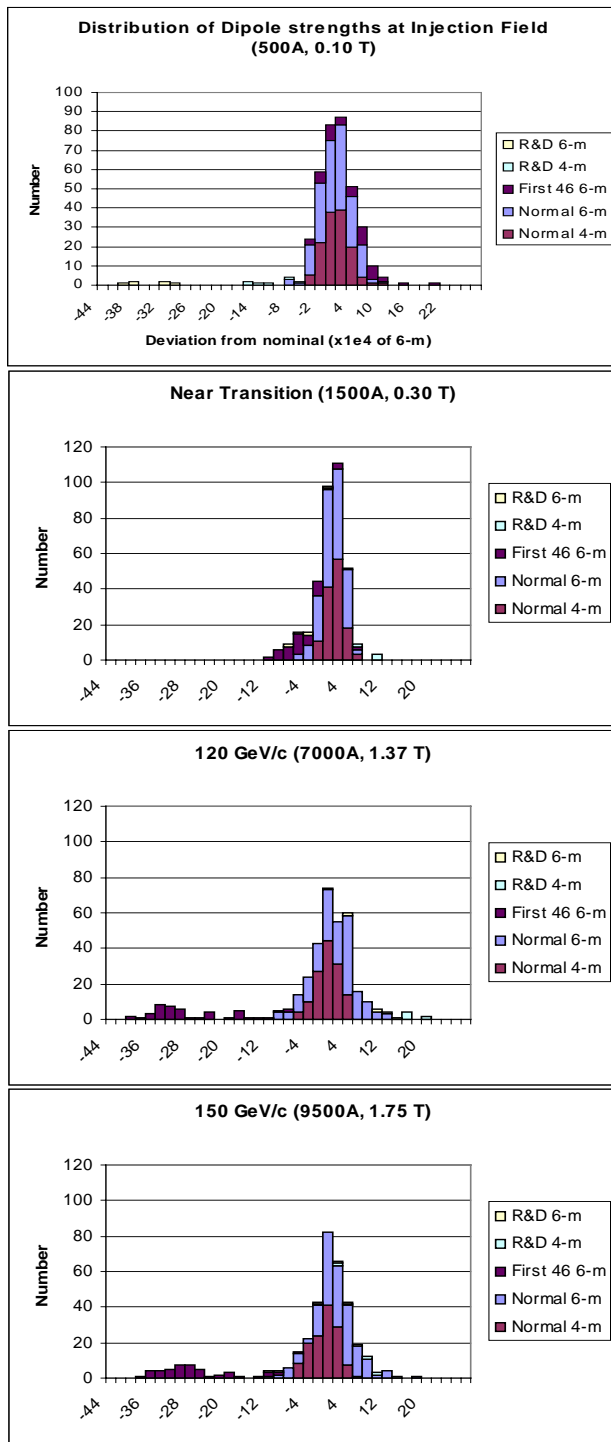


Figure 2: Distribution of magnet strength at four key excitations.

these groups of magnets is clear in the histograms of Figure 2 which represent slices through the Figure 1 mountain range.

The hysteresis in the dipoles has also been studied. The variety of operational modes requires that it be included in control systems calculations.[24,25]

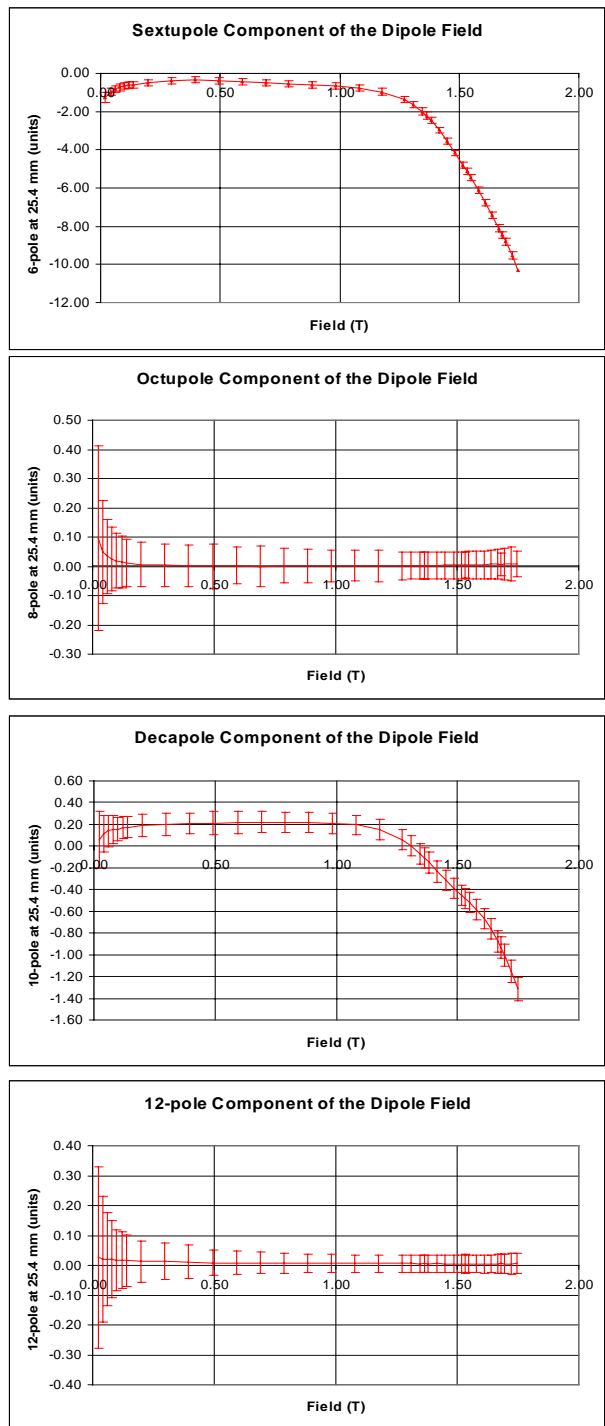


Figure 3: Multipole components of the dipole magnets as a function of magnetic field. The ordinate scales vary.

3 HARMONICS

We characterize the variation of the magnet field across the aperture by the coefficients of its harmonic decomposition. The coefficient we quote is the fraction of the field due to the component in question at 25.4 mm (typical of the maximum beam size) relative to the dipole component in "units" or parts in 10^4 .

Figure 3 shows the distribution of the normal sextupole, octupole, decapole, and 12-pole as a function of magnetic field. The error bars represent one standard deviation. Note that the plots extend below the injection field of 0.10 T. As expected, we see some contribution of even terms as the steel saturates, reflecting the symmetry of the magnet, but the design and fabrication process minimizes the antisymmetric terms.

In operation, a significant sextupole field is also generated by eddy currents in the beam tube.[26,27]

4 CONCLUSION

Although the variation in steel properties prevented the overall Main Injector dipole strength variation from meeting expectations, within a steel run the uniformity was excellent. The field shapes meet the project requirements.[28] The non-standard magnets have been assigned locations in the ring where they produce small, local two-bumps, minimizing their impact on the closed orbit.[29]. Care has been taken to reserve a suitable collection of spare magnets to allow replacement of any magnet with a like magnet.

Purchasing all the steel before the project was funded would have alleviated the strength variation by increasing the uniformity of the steel and permitting homogenization of the magnet cores. In the end, the cost and schedule savings enabled by the phased steel purchases justify the extra effort required.

5 REFERENCES

[1] S.D. Holmes *et al.*, "The Fermilab Upgrade", In *Proceedings of the 1989 Particle Accelerator Conference*, Chicago, (1989).
 [2] S.D. Holmes, "Tevatron Performance Goals for the Coming Decade", In *Proceedings this Conference*, (1999).
 [3] *The Fermilab Main Injector Technical Design Handbook*, (Fermilab, Batavia, 1997).
 [4] D.J. Harding *et al.*, "Design Considerations and Prototype Performance of the Fermilab Main Injector Dipole", In *Proceedings of the 1991 Particle Accelerator Conference*, San Francisco, (1991).
 [5] M. Bleadon *et al.*, "The Fermilab Main Injector Dipole Construction Techniques and Prototype Magnet Measurements", Presented at the 12th International Conference on Magnet Technology, Leningrad, (1991).
 [6] B.C. Brown *et al.*, "The Design and Manufacture of the Fermilab Main Injector Dipole Magnet", Presented at the EPAC Conference, Berlin, (1992).
 [7] J. Ostiguy, "Magnet End Design: The Main Injector Dipoles", In *Proceedings of the 1991 Particle Accelerator Conference*, San Francisco, (1991).
 [8] J. Ostiguy, "Longitudinal Profile and Effective Length of a Conventional Dipole Magnet", In *Proceedings of the 1993 Particle Accelerator Conference*, Washington, (1993).
 [9] H. D. Glass, "Techniques for Measurement of Dipole Endfields with a Rigid Integrating Coil", In *Proceedings of the 1993 Particle Accelerator Conference*, Washington, (1993).
 [10] D.J. Harding *et al.*, "Design and Measurements of Prototype Fermilab Main Injector Dipole Endpacks", In *Proceedings of the 1993 Particle Accelerator Conference*, Washington, (1993).

[11] D.J. Harding *et al.*, "Experience with the Source Evaluation Board Method of Procuring Technical Components for the Fermilab Main Injector", In *Proceedings of the 1993 Particle Accelerator Conference*, Washington, (1993).
 [12] A.D. Russell *et al.*, "Selecting Magnet Laminations Recipes Using the Method of Simulated Annealing", In *Proceedings of the 1997 Particle Accelerator Conference*, Vancouver, (1997).
 [13] H. D. Glass *et al.*, "Flatcoil Systems for Measurements of Fermilab Magnets", Presented at the Fourteenth International Conference on Magnet Technology, Tampere, Finland, (1995).
 [14] B.C. Brown *et al.*, "Software Design for a Database Driven System for Accelerator Magnet Systems", In *Proceedings of the 1991 Particle Accelerator Conference*, San Francisco, (1991).
 [15] J.W. Sim *et al.*, "A Relational Database for Magnets and Measurement Systems at the Fermilab Magnet Test Facility", In *Proceedings of the 1995 Particle Accelerator Conference*, Dallas, (1995).
 [16] J.W. Sim *et al.*, "Software for a Database-Controlled Measurement System at the Fermilab Magnet Test Facility", In *Proceedings of the 1995 Particle Accelerator Conference*, Dallas, (1995).
 [17] D.J. Harding *et al.*, "Magnetic Field Measurements of the Initial Fermilab Main Injector Production Dipoles", In *Proceedings of the 1995 Particle Accelerator Conference*, Dallas, (1995).
 [18] B.C. Brown *et al.*, "Results on Fermilab Main Injector Dipole Measurements", Presented at the Fourteenth International Conference on Magnet Technology, Tampere, (1995).
 [19] J.A. Satti, "The Fermilab Main Injector Dipole and Quadrupole Cooling Design and Bus Connections", In *Proceedings of the 1995 Particle Accelerator Conference*, Dallas, (1995).
 [20] P.S. Martin *et al.*, "Fermilab Main Injector Commissioning Status", In *Proceedings this Conference*, (1999).
 [21] C.S. Mishra, "Simulation and Measurements of the Fermilab Main Injector Dynamic Aperture", In *Proceedings this Conference*, (1999).
 [22] P.S. Martin *et al.*, "Variations in the Steel Properties and the Excitation Characteristics of Fermilab Main Injector Dipoles", In *Proceedings of the 1997 Particle Accelerator Conference*, Vancouver, (1997).
 [23] P.S. Martin *et al.*, "Modifications to the Excitation Characteristics of Fermilab Main Injector Dipoles by Machining", *Proceedings of the 1997 Particle Accelerator Conference*, Vancouver, (1997).
 [24] B.C. Brown *et al.*, "Design for Fermilab Main Injector Magnet Ramps which Account for Hysteresis", In *Proceedings of the 1997 Particle Accelerator Conference*, Vancouver, (1997).
 [25] B.C. Brown *et al.*, "Analytic Fits to Hysteretic Fields in Main Injector Dipoles, Quadrupoles and Sextupoles", In *Proceedings this Conference*, (1999).
 [26] D.G.C. Walbridge *et al.*, "Measurements of Beam Pipe Eddy Current Effects in Main Injector Dipole Magnets", Presented at the XVth International Conference on High Energy Accelerators, Hamburg, (1992).
 [27] D.G.C. Walbridge *et al.*, "Field Errors Introduced by Eddy Currents in Fermilab Main Injector Magnets", In *Proceedings of the 15th International Conference on Magnet Technology*, Beijing, (1997).
 [28] F.A. Harfoush *et al.*, "Defining the Systematic and Random Multipoles Errors for Main Injector Tracking," In *Proceedings of the 1993 Particle Accelerator Conference*, Washington, (1993).
 [29] P.S. Martin *et al.*, "Excitation Characteristics of Fermilab Main Injector Dipoles and Magnet Assignment to Reduce Closed Orbit Errors", In *Proceedings of the 1997 Particle Accelerator Conference*, Vancouver, (1997).