Magnetic crystalline-symmetry-protected axion electrodynamics and field-tunable unpinned Dirac cones in EuIn₂As₂

S. X. M. Riberolles,^{1,*} T. V. Trevisan,^{1,2} B. Kuthanazhi,^{1,2} T. W. Heitmann,³ F. Ye,⁴

D. C. Johnston,^{1,2} S. L. Bud'ko,^{1,2} D. H. Ryan,⁵ P. C. Canfield,^{1,2} A. Kreyssig,^{1,2}

A. Vishwanath,⁶ R. J. McQueeney,^{1,2} L. -L. Wang,^{1,2} P. P. Orth,^{1,2} and B. G. Ueland^{1,†}

¹Ames Laboratory, Ames, IA, 50011, USA ²Department of Physics and Astronomy, Iowa State University, Ames, IA, 50011, USA

³University of Missouri Research Reactor, Columbia, MO, 65211, USA

⁴Oak Ridge National Laboratory, Oak Ridge, TN, 37830, USA

⁵Physics Department and Centre for the Physics of Materials,

McGill University, Montreal, Quebec H3A 2T8, Canada ⁶Department of Physics and Astronomy, Harvard University, Cambridge, MA, 02138, USA

(Dated: April 7, 2021)

Abstract

Knowledge of magnetic symmetry is vital for exploiting nontrivial surface states of magnetic topological materials. EuIn₂As₂ is an excellent example, as it is predicted to have collinear antiferromagnetic order where the magnetic moment direction determines either a topological-crystallineinsulator phase supporting axion electrodynamics or a higher-order-topological-insulator phase with chiral hinge states. Here, we use neutron diffraction, symmetry analysis, and density functional theory results to demonstrate that EuIn₂As₂ actually exhibits low-symmetry helical antiferromagnetic order which makes it a stoichiometric magnetic topological-crystalline axion insulator protected by the combination of a 180° rotation and time-reversal symmetries: $C_2 \times \mathcal{T} = 2'$. Surfaces protected by 2' are expected to have an exotic gapless Dirac cone which is unpinned to specific crystal momenta. All other surfaces have gapped Dirac cones and exhibit half-integer quantum anomalous Hall conductivity. We predict that the direction of a modest applied magnetic field of $\mu_0 H \approx 1$ to 2 T can tune between gapless and gapped surface states.

INTRODUCTION

Electrons attaining a nontrivial Berry phase due to symmetry-protected features in the electronic band structure [1-4] and/or the presence of noncoplanar magnetic order [5-7] can lead to astonishing topological physical properties such as dissipationless chiral-charge transport, quantum anomalous Hall (QAH) effect, and axion electrodynamics [4, 8]. Whereas topological-crystalline insulators (TCIs) are broadly defined as insulators with nontrivial topological properties protected by crystalline symmetry, magnetic TCIs offer the possibility of tuning topological properties via manipulating the magnetic order [4]. Indeed, much theoretical effort is focused on predicting magnetic crystalline materials with nontrivial topological states by considering symmetries associated with the magnetic space groups (MSGs) describing their magnetic order [9-11]. A database with predictions for nontrivial topological band structures based on MSG symmetries provides important guidance towards finding new magnetic topological materials using high-throughput *ab initio* studies [11]. However, an often limiting bottleneck is detailed knowledge of a candidate's intrinsic magnetic order, which is difficult to predict theoretically. Determining such order can be a subtle task requiring significant experimental effort.

QAH and axion insulators (AXIs) are particularly attractive topological states as the

former manifests quantized Hall conductivity in the absence of an applied magnetic field, and the latter shares similarities with the axion particle in quantum chromodynamics [12]. AXIs exhibit the topological magnetoelectric (TME) effect for which an applied electric field \mathbf{E} induces a parallel magnetization \mathbf{M} or a magnetic field \mathbf{H} induces a parallel electric polarization [4]. An AXI requires that the axion angle θ in the action of axion electrodynamics $S_{\theta} = \theta \frac{e^2}{4\pi^2} \int dt \, d^3 r \mathbf{E} \cdot \mathbf{B}$ is $\theta = \pi$, which leads to the presence of half-integer QAH-type conductivity on insulating surfaces [10, 13]. Here, $\mathbf{B} = \mu_0(\mathbf{H} + \mathbf{M})$ is the magnetic induction, μ_0 is the permeability of free space, and e is the electron charge. θ is quantized to zero or π in the presence of either time-reversal \mathcal{T} or inversion \mathcal{I} symmetry, but also any other symmetry operation that reverses an odd number of space-time coordinates [14].

Hexagonal EuIn₂As₂ [space goupe $P6_3/mmc$ (No. 194) with lattice parameters a = 4.178(3) Å and c = 17.75(2) Å] is a magnetic TCI built of alternating Eu and In₂As₂ layers stacked along **c** as shown in Fig. 1c [15, 16]. The magnetic Eu²⁺ (spin $S = \frac{7}{2}$) layers undergo antiferromagnetic (AF) ordering at a Néel temperature of $T_N \approx 18$ K [17] which density functional theory (DFT) calculations predict to be A-type [18]. A-type order is collinear, with the ordered Eu magnetic moments μ ferromagnetically aligning in each layer and the layers stacking AF along **c**. Theory predicts that depending on the orientation of μ , the A-type order leads to an AXI that is either a TCI with some gapless surfaces or a higher-order topological insulator with chiral-hinge states [17, 18]. Attractively, the ordered Eu moments may influence topological fermions in In₂As₂ layers, providing a path for *in situ* control of band topology.

Below we detail our discovery of low-symmetry broken-helix magnetic order in EuIn₂As₂ using single-crystal neutron diffraction. We find that the broken-helix order has 2' symmetry elements along specific crystalline axes that lead to the emergence of an AXI in the absence of \mathcal{I} and \mathcal{T} , both of which are broken by the magnetic ordering. The 2' symmetry element denotes the product of a two-fold rotation (C_2) and the \mathcal{T} operation: $2' = C_2 \times \mathcal{T}$. C_2 rotates the lattice and the spins around the axis by π and \mathcal{T} then reverses the direction of the spins. As shown in detail in Supplementary Figs. 16 and 17, the 2' transformations leave the broken-helix order invariant and protect gapless surface Dirac cones that are not pinned to time-reversal-invariant momenta (TRIM). Surfaces not associated with a 2' axis have gapped Dirac cones and exhibit half-integer QAH-type conductivity. Our symmetry analyses and magnetization data predict that the surface states are highly tunable by a modest field of $\mu_0 H \approx 1$ to 2 T which is strong enough to polarize the magnetic moments along its direction. This induces a gap and, depending on the field's direction, creates new unpinned gapless states on previously gapped surfaces.

RESULTS

Neutron diffraction determination of the antiferromagnetic order. Figure 1a shows neutron diffraction data for the (h0l) reciprocal-lattice plane taken below $T_{\rm N} \approx 18$ K at T = 6 K, and Fig. 1b shows data along the (00l) direction taken above and below $T_{\rm N}$ at 30 and 6 K. Nuclear Bragg peaks occur in Fig. 1b at l = 2n positions for both temperatures whereas magnetic Bragg peaks only appear in the 6 K data. Two AF propagation vectors define the locations of the magnetic Bragg peaks: (1) peaks at $l = 2n \pm \tau_{1z}$ positions correspond to $\boldsymbol{\tau}_1 = (0, 0, \tau_{1z})$ with $\tau_{1z} = 0.303(1)$; (2) nuclear-forbidden peaks at l = 2n + 1positions in Fig. 1b correspond to $\tau_2 = (0, 0, 1)$ [20]. Within the (h0l) reciprocal-lattice plane, magnetic Bragg peaks matching τ_2 overlap with nuclear Bragg peaks with odd values of l when the conditions h = 3n + 1 or h = 3n + 2 (n = integer) are satisfied. The predicted A-type order would be consistent with magnetic Bragg peaks appearing only at positions corresponding to τ_2 . However, the existence of additional magnetic Bragg peaks at τ_1 reveals the presence of more complex helical or spin-density-wave type (itinerant) AF order. Our measurements cannot distinguish between these two types of order, but our DFT calculations reveal that the Eu 4f bands are located well below the Fermi level which is more supportive of local-moment helical order.

Using magnetic symmetry analysis and single-crystal refinements to our data from the TRIAX triple-axis spectrometer and the CORELLI time-of-flight spectrometer, we discover that EuIn₂As₂ has the complex broken-helix AF order illustrated in Fig. 1d and Supplementary Figure 5. It consists of ferromagnetically-aligned layers with $\mu \perp c$ that are helically stacked along c. We find that the orthorhombic MSG $C2'2'2_1$ (No. 20.33) describes the symmetry, but for continuity we refer to directions with respect to the hexagonal chemical unit cell. We find $\mu = 6.0(3) \mu_{\rm B}/{\rm Eu}$ at T = 6 K, which is smaller than the expected value of 7.0 $\mu_{\rm B}/{\rm Eu}$ and the saturation moment of $\mu_{\rm sat} = 7.00(6) \mu_{\rm B}$ shown below and in Supplementary Figure 11. We note that neutron diffraction studies of other Eu containing compounds report less than 7.0 $\mu_{\rm B}/{\rm Eu}$ [21, 22], and, as shown below, the ordered moment is

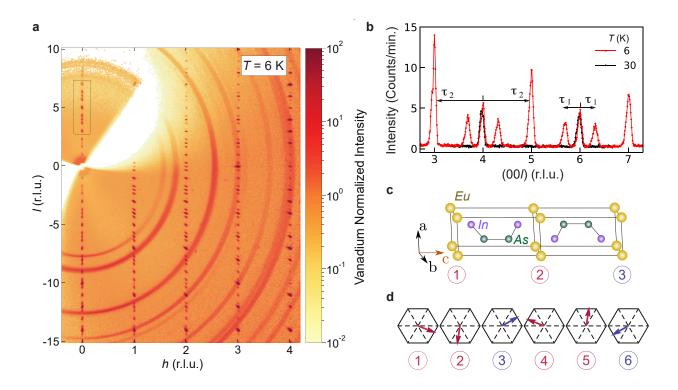


Figure 1. Neutron diffraction determination of the broken-helix magnetic order. a, Data for the (h0l) reciprocal-lattice plane measured at a temperature of T = 6 K with the CORELLI spectrometer [19]. Bragg peaks from the single-crystal sample appear as dots, whereas Bragg peaks due to the polycrystalline Al sample holder appear as rings centered at 0. b, Scans along the (00l)reciprocal-lattice direction for 6 K (red) and 30 K (black) made with the TRIAX instrument. The 30 K data show Bragg peaks solely due to the chemical lattice, and the two sets of magnetic Bragg peaks appearing in the 6 K data are labeled by the antiferromagnetic propagation vectors $\tau_1 = (0, 0, \tau_{1z})$, with $\tau_{1z} = 0.303(1)$, and $\tau_2 = (0, 0, 1)$ [20]. c, Chemical unit cell of EuIn₂As₂ where the numbers correspond to labeling in panel d. d, Layer-by-layer diagram of the 6 K broken-helix order using the notation of the hexagonal chemical unit cell. The magnetic unit cell is actually orthorhombic and is tripled along c with the **a**_{ortho} and **b**_{ortho} orthorhombic unit-cell axes lying along [$\overline{110}$] and -[110], respectively. Each Eu layer is ferromagnetically aligned with the ordered magnetic unit cell are colored red (layers 1, 2, 4 and 5) and blue (layers 3 and 6). Moments in the blue layers are constrained by symmetry to lie along [$\overline{110}$].

still increasing with decreasing temperature below 6 K. Details of the corrections performed to account for the strong thermal neutron absorption of Eu are given in the Methods Section and Supplementary Note 1.

To analyze the broken-helix order, we assume a tripling of the chemical unit cell since $\tau_z = 0.303(1) \approx \frac{1}{3}$ and the relatively small incommensurability results in maximum disagreement only at the 33rd Eu layer. Referring to Fig. 1d, we designate the two Eu crystallographic sites in $C2'2'_{21}$ as red and blue. This in turn indicates red and blue ferromagnetically-aligned layers, and allows for defining the helix turn angles $\phi_{\rm rr}$ and $\phi_{\rm rb}$ between successive red-red and red-blue layers, respectively. The MSG symmetry dictates that $\phi_{\rm rr} + 2\phi_{\rm rb} = 180^{\circ}$ and constrains magnetic moments in the blue layers to lie along [$\bar{1}10$]. Our refinements find that $\phi_{\rm rb} = 127(3)^{\circ}$ at T = 6 K, and more details of the refinements are given in Supplementary Figures 1–9 and Supplementary Tables I–III.

We simulate in Fig. 2a the integrated intensities for representative magnetic Bragg peaks for different values of $\phi_{\rm rb}$ using the determined MSG and $\mu \perp c$. Magnetic Bragg peaks corresponding to τ_2 disappear as $\phi_{\rm rb} \rightarrow 60^\circ$ (pure 60°-helix order), whereas magnetic Bragg peaks matching τ_1 disappear as $\phi_{\rm rb} \rightarrow 180^\circ$ (A-type order). We find that the pure 60°-helix order can be described by the higher-symmetry MSG $P6_12'2'$ (No. 178.159) and that the A-type order can be described by MSG Cm'c'm (No. 63.462). The darker shaded area in Fig. 2a indicates the experimental value of $\phi_{\rm rb}$ at T = 6 K.

Figures 2b and 2c reveal the temperature evolution of the AF order. Figure 2b displays the measured integrated intensities of the $(2, 0, 2) \pm \tau_1$ and (2, 0, 1) magnetic Bragg peaks scaled to 1 at T = 6 K. The curves suggest that μ continues to increase with decreasing temperature below 6 K. Two transitions are evident: the incommensurate magnetic Bragg peaks corresponding to τ_1 with $\tau_{1z} \approx \frac{1}{3}$ emerge at $T_{N1} = 17.6(2)$ K and commensurate magnetic Bragg peaks corresponding to τ_2 appear at $T_{N2} = 16.2(1)$ K. These transitions also appear in the magnetic susceptibility, resistance, and ¹⁵¹Eu Mössbauer data shown in Supplementary Figure 10. Figure 2c displays the temperature dependence of τ_1 which indicates that pure 60°-helix order first emerges at T_{N1} , and τ_{1z} decreases upon cooling until T_{N2} where broken-helix order emerges. This sequence follows the rightmost path in the group-subgroup chart in Supplementary Figure 18 which traces second-order magnetic transitions from the paramagnetic state to pure 60°-helix order to broken-helix order.

The inset to Fig. 2b shows the evolution of the helix turn angle ϕ below $T_{\rm N1}$. $\phi \approx 60^{\circ}$

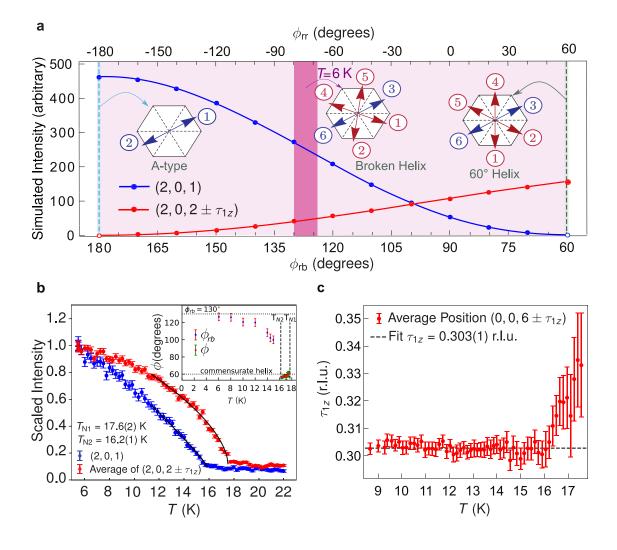


Figure 2. Details of the broken-helix magnetic order. a, Simulations of the magnetic neutron diffraction intensity for the (2, 0, 1) Bragg peak and the average of the $(2, 0, 2) \pm \tau_1$ Bragg peaks as functions of the broken-helix turn angles $\phi_{\rm rb}$ and $\phi_{\rm rr}$. b, Temperature dependencies of the integrated intensity of the (2, 0, 1) Bragg peak and the average integrated intensity for the $(2, 0, 2) \pm \tau_1$ magnetic Bragg peaks measured on the CORELLI spectrometer and scaled to 1 at T = 6 K. The inset displays the helix turn angles ϕ in the pure 60° -helix phase $(T_{\rm N2} < T \leq T_{\rm N1})$ and $\phi_{\rm rb}$ for the broken-helix phase $(T \leq T_{\rm N2})$. c, Temperature dependence of $\tau_1 = (0, 0, \tau_{1z})$ from the average of the positions of the $(0, 0, 6) \pm \tau_1$ magnetic Bragg peaks. In b, $\phi(T)$ is calculated from the temperature evolution of τ_{1z} . $\phi_{\rm rb}(T)$ is calculated from the temperature dependence of the ratio of the integrated intensity of the (0, 0, 5) magnetic Bragg peak to that of the $(006) - \tau_1$ magnetic Bragg peak. These data are from measurements made on the TRIAX spectrometer and are shown in Supplementary Figure 9.

at $T_{\rm N1}$ and slightly decreases upon cooling for $T_{\rm N2} < T < T_{\rm N1}$. The small change from 60° reflects the change in τ_{1z} . For $T < T_{\rm N2}$, the broken-helix order emerges and the inset to Fig. 2b plots $\phi = \phi_{\rm rb}$, which is calculated from data shown in Supplementary Figure 9. $\phi_{\rm rb}$ rapidly increases immediately below $T_{\rm N2}$ and approaches $\phi_{\rm rb} = 130^{\circ}$ as $T \to 0$ K. The temperature evolution of $\phi_{\rm rb}$ below $T_{\rm N2}$, while maintaining $\tau_{1z} = 0.303(1)$, agrees with the calculations in Fig. 2a showing that broken-helix order persists over a range of $\phi_{\rm rb}$.

Density functional theory calculations and symmetry analyses. Having established and described the emergence of complex helical order, we now discuss and compare the impacts of broken-helix, pure 60°-helix, and A-type order on the electronic band structure and topology. First, similar to previous reports [18], our DFT calculations and symmetry analyses find that A-type order creates an AXI state with inverted bulk bands near Γ and an electronic band gap of ≈ 100 meV. Looking at the phase diagram in Fig. 2a, we realize that by adiabatic continuation the magnetic symmetry can be lowered away from the pure 60° -helix or A-type ordered states by varying $\phi_{\rm rb}$ while maintaining the constraints that $\phi_{\rm rr} + 2\phi_{\rm rb} = 180^{\circ}$ and ordered moments in the blue layers lie along [$\bar{1}10$]. For example, starting from A-type order, reducing $\phi_{\rm rb}$ from 180° immediately breaks the mirror and \mathcal{I} symmetries present in MSG Cm'c'm.

Using this adiabatic continuation approach, we find via DFT calculations that a full band gap persists for any value of $\phi_{\rm rb}$. Figure 3a shows a diagram of the Brillouin zone and Fig. 3b shows the calculated electronic bands for $\phi_{\rm rb} = 130^{\circ}$. Figure 3c focuses on the gap region near Γ where band inversion is highlighted by green bars denoting As $4p_z$ orbital character, and Fig. 3d demonstrates that the inverted gap remains for pure 60°-helix order. Supplementary Figure 15 shows that this result holds for other values of $\phi_{\rm rb}$ spanning $180^{\circ} \leq \phi_{\rm rb} \leq 60^{\circ}$. Thus, the inverted gap remains across all three magnetic orders connected by the internal parameter $\phi_{\rm rb}$ and indicates that the topological phase is robust to changes to $\phi_{\rm rb}$. In contrast, we find that bands cross the Fermi level for the case of ferromagnetic order as shown in Supplementary Figure 15. This opens the possibility of controlling the band structure by applying a magnetic field strong enough to align μ along a single direction. This point is discussed further below.

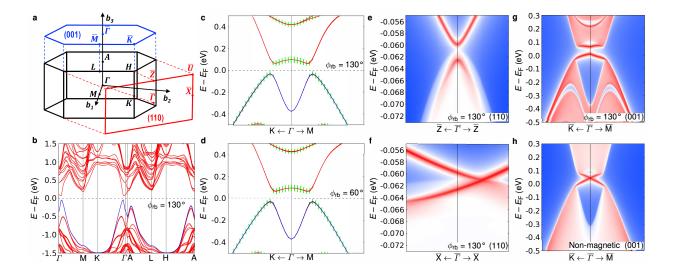


Figure 3. Bulk and surface electronic band structures for various magnetic ground states. a, Hexagonal Brillouin zone and the projected (110) and (001) surface-Brillouin zones with high-symmetry points (capital letters) and reciprocal-lattice axes ($\mathbf{b}_1 = \mathbf{a}^*, \mathbf{b}_2 = \mathbf{b}^*$, and $\mathbf{b}_3 = \mathbf{c}^*$) indicated. **b**, Bulk band structure along high-symmetry paths for broken-helix order with $\phi_{\rm rb} = 130^{\circ}$. $E_{\rm F}$ is the Fermi energy. c,d, Views of the minimal gap region along the K- Γ -M direction for $\phi_{\rm rb} = 130^{\circ}$ (broken-helix order) (c) and $\phi_{\rm rb} = 60^{\circ}$ (pure 60°-helix order) (d). The top valence band according to simple band filling is indicated in blue and the rest of the bands are colored red. Green vertical bars show As $4p_z$ orbital character and indicate band inversion near the minimal gap. e-h Surface bands for the (110) (e,f) and (001) (g,h) projected surfaces along high-symmetry lines for $\phi_{\rm rb} = 130^{\circ}$ (e,f,g). A Dirac cone exists on each surface, but the presence of a gap and whether or not the cone is pinned to a time-reversal-invariant momentum (TRIM) depends on symmetry: a gapless Dirac cone unpinned from a TRIM occurs for the (110) surface preserving the 2' symmetry axis. On the other hand, the (001) surface (g) has a gapped Dirac cone at $\overline{\Gamma}$ due to the absence of a 2' axis and any other symmetry that reverses an odd number of space-time coordinates. The surfaces with gapped Dirac cones support half-integer quantumanomalous-Hall-type conductivity. The nonmagnetic calculation for the (001) surface (h) has a gapless Dirac cone pinned to Γ . Note that panels e and f are zoomed in around the bottom of the band gap to show the details of the surface Dirac cone. $E_{\rm F}$ is inside the gap and the surface Dirac point is at $E_{\rm F} - 0.061$ eV, very close to the top of valence band projection. More details of the surface band structure are found in Supplementary Fig. 15g.

DISCUSSION

With these results in hand, we now address why EuIn₂As₂ is an AXI in its magneticallyordered phases despite the absence of \mathcal{I} . We determine $\theta = \pi$ in S_{θ} for the broken-helix order by finding that $\theta = \pi$ in the presence of \mathcal{I} for $\phi_{\rm rb} = 180^{\circ}$ (A-type order) via calculating the parity-based symmetry indicator $\mathbb{Z}_4 = \frac{1}{2} \sum_{k \in \text{TRIMs}} (n_k^+ - n_k^-) \mod 4 = 2$ [10, 11, 18, 23]. Here, $n_k^{\pm} \geq 0$ denotes the total number of filled bands with parity eigenvalue ± 1 at TRIM k. Since the band gap remains for $60^{\circ} \leq \phi_{\rm rb} \leq 180^{\circ}$, adiabatic continuity ensures that $\theta = \pi$ for all three magnetic structures, and, remarkably, the entire family of A-type, broken-, and pure 60°-helix states are AXIs as long as the Fermi energy resides in the band gap. It is the 2' symmetry operator along [110] and [$\overline{1}10$] for the broken-helix order and along [110] and [100] for the pure 60°-helix order that permits an AXI in the absence of \mathcal{I} [14].

The presence of 2' symmetry axes for the broken-helix order enforces an odd number of gapless unpinned surface Dirac cones on the ($\bar{1}10$) and (110) surfaces. More specifically, the unpinned gapless Dirac cones occur on surfaces perpendicular to the 2' axes. These exotic topological surface states appear in the presence of 2' because it reverses an odd number of space-time coordinates [14]. Figures 3e and 3f show the surface band structure for (110) wherein a gapless Dirac cone is seen which is offset from $\bar{\Gamma}$ along $\bar{\Gamma}-\bar{X}$. This result contrasts with the gapped Dirac cone at $\bar{\Gamma}$ on the (001) surface shown in Fig. 3g. For the case of no magnetic order, Fig. 3h shows a gapless Dirac cone on the (001) surface pinned to $\bar{\Gamma}$. These calculations did not include the Eu 4f orbitals. We find that $\mathbb{Z}_2 = 1$ which signals a strong topological insulator, rather than an AXI phase, for the non-magnetic state.

The AXI state protected by 2' symmetry is different from the AXI phase protected by a combination of \mathcal{T} and a translation recently proposed for MnBi₂Te₄ [24]. In MnBi₂Te₄, this symmetry is only unbroken on surfaces that contain the translation vector, where it leads to gapless Dirac cones that are pinned to TRIM. The Dirac cones are gapped on all other surfaces. In contrast, in EuIn₂As₂ the AXI state is protected by 2' symmetry, leading to unpinned Dirac surface states whenever the 2' axis is normal to the surface and gapped surface states appear on all other surfaces.

The different topological surface states resulting from the presence or absence of 2' symmetry leads to differing physical properties. To facilitate this discussion, Fig. 4a shows the relationships between real-space and reciprocal-lattice directions, and the direction(s) of the

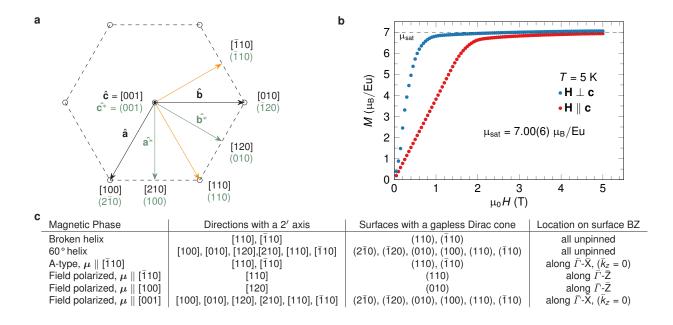


Figure 4. Tuning surface Dirac cones via an applied magnetic field. **a**, Diagram showing real-space (denoted by brackets) and reciprocal-space (denoted by parentheses) directions for the **ab** plane. The magnetic orthorhombic unit cells for broken-helix and A-type orders discussed in the main text have their \mathbf{a}_{orth} and \mathbf{b}_{orth} axes along [$\bar{1}10$] and -[110], respectively. **b**, Magnetization versus magnetic field curves for a temperature of T = 5 K and the field applied either perpendicular or parallel to **c**. **c**, A table indicating the 2' axis/axes, the surface(s) containing a gapless Dirac cone, and the location of the gapless Dirac cone on the projected surface Brillouin Zone(s) (BZ) for various zero-field and field-polarized magnetic states. The direction of the ordered magnetic moment $\boldsymbol{\mu}$ is indicated where appropriate. The results for the broken-helix and 60°-helix phases assume that the blue Eu layers lie along [$\bar{1}10$].

2' axis/axes are listed in Fig. 4c for various magnetic states. For the broken-helix order, (001) and other gapped surfaces without a 2' axis exhibit half-integer QAH-type conductivity [4]. On the other hand, similar to a 3D topological insulator, the gapless surface Dirac cones on (110) and ($\bar{1}10$) support dissipationless charge transport where sweeping $E_{\rm F}$ through the Dirac point switches the handedness of the chirality associated with the itinerant charge. Similar analyses of the surface states can be performed for the pure 60°-helix and A-type order phases. In particular, Fig. 4c shows that the pure 60°-helix phase supports multiple surfaces with an unpinned gapless Dirac cone. The consequences of the gapless Dirac cones being exotically unpinned from TRIM, which require absence of Kramer's degeneracy, however, lacks investigation.

Figure 4c also illustrates that the surface states are highly tunable by an external magnetic field, and Fig. 4b shows that modest field strengths of $\mu_0 H \approx 1$ to 2 T are sufficient to polarize the Eu magnetic moments along any direction at T = 5 K. For example, the row in Fig. 4c corresponding to broken-helix order indicates that a gapless completely unpinned Dirac cone exists only on the ($\bar{1}10$) and (110) surfaces, and, therefore, all of the other surfaces have a gapped Dirac cone. For a field-polarized state with $\mu \parallel [100]$, Fig. 4c indicates that only the (010) surface has a gapless surface Dirac cone and its node is constrained to lie along $\bar{\Gamma}-\bar{Z}$. Thus, a field provides an effective means for switching by inducing a gap in previously gapless surface states while eliminating the gap in previously gapped surface states. Further, the position of the node of the gapless Dirac cone can change from being completely unpinned to being constrained to a line. Figure 4c also highlights the direct correlation between the existence of a 2' axis and gapless surface states. More details of our symmetry analyses are given in Supplementary Table IV and in the associated discussion in Supplementary Note 5.

Finally, a true AXI state only occurs for insulating compounds, but resistance and angleresolved-electron-photoemission data for EuIn₂As₂ are consistent with it being a slightly hole-doped compensated semimetal [17, 25], see Supplementary Figure 10c. Thus, $E_{\rm F}$ needs to be shifted into the bulk gap for an AXI to be observed. Fortunately, the robust quantization of $\theta = \pi$ with respect to changes of $\phi_{\rm rb}$ suggests that small perturbations to the magnetic order potentially caused via tuning $E_{\rm F}$ will not destroy the symmetry leading to an AXI state. Further, the fact that τ_1 is not exactly $\frac{1}{3}$ does not invalidate our analysis, because the slight incommensurability should enter into the calculation of θ as only a small perturbation. Investigations into growing thin films may permit gating or strain to shift the chemical potential, and growth of films on magnetic substrates may allow for simultaneous gating while facilitating magnetic-field control of the topological surface states.

To conclude, we have established that complex helical magnetic order emerges in $EuIn_2As_2$ upon cooling below $T_{N1} = 17.6(2)$ K (pure 60°-helix order) and $T_{N2} = 16.2(1)$ K (broken-helix order). Both of these helical orders create 2' symmetry axes that protect an AXI state in the absence of \mathcal{I} . Our DFT calculations and symmetry analyses show that the band topology is robust to changes of the helical turn angles, such that the magnetic order can change from A-type, to broken-helix, to pure 60°-helix order while maintaining

the same topological phase. We further find that the existence of 2' symmetry axes protects gapless Dirac cones on specific surfaces which are unpinned from TRIM and that the other surfaces possess gapped Dirac cones and exhibit QAH-type conductivity. Our magnetization results show that only a moderate magnetic field of $\mu_0 H \approx 1$ to 2 T is necessary for tuning the direction of the magnetic moment, which our symmetry analyses show can choose the surfaces supporting gapless unpinned Dirac cones. This opens up the possibility for novel device development as well as further research into the physical properties associated with unpinned surface Dirac cones. For example, experiments exploring if these exotic surface states can be moved in the surface Brillouin zone via pressure or strain may yield insight into basic material interactions and reveal unexpected properties. The intrinsic low-symmetry broken-helix magnetic order of EuIn₂As₂ offers an excellent opportunity to study and tune exotic surface states in a magnetic topological-crystalline insulator.

METHODS

Sample synthesis. Single crystals of $EuIn_2As_2$ were grown using a flux method similar to Ref. [15] and found to be single phase via powder x-ray diffraction. An initial composition of Eu:In:As = 3 : 36 : 9 was weighed out and packed in fritted alumina crucibles [26], followed by sealing in a fused silica tube. The prepared ampoule was first heated up to 300°C over 2 hours and held there for an hour, then heated up to 580°C over 3 hours and held there for 2 hours, and finally heated up to 900°C over 10 hours followed by a 2 hour dwell. The intermediate dwells were to ensure maximum dissolving and incorporation of the volatile elements into the melt. The final dwell was followed by a 48 hour cool down to 770°C, at which point excess flux was decanted using a centrifuge. This process yielded plate-like crystals of EuIn₂As₂ with masses of a few milligrams.

Magnetization experiments. Magnetization measurements were made on singlecrystal samples down to T = 2 K under applied magnetic fields up to $\mu_0 H = 5$ T using a Quantum Design, Inc. Superconducting Quantum Interference Device.

Neutron diffraction experiments. Neutron diffraction measurements were made on the TRIAX triple-axis spectrometer at the University of Missouri Research Reactor, and on the time-of-flight (TOF) CORELLI spectrometer at the Spallation Neutron Source at Oak Ridge National laboratory [19]. Single-crystal samples with masses of 4.5 and 11.6 mg were used on TRIAX and CORELLI, respectively. The samples were attached to Al sample mounts and cooled down to T = 6 K using closed-cycle He refrigerators. The integrated intensities of recorded Bragg peaks were corrected for the effects of neutron absorption using the MAG2POL [27] software according to the procedure described in Ref. [28]. The samples were flat rectangular plates with thicknesses of 0.1 mm along [001]. The TRIAX sample has an approximate width of 3 mm along [100] and approximate length of 2 mm along [010]. The CORELLI sample has an approximate width of 3 mm along [110] and approximate length of 3 mm along [1 $\overline{10}$].

The TRIAX experiments were performed in elastic mode with incident and final neutron energies of $E_{i,f} = 14.7$ and 30.5 meV. Söller slit collimators with divergences of 60'-60'-80'-80' were inserted before the pyrolytic graphite (PG) (002) monochromator, between the monochromator and sample, between the sample and PG (002) analyzer, and between the analyzer and detector, respectively. PG filters were inserted before and after the sample to eliminate higher-order beam harmonics. The sample's (*h0l*) reciprocal-lattice plane was aligned within the horizontal scattering plane. In order to collect data for purely nuclear and magnetic Bragg peaks, a series of (*h0l*) reflections were recorded at T = 30 and 6 K, i.e. significantly above T_{N1} and below T_{N2} , respectively. Each Bragg peak was fitted with a Gaussian lineshape in order to determine its integrated intensity (area), center, and full width at half maximum. The magnetic signals of the low-temperature τ_2 Bragg peaks were then extracted by subtracting the integrated intensity of the 30 K nuclear contribution when appropriate. A Lorentz factor ($L = \frac{1}{\sin 2\theta}$) was also applied. Refinements were made with FULLPROF [29]. Throughout this work, error bars represent one standard deviation.

CORELLI experiments were performed at several temperatures above and below T_{N1} and T_{N2} with the (hol) plane set horizontal. However, the spectrometer employs 2-D positionsensitive detectors which allow for recording some Bragg peaks above and below this plane. The TOF measurement technique employs a white neutron beam, and the sample was rotated around its vertical axis at discrete intervals in order to cover a large swath of reciprocal space. Individual Bragg peaks were obtained by performing cuts through the 2-D maps recorded by the instrument, returning intensity versus **Q** profiles of the peaks. Integrated intensities were in turn calculated by adding up all of the data points located in the peak profile that were above background. To account for the pulsed beam's non-linear distribution of wavelengths, a normalization to vanadium scattering was applied. CORELLI data used for the structural and magnetic refinements presented in Supplementary Note 1 are restricted to a bandwidth of incoming neutron energies of 45–55 meV in order to accurately correct for neutron absorption.

Electronic-band structure calculations. Band structures using density functional theory with spin-orbit coupling were calculated with the Perdew-Burke-Ernzerhof (PBE) exchange-correlation functional, a plane-wave basis set, and the projected-augmented-wave method as implemented in VASP [30, 31]. To account for the half-filled strongly-localized Eu 4f orbitals, a Hubbard-like [32] U value of 5.0 eV is used. For different helical magnetic structure with $\tau \approx (0, 0, 1/3)$, i.e. the hexagonal unit cell is tripled along the **c** axis with atoms fixed in their bulk positions. A Monkhorst-Pack $12 \times 12 \times 1$ k-point mesh with a Gaussian smearing of 0.05 eV including the Γ point and a kinetic-energy cutoff of 250 eV have been used. To search for possible band gap closing points in the full Brillouin Zone, a tight-binding model based on maximally localized Wannier functions [33] was constructed to reproduce closely the bulk band structure including spin-orbit coupling in the range of $E_{\rm F} \pm 1$ eV with Eu sdf, In sp and As p orbitals as implemented in WannierTools [34].

DATA AVAILABILITY

The neutron scattering data that support our analysis of the ground state magnetic order in the $EuIn_2As_2$ are displayed in the Supplementary Note 1 and/or available in the MDF Open data repository with the identifiers DOI: 10.18126/u3j8-aplr and URL: https://doi.org/10.18126/u3j8-aplr.

- Hasan, M. Z. & Kane, C. L. Colloquium: Topological insulators. *Review of Modern Physics* 82, 3045-3067 (2010).
- Yan, B. & Felser, C. "Topological Materials: Weyl Semimetals." Annual Review of Condensed Matter Physics 8, 337-354 (2017).
- [3] Armitage, N. P., Mele, E. J. & Vishwanath, A. "Weyl and Dirac semimetals in threedimensional solids." *Review of Modern Physics* **90**, 015001 (2018).
- [4] Vanderbilt, D. Berry Phases in Electronic Structure Theory: Electric Polarization, Orbital Magnetization and Topological Insulators (Cambridge Univ. Press, Cambridge, 2018).

- [5] Ye, J. et al. Berry Phase Theory of the Anomalous Hall Effect: Application to Colossal Magnetoresistance Manganites. Physical Review Letters 83, 3737-3740 (1999).
- [6] Taguchi, Y., Oohara, Y., Yoshizawa, H., Nagaosa, N. & Tokura, Y. Spin Chirality, Berry Phase, and Anomalous Hall Effect in a Frustrated Ferromagnets. *Science* 291, 2573-2576 (2001).
- [7] Ueland, B. G. et al. Controllable chirality-induced geometrical Hall effect in a frustrated highly correlated metal. Nature Communications 3, 1067 (2012).
- [8] Yu, Rui *et al.* Quantized anomalous Hall effect in magnetic topological insulators. *Science* 329, 61-64 (2010).
- [9] Wan, X., Turner, A. M., Vishwanath, A. & Savrasov, S. Y. Topological semimetal and Fermiarc surface states in the electronic structure of pyrochlore iridates. *Physical Review B* 83, 205101 (2011).
- [10] Turner, A. M., Zhang, Y., Mong, R. S. K. & Vishwanath, A. Quantized response and topology of magnetic insulators with inversion symmetry. *Physical Review B* 85, 165120 (2012).
- [11] Watanabe, H., Po, H. C. & Vishwanath, A. Structure and topology of band structures in the 1651 magnetic space groups. *Science Advances* 4, (2018).
- [12] Wilczek, F. Two applications of axion electrodynamics. *Physical Review Letters* 58, 1799-1802 (1987).
- [13] Qi, X.-L., Hughes, T. L. & Zhang, S.-C. Topological field theory of time-reversal invariant insulators. *Physical Review B* 78, 195424 (2008).
- [14] Fang, C. & Fu, L. New classes of three-dimensional topological crystalline insulators: Nonsymmorphic and magnetic. *Physical Review B* 91, 161105 (2015).
- [15] Goforth, A. M., Klavins, P., Fettinger, J. C. & Kauzlarich, S. M. Magnetic properties and negative colossal magnetoresistance of the rare earth zintl phase EuIn₂As₂. *Inorganic Chemistry* 47, 11048-11056 (2008).
- [16] Rosa, P. F. S. et al. Electron spin resonance of the intermetallic antiferromagnet EuIn₂As₂.
 Physical Review B 86, 094408 (2012).
- [17] Zhang, Y. et al. In-plane antiferromagnetic moments and magnetic polaron in the axion topological insulator candidate EuIn₂As₂. Physical Review B 101, 205126 (2020).
- [18] Xu, Y., Song, Z., Wang, Z., Weng, H. & Dai, X. Higher-order topology of the axion insulator EuIn₂As₂. *Physical Review Letters* **122**, 256402 (2019).

- [19] Ye, F., Liu, Y., Whitfield, R., Osborn, R. & Rosenkranz, S. Implementation of cross correlation for energy discrimination on the time-of-flight spectrometer CORELLI. *Journal of Applied Crystallography* 51, 315-322 (2018).
- [20] $\tau_2 = (0,0,1)$ is equivalent to $\tau_2 = (0,0,0)$ for $P6_3/mmc$. We use $\tau_2 = (0,0,1)$ to facilitate presentation of the diffraction data.
- [21] Gong, D. et al. Canted Eu magnetic structure in EuMnSb₂. Physical Review B 101, 224422 (2020).
- [22] Chattopadhyay T., Schnering H. G. & Brown P. J. Neutron diffraction study of the magnetic ordering in EuAs₃. Journal of Magnetism and Magnetic Materials 28, 247-249 (1982).
- [23] Khalaf, E., Po, H. C., Vishwanath, A. & Watanabe, H. Symmetry Indicators and Anomalous Surface States of Topological Crystalline Insulators. *Physical Review X* 8, 031070 (2018).
- [24] Zhang, D. et al. Topological Axion States in the Magnetic Insulator MnBi₂Te₄ with the Quantized Magnetoelectric Effect. Physical Review Letters 122, 206401 (2019).
- [25] Regmi, S. et al. Temperature dependent electronic structure in a higher order topological insulator candidate EuIn₂As₂. Physical Review B 102, 165153 (2020).
- [26] Canfield, P. C., Kong, T., Kaluarachchi, U. S. & Jo, N. H. Use of frit-disc crucibles for routine and exploratory solution growth of single crystalline samples. *Philosophical Magazine* 96, 84-92 (2016).
- [27] Qureshi, N. Mag2Pol: A program for the analysis of spherical neutron polarimetry, flipping ratio and integrated intensity data. Journal of Applied Crystallography 52, 175-185 (2019).
- [28] Busing, W. R. & Levy, H. A. High-speed computation of the absorption correction for singlecrystal diffraction measurements. Acta Crystallographica 10, 180-182 (1957).
- [29] Rodríguez-Carvajal, J. Recent advances in magnetic structure determination by neutron powder diffraction. *Physica B: Condensed Matter* **192**, 55-69 (1993).
- [30] Kresse, G. & Furthmüller, J. Efficient iterative schemes for ab-initio total-energy calculations using a plane-wave basis set. *Physical Review B* 54, 11169-11186 (1996).
- [31] Kresse, G. & Furthmüller, J. Efficiency of ab-initio total energy calculations for metals and semiconductors using a plane-wave basis set. *Computational Materials Science* 6, 15-50 (1996).
- [32] Dudarev, S. L., Botton, G. A., Savrasov, S. Y., Humphreys, C. J. & Sutton, A. P. Electronenergy-loss spectra and the structural stability of nickel oxide: An LSDA+U study. *Physical Review B* 57, 1505-1509 (1998).

- [33] Marzari, N., Mostofi, A. A., Yates, J. R., Souza, I. & Vanderbilt, D. Maximally localized Wannier functions: Theory and applications. *Review of Modern Physics* 84, 1419-1475 (2012).
- [34] Wu, Q., Zhang, S., Song, H.-F., Troyer, M. & Soluyanov, A. A. WannierTools : An opensource software package for novel topological materials. *Computer Physics Communications* 224, 405-416 (2018).

ACKNOWLEDGEMENTS

This research was supported by the Center for Advancement of Topological Semimetals, an Energy Frontier Research Center funded by the U.S. Department of Energy Office of Science, Office of Basic Energy Sciences, through the Ames Laboratory under Contract No. DE-AC02-07CH11358. D.C.J., S.L.B., and A.K. were supported by U.S. Department of Energy Office of Science, Office of Basic Energy Sciences, Field Work Proposals at the Ames Laboratory operated under the same contract number. This research used resources at the Spallation Neutron Source, a DOE Office of Science User Facility operated by the Oak Ridge National Laboratory. This research used resources at the Missouri University Research Reactor. Financial support for this work was provided by Fonds Québécois de la Recherche sur la Nature et les Technologies. Much of this work was carried out while D.H.R. was on sabbatical at Iowa State University and Ames Laboratory, and their generous support under the U.S. Department of Energy Office of Science, Office of Basic Energy Sciences Contract No. DE-AC02-07CH11358 during this visit is gratefully acknowledged.

AUTHOR CONTRIBUTIONS

S.X.M.R, B.G.U., R.J.M., T.W.H., and F.Y. conducted neutron scattering experiments. S.X.M.R. refined the neutron diffraction data and determined the magnetic structure with input from A.K., B.G.U., D.C.J., and R.J.M. B.K., S.L.B., and P.C.C. synthesized crystals and performed magnetization and resistance measurements. D.H.R. performed Mössbauer measurements. T.V.T., P.P.O., L.L.W, and A.V. performed symmetry analyses concerning the topologically protected properties. L.L.W. performed electronic-band-structure calculations.

ADDITIONAL INFORMATION

Supplementary Information is available.

COMPETING INTERESTS


The authors declare no competing interests.

Magnetic crystalline-symmetry-protected axion electrodynamics and field-tunable unpinned Dirac cones in $EuIn_2As_2$

(Supplementary Information)


Supplementary Note 1. SINGLE-CRYSTAL NEUTRON DIFFRACTION EXPERI-MENTS

In the following, we detail our determination of the $T < T_{N2}$ magnetic order using the TRIAX and CORELLI data.

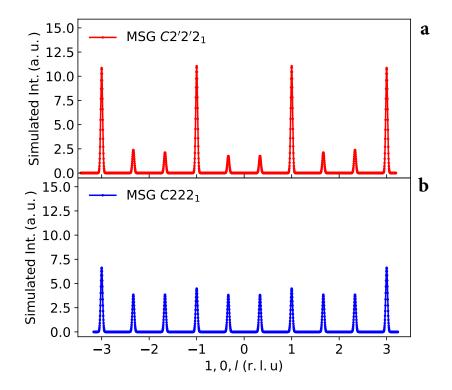

Supplementary Figure 1. Simulated magnetic neutron diffraction patterns for brokenhelix order with $\mu \perp c$. a,b, Simulated pattern for magnetic space group (MSG) $C2'2'2_1$ (a) and MSG $C222_1$ (b) with helical-turn angles $\phi_{\rm rr} = -80^\circ$, $\phi_{\rm rb} = 130^\circ$, and $\mu = 6.0 \ \mu_{\rm B}$.

We first detail the symmetry analysis and magnetic space group (MSG) determination procedures which utilized the Bilbao Crystallography Server [1] and simulations of diffraction patterns made with MAG2POL [2]. Combinations of two distinct magnetic phases individually corresponding to τ_1 [approximated to $\tau_1 = (0, 0, \frac{1}{3})$] and $\tau_2 = (0, 0, 1)$ were discarded as they returned spin-density-wave rather than local-moment type AF order. Local-moment type

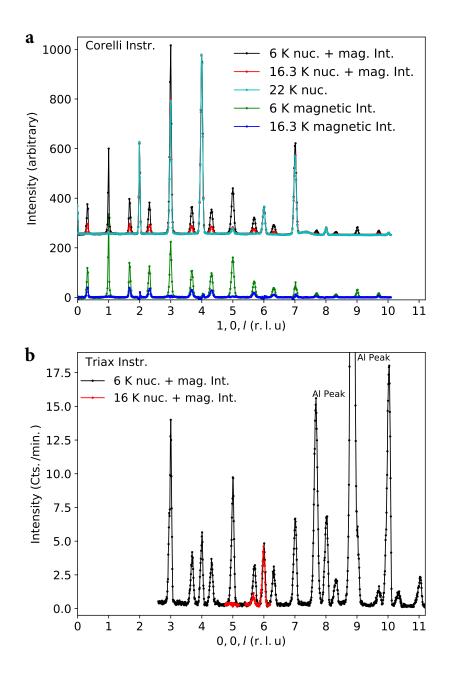

Supplementary Figure 2. Diffraction patterns from measurements made on CORELLI and TRIAX. a, Line cuts of CORELLI data along (10*l*) collected at T = 6 (black), 16.3 (red) and 22 K (cyan). For clarity, a 250 counts/minute offset has been applied. The 16.3 (blue) and 6 K (green) data not offset are the results of subtracting off the 22 K data in order to visualize the magnetic diffraction. b, (00*l*) line cut collected on TRIAX at 6 (black) and 16 K (red).

Supplementary Table I. The Eu crystallographic sites in magnetic space group $C2'2'2_1$ (No. 20.33). Positions are given in the setting of the parent space group $P6_3/mmc$ (No. 194) with lattice parameters (a, b, 3c). m_i are components of the ordered magnetic moment μ . This table was created using the Bilbao Crystallography Server [1].

Atoms	Coordinates with Magnetic Moments	Multiplicity	m_x, m_y, m_z $(\mu_{ m B}/{ m Eu})$
Eu(red)	$(0,0,0 \mid m_x, m_y, m_z)(0,0,\frac{1}{6} \mid m_y, m_x, m_z)$ $(0,0,\frac{1}{2} \mid -m_x, -m_y, m_z)(0,0,\frac{2}{3} \mid -m_y, -m_x, m_z)$	4	$m_x = 2.35$ $m_y = 6.69$ $m_z = 0.00$
Eu(blue)	$(0,0,\frac{1}{3} \mid m_x, -m_x, m_z)(0,0,\frac{5}{6} \mid -m_x, m_x, m_z)$	2	$m_x = -3.39$ $m_z = 0.00$

AF order is more accurate than itinerant AF order based on our band-structure calculations indicating that bands with significant Eu 4f character lie well below the Fermi energy $E_{\rm F}$.


We next searched for a single MSG with symmetry elements leading to reflection conditions consistent with both au_1 and au_2 that is also a subgroup of the paramagnetic grey MSG $P6_3/mmc1'$ (No. 194.264). We found that MSGs Cmcm (No. 63.457), Cm'c'm (No. $(63.452), C2'2'2_1$ (No. 20.33), $C222_1$ (No. 20.31), and $P2_1/m$ (No. 11.50) are consistent with both propagation vectors. Note that additional MSGs are consistent with these propagation vectors but require further symmetry reductions and were thus disregarded. We ruled out *Cmcm*, *Cm'c'm*, *C*222₁ and *P*2₁/*m* by simulating diffraction patterns for both $\mu \perp c$ and $\mu \parallel c$ and comparing them to T = 6 K data. Examples of simulated profiles are shown in Supplementary Figure 1 which can be compared to 6 K diffraction data in Supplementary Figure 2a. In particular, Supplementary Figure 1 illustrates the clear difference between the relative heights of commensurate and incommensurate magnetic Bragg peaks for $C2'2'_{1}$ and $C222_1$, revealing the incompatibility of the latter with the 6 K data in Supplementary Figure 2a. We are thus left with $C2'2'_{2_1}$ as the MSG for the $T < T_{N_2}$ AF order. Supplementary Table I shows the positions for the two Eu sites [referred to as Eu(red) and Eu(blue)] in $C2'2'_{1}$ assuming a tripling along **c** of the hexagonal chemical-unit cell. Constraints imposed by the MSG on the orientation of the ordered magnetic moment associated with each Eu site are also indicated.

We next detail the steps of the refinements. Examples of TRIAX data not corrected for neutron absorption are shown in Supplementary Figs. 2b and 3. Supplementary Tables II and III list the Bragg peaks used for the refinements along with their integrated intensities and the corresponding absorption-corrected values. First, a single-crystal refinement to the absorption corrected T = 30 K data [corresponding to the paramagnetic (PM) phase] using the known chemical structure of the material [3, 4] was performed allowing the scale factor and atomic positions to vary. The site occupations and thermal parameters could not be refined. The magnetic structure was then refined using the 6 K absorption-corrected data corresponding to the magnetic order. This refinement used the magnetic symmetry files created on the Bilbao crystallography server [1] for $C2'2'_{1}$ and the parameters found from the refinement to the 30 K data. To account for the localized nature of the Eu^{2+} magnetic moments, a refinement constraint of equal values of the total ordered magnetic moment μ for both sites was used. Supplementary Figure 4 illustrates the refinement which returned a goodness-of-fit value of $R_{\rm F} = 7.50$. The determined magnetic structure at 6 K is the brokenhelix order diagrammed in Fig. 1d as well as Supplementary Figure 5 with turn angles of $\phi_{\rm rr} = -80(2)^{\circ}$ and $\phi_{\rm rb} = 130(1)^{\circ}$, and $\mu = 5.9(2) \ \mu_{\rm B}/{\rm Eu}$ lying within the **ab** plane.

This result is confirmed by a refinement to T = 6 K data collected on the CORELLI instrument for a different sample. Data corresponding to a reduced incident neutron energy bandwidth centered at E = 50 meV (1.54 Å) and spanning 45–55 meV were used in order to accurately perform a correction for neutron absorption using MAG2POL [2]. The absorption correction and refinement procedures employed were similar to these previously described for the TRIAX data analysis. Sets of 18 nuclear (22 K) and 108 magnetic (6 K) independent reflections were used. We obtained turn angles of $\phi_{\rm rr} = -68(2)^{\circ}$ and $\phi_{\rm rb} = 124(1)^{\circ}$, $\mu =$ $6.1(2) \mu_{\rm B}/{\rm Eu}$ and a goodness-of-fit value of $R_{\rm F} = 17.2$. Figure 6 illustrates the quality of this refinement.

In the following, we detail our determination of the $T_{N2} < T \leq T_{N1}$ magnetic order using TRIAX and CORELLI data.

A reliable refinement of the TRIAX data for $T_{N2} < T \leq T_{N1}$ could not be completed. This is due to the rather weak magnetic intensities at these temperatures because of the smaller value of μ and the strong neutron absorption. Nevertheless, data in Fig. 2b and Supplementary Figure 2 reveal the systematic absence of Bragg peaks corresponding to τ_2

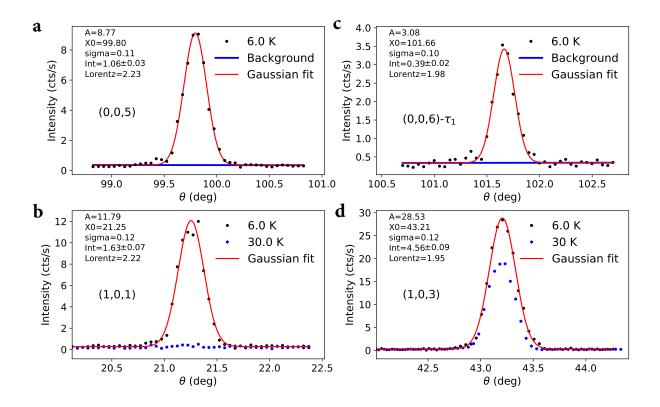


Supplementary Figure 3. Examples of Bragg peaks collected on TRIAX. a–d, Measured profiles for T = 6 and 30 K. The 30 K data are substituted by background lines for purely magnetic reflections in **a** and **c**. Each peak is fit using the combination of a Gaussian lineshape $[y=A\exp(-\frac{(x-x_0)^2}{2\sigma^2})]$ and a linear background. The obtained fit parameters and the corresponding integrated intensities corrected by the Lorentz factor (labeled as Int) are displayed in each panel.

for $T > T_{N2}$. The presence of magnetic Bragg peaks at positions corresponding to τ_1 is in agreement with the stabilization of pure 60°-helix order and the reflection conditions for MSGs $P6_12'2'$ (No. 178.159), $P6_122$ (No. 178.155), $P6_52'2'$ (No. 179.165), and $P6_522$ (No. 179.161). As shown by the group-subgroup graph given in Supplementary Figure 18 and discussed further below, MSGs $P6_122$ and $P6_522$ are inconsistent with the stabilization of broken-helix magnetic order with MSG $C2'2'2_1$ for $T < T_{N2}$. The remaining two MSGs $(P6_12'2' \text{ and } P6_52'2')$ represent right-handed and left-handed chiral versions of the same pure 60°-helix order and cannot be differentiated with our data. Using either one of these MSGs and the intensity of the $(0, 0, 6) - \tau_1$ reflection measured on TRIAX at 16 K (see Supplementary Figure 2b), we calculate that $\mu = 2.0(2) \mu_{\rm B}/{\rm Eu}$ at 16 K.

To complement these results, we made a refinement for the $T_{\rm N2} < T \leq T_{\rm N1}$ magnetic

Supplementary Table II. Integrated intensities for Bragg peaks recorded on TRIAX at T = 30 K. The correction for neutron absorption was applied using MAG2POL [2] as described in Ref. [5].


(h, 0, l)	Integrated Intensity	Absorption Corr. Intensity
(1,0,0)	0.29 ± 0.02	0.41 ± 0.03
(1, 0, 2)	1.70 ± 0.05	2.47 ± 0.07
(1, 0, 3)	3.08 ± 0.06	4.65 ± 0.09
(0, 0, 6)	0.60 ± 0.03	1.53 ± 0.08
(1, 0, 4)	5.04 ± 0.21	8.08 ± 0.34
(2,0,0)	0.23 ± 0.02	0.33 ± 0.03
(2, 0, 2)	1.22 ± 0.03	1.79 ± 0.04
(2, 0, 3)	1.96 ± 0.03	2.93 ± 0.04
(2, 0, 4)	2.72 ± 0.10	4.17 ± 0.15

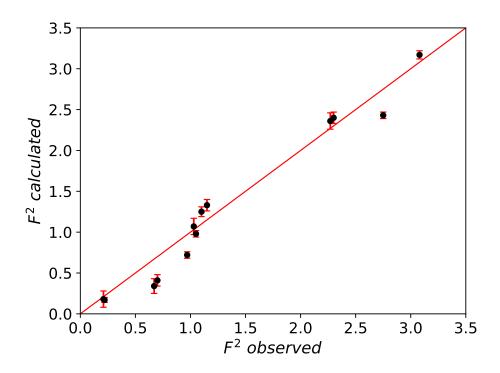


Supplementary Figure 4. Calculated versus observed square of the magnetic structure factor F^2 for the refinement to data in Supplementary Table III using MSG $C2'2'2_1$. The line indicates the refinement, which has a goodness of fit of $R_{\rm F} = 7.5$.

Supplementary Table III. Integrated intensities for Bragg peaks recorded on TRIAX at T = 6 K. The correction for neutron absorption was applied using MAG2POL [2] as described in Ref. [5]. When present, nuclear contributions to the Bragg peaks were subtracted using the 30 K data given in Table. II.

	(h, 0, l)	Integrated Intensity	Absorption Corr. Intensity
($(0,0,4) - \tau_1$	0.31 ± 0.02	1.15 ± 0.07
($(0,0,4) + \boldsymbol{\tau}_1$	0.34 ± 0.02	1.10 ± 0.06
($(1,0,0)+ au_1$	0.48 ± 0.03	0.67 ± 0.04
	(0,0,5)	1.06 ± 0.03	3.08 ± 0.09
	(1, 0, 1)	1.63 ± 0.07	2.30 ± 0.10
($(1,0,2)-oldsymbol{ au}_1$	0.49 ± 0.03	0.70 ± 0.04
	(1, 0, 3)	1.50 ± 0.07	2.27 ± 0.10
($(0,0,6)- au_1$	0.39 ± 0.02	1.03 ± 0.05
($(0,0,6) + \boldsymbol{\tau}_1$	0.43 ± 0.03	1.05 ± 0.07
	(0, 0, 7)	1.20 ± 0.03	2.75 ± 0.07
($(0,0,8)+ au_1$	0.47 ± 0.05	0.97 ± 0.10
($(2,0,2) + \tau_1$	0.15 ± 0.03	0.22 ± 0.04
($(2,0,4) - \tau_1$	0.14 ± 0.02	0.21 ± 0.03

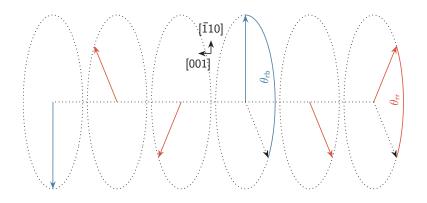

Supplementary Figure 5. **Diagram of the broken-helix order.** The ordered moment lies \perp [001], and the ferromagnetically aligned Eu layers are labeled red or blue, with the blue layers constrained to point along either [$\bar{1}10$] or $-[\bar{1}10]$. $\phi_{\rm rr}$ and $\phi_{\rm rb}$ are the helical-turn angles between successive red-red and red-blue layers, respectively.

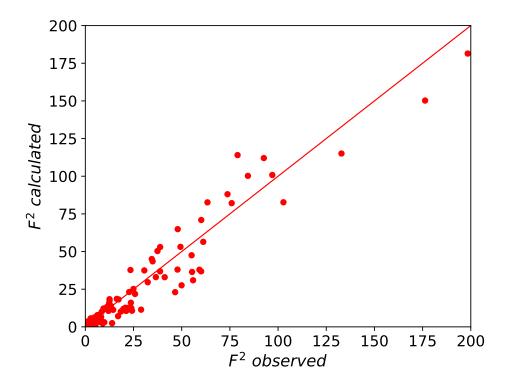


Supplementary Figure 6. Calculated versus observed square of the magnetic structure factor F^2 for the refinement to 6 K CORELLI data using MSG $C2'2'2_1$. The line indicates the refinement, which has a goodness of fit of $R_{\rm F} = 17.2$.

phase using MSG $P6_12'2'$ and data for 20 independent Bragg peaks corresponding to τ_1 taken with CORELLI at 16.3 K. Similar to above, data corresponding to a reduced incident neutron energy bandwidth centered at E = 50 meV (1.54 Å) and spanning 45–55 meV were used in order to accurately perform a correction for neutron absorption using MAG2POL [2]. In agreement with our TRIAX estimation, the refinement returns $\mu = 2.5(5) \mu_{\rm B}/\text{Eu}$ with a goodness-of-fit value of $R_{\rm F} = 7.37$. Supplementary Figure 7 illustrates the quality of this refinement.

In the following, we detail our determination of the magnetic phases' temperature evolution using CORELLI data.


The CORELLI data also allowed us to precisely and efficiently visualize the appearance of magnetic Bragg peaks and their positions upon cooling down to T = 6 K. Figure 2b displays data from magnetic order parameter measurements and Fig. 2c displays the temperature evolution of the incommensurability associated with τ_1 below $T_{\rm N1}$. Large sets of

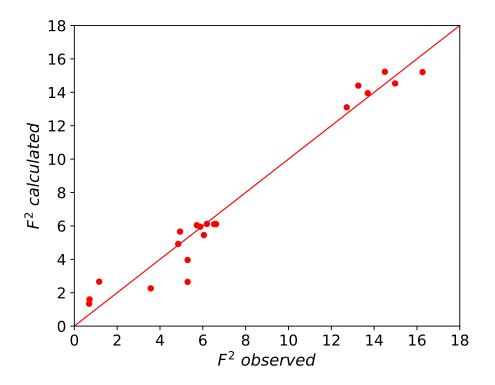

Supplementary Figure 7. Calculated versus observed squares of the magnetic structure factor F^2 for the refinement to 16.3 K CORELLI data using MSG $P6_12'2'$. The line indicates the refinement, which has a goodness of fit of $R_{\rm F} = 7.37$.

data collected at 6, 16.3 and 22 K are shown in Fig. 1a and Supplementary Figure 2a. The positions of the magnetic peaks at 6 K lead to the precise determination of the two antiferromagnetic (AF) propagation vectors: (1) $\tau_1 = (0, 0, \tau_{1z})$ with $\tau_{1z} = 0.303(1)$ corresponding to the incommensurate peaks; (2) $\tau_2 = (0, 0, 1)$ [6] corresponding to commensurate magnetic Bragg peaks. Note that for τ_2 some nuclear and magnetic Bragg peaks overlap. CORELLI data were also used to determine symmetry and ordered-moment-direction aspects of the magnetic phases. For instance, we observed the absence of magnetic Bragg peaks along the (h00) direction. Supplementary Figure 8 further shows that the (1,0,0) Bragg peak has no significant temperature dependence which, based on our simulations, indicates that μ does not have a ferromagnetic component along c. This information, along with the magnetization data shown in Fig. 4b and Supplementary Figure 11b support the conclusion that μ lies in the **ab** plane below T_{N1} .

Lastly, for comparison with Fig. 2b, absorption corrected TRIAX data for the temper-

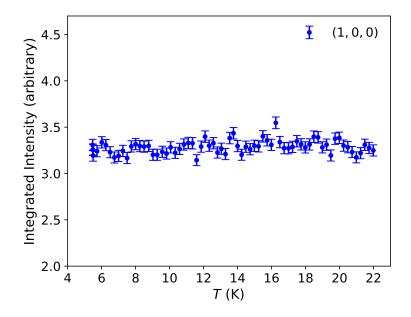


Supplementary Figure 8. Temperature dependence of the integrated intensity of the (1,0,0) Bragg peak measured on CORELLI. The featureless temperature dependence between T = 5.5 and 22 K indicates an absence of a ferromagnetic moment pointing along c.

ature dependencies of the (0, 0, 5) and $(0, 0, 6 - \tau_{1z})$ Bragg peaks are displayed in Supplementary Figure 9.

Supplementary Note 2. MAGNETIC SUSCEPTIBILITY, MAGNETIZATION, AND RESISTANCE

Supplementary Figure 10a reproduces the magnetic order parameter plots determined from neutron diffraction that are also shown in Fig. 2b. We find features corresponding to the two Néel temperatures $[T_{N1} = 17.6(2) \text{ and } T_{N2} = 16.2(1) \text{ K}]$ in magnetization, resistance, and ¹⁵¹Eu Mössbauer spectroscopy measurments as well. Supplementary Figure 10b. shows the temperature dependence of the magnetic susceptibility $\chi = \frac{M}{H}$ and $\frac{d(\chi T)}{dT}$ for an applied magnetic field of $\mu_0 H = 0.01$ T. Changes in the slope of $\chi(T)$ are evident near the dashed lines indicating T_{N1} and T_{N2} .

Standard 4-wire resistance (R) measurements were made on single-crystal samples down to T = 2 K with a Quantum Design, Inc. Physical Property Measurement System using Pt leads attached with Epotek H20E silver epoxy. Resistance data plotted in Supplementary

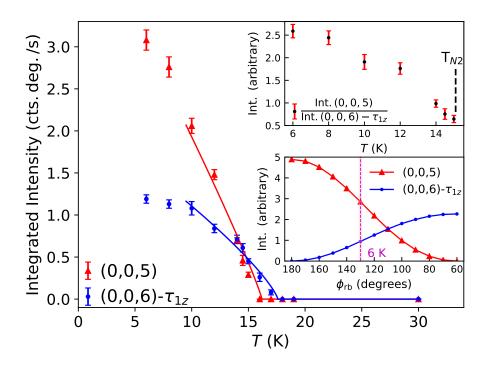


Supplementary Figure 9. Magnetic order parameters measured on TRIAX. The temperature evolutions of the integrated intensities of the (0, 0, 5) and $(0, 0, 6 - \tau_{1z})$ Bragg peaks. Lines are guides to the eye. The top right inset displays the ratio of the integrated intensities of the two peaks. The bottom right inset shows a simulation of the peaks intensities as a function of the helix turn angle $\phi_{\rm rb}$.


Figure 10c show a loss of spin-disorder scattering upon cooling through $T_{\rm N1}$ and a distinct change in slope upon further cooling through $T_{\rm N2}$.

Next, Supplementary Fig. 10d shows that the Fourier components of the hyperfine field found by ¹⁵¹Eu Mössbauer spectroscopy measurements also show evidence for the two magnetic ordering transitions. More details concerning the Mössbauer measurements and the plots in Supplementary Figure 10d are given in a separate section below.

A Curie-Weiss fit to high-temperature $\chi(T)$ data is shown in Supplementary Figure 11a and yields an effective magnetic moment of $\mu_{\text{eff}} = 8.05(7) \ \mu_{\text{B}}/\text{Eu}$ and a Weiss temperature of $\theta_{\text{CW}} = 18.6(1)$ K. μ_{eff} is consistent with Eu²⁺, whereas the positive value of θ_{CW} indicates predominantly ferromagnetic interactions and likely reflects the magnetic interactions associated with the ferromagnetically-aligned moments within the Eu planes. The Curie-Weiss fits were performed after taking the appropriate polycrystalline average of data taken with

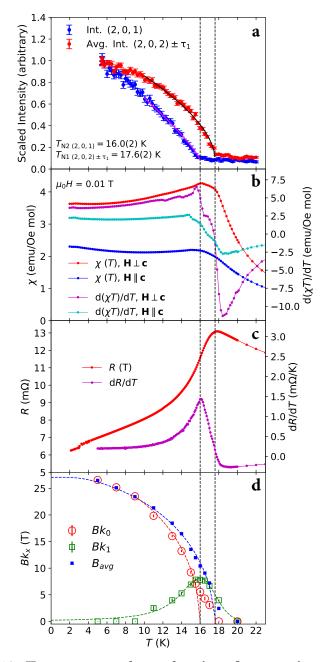

Supplementary Figure 10. Temperature dependencies of magnetic order parameter, magnetic susceptibility, resistance, and ¹⁵¹Eu hyperfine field. a, Magnetic order parameter of the (2,0,1) and $(2,0,2)\pm\tau_1$ Bragg peaks measured on CORELLI [7] scaled to be 1 at T = 6 K. The Néel temperatures T_{N1} and T_{N2} found by neutron diffraction are indicated by vertical dashed lines through the different panels. b, Magnetic susceptibility (red+blue) and its derivative with respect to temperature (magenta+cyan). c, Temperature evolution of the electrical resistance (red), and its derivative with respect to temperature (magenta). d, Temperature dependence of the Fourier components of the hyperfine field (B_{hf}) from analysis of ¹⁵¹Eu Mössbauer spectra.

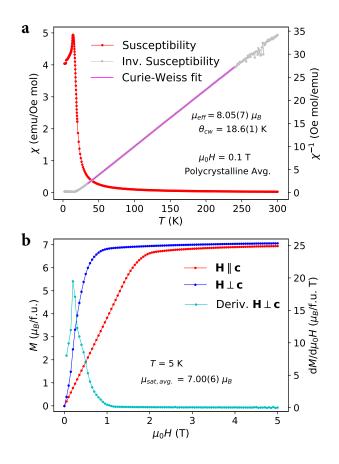

Supplementary Figure 11. Curie-Weiss fit and magnetization versus magnetic field data at T = 5 K. a, The magnetic susceptibility (red) and its inverse (grey) plotted versus temperature for an applied magnetic field of $\mu_0 H = 0.1$ T. The linear region of the inverse susceptibility is fitted with a Curie-Weiss model (fuchsia). b, Data from magnetization measurements performed for $\mathbf{H} \parallel \mathbf{c}$ (red) and $\mathbf{H} \perp \mathbf{c}$ (blue). The field derivative of the $\mathbf{H} \perp \mathbf{c}$ data $(\frac{dM}{dH})$ is also shown (cyan). Magnetic anisotropy consistent with the ordered magnetic moment lying perpendicular to \mathbf{c} is evident, and a saturation magnetization of 7.00(6) $\mu_{\rm B}/\text{f.u.}$ is obtained. The $\mathbf{H} \perp \mathbf{c}$ data show an inflection point at $\mu_0 H \approx 0.2$ T that is visible as a peak in $\frac{dM}{dH}$.

H applied either perpendicular or parallel to the crystalline \mathbf{c} axis.

Magnetization versus field measurements made with $\mathbf{H} \perp \mathbf{c}$ or $\mathbf{H} \parallel \mathbf{c}$ reveal magnetic anisotropy consistent with magnetic moments ordered solely within the **ab**-plane. These data appear in Fig. 4b and in Supplementary Figure 11b. A saturated moment of $\mu_{\text{sat}} =$ 7.00(6) $\mu_{\text{B}}/\text{f.u.}$ is achieved as expected for Eu²⁺, where $M_{\text{sat}} = gS = 7 \mu_{\text{B}}/\text{f.u.}$ with g = 2and S = 7/2. g is the spectroscopic splitting factor and S is the spin. Data for $\mathbf{H} \perp \mathbf{c}$ show an inflection point at $H \approx 2$ kOe which is seen as a sharp peak in $\frac{dM}{dH}$. This feature may indicate a continuous crossover from helical- to fan-type AF order with increasing field [8].

Supplementary Note 3. DETAILS OF THE ¹⁵¹Eu MÖSSBAUER STUDY

¹⁵¹Eu Mössbauer spectroscopy measurements were carried out using a 4 GBq ¹⁵¹SmF₃ source driven in sine mode and calibrated using a standard ⁵⁷Co<u>Rh</u>/ α -Fe foil. Isomer shifts are quoted relative to EuF₃ at ambient temperature. The sample was cooled in a vibrationisolated closed-cycle helium refrigerator with the sample in helium exchange gas. Spectra for different temperatures are shown in Supplementary Figure 12.


In order to determine the hyperfine field $B_{\rm hf}$, the spectra in Supplementary Figure 12 are fit as follows. Spectra for $T \leq 10$ K and $T \gtrsim 18$ K are fit to a sum of Lorentzian lineshapes with the positions and intensities derived from a full solution to the nuclear Hamiltonian [9]. However, spectra taken between 10 K and 18 K are fit using a model that derives a distribution of hyperfine fields from an (assumed) incommensurate magnetic structure with a sinusoidally modulated value for the ordered magnetic moment μ [10, 11]. We next describe this distribution model.

If we denote the antiferromagnetic (AF) propagation vector as \mathbf{k} (instead of $\boldsymbol{\tau}$), assume that the modulation in μ along the direction of the propagation vector can be written in terms of its Fourier components, and that the hyperfine field is a linear function of μ at any given site, then the variation of $B_{\rm hf}$ with distance x along \mathbf{k} can be written as:[10]

$$B_{\rm hf}(kx) = Bk_0 + \sum_{l=0}^{n} Bk_{2l+1} \sin[(2l+1)kx] .$$
(1)


 Bk_n are the odd Fourier coefficients of the field modulation and kx is a position in reciprocal space along the direction of **k**. As $+B_{\rm hf}$ and $-B_{\rm hf}$ are indistinguishable, kx only needs to run over half the modulation period. Variations of this modeling have been used to fit spectra for EuPdSb [10] and Eu₄PdMg [12].

The fitting sequence is as follows: Starting with an initial set of Bk_n , the evolution of $B_{\rm hf}$ along **k** is evaluated as shown in Supplementary Figure 13. From $B_{\rm hf}$ versus kx, the histogram in Supplementary Figure 14 is constructed, and the calculated ¹⁵¹Eu Mössbauer spectrum is obtained through a sum of magnetic patterns weighted according to the histogram. A conventional non-linear least-squares minimization routine is then used to adjust

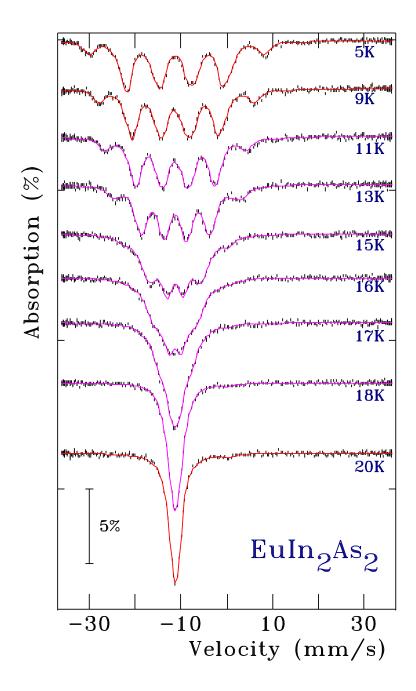

Supplementary Figure 12. ¹⁵¹Eu Mössbauer spectra showing the evolution of the magnetic order on heating from a temperature of T = 5 to 20 K. Solid lines are fits using the full Hamiltonian (red lines, 5 K, 9 K and 20 K) or the incommensurate modulated model (magenta lines). A description of the fitting procedure is given in the text.


 Bk_n , a uniform baseline, an overall scale factor, and the isomer shift. It is essential to note that since the modulation is explicitly assumed to be incommensurate with the crystal lattice, positions along kx do not correspond to specific positions in the chemical unit cell.

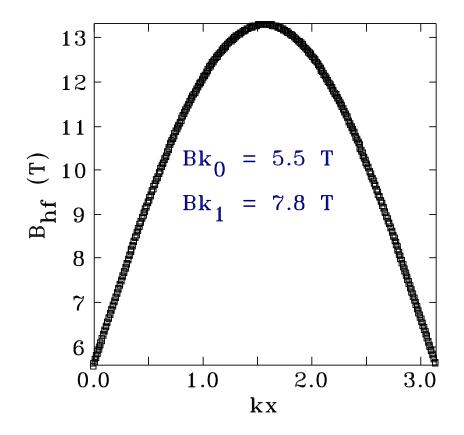

Supplementary Figure 13. Magnitude of the hyperfine magnetic field as a function of distance along the direction of the magnetic-propagation vector for T = 16 K. $kx = \pi$ corresponds to the length of the Brillouin zone along kx. Values of the Fourier components Bk_0 and Bk_1 discussed in the text are indicated.

Rather, they represent how $B_{\rm hf}$ is sampled by the Eu. As the periodicity of the modulation and the crystal cell are not related by a simple rational fraction, neighboring points along the kx axis will be far apart in real space.

The room temperature ¹⁵¹Eu Mössbauer spectrum has a single peak much like the T = 20 K spectrum shown in Supplementary Figure 12. Fitting the spectrum gives an isomer shift of -11.35(2) mm/s, indicating Eu²⁺. No trivalent impurity (within a sensitivity of 1%) was detected. The similar isomer shifts at 20 K (-11.28(1) mm/s) and 5 K (-11.20(2) mm/s) confirm that the valence does not change over the temperature range studied. The fitted $B_{\rm hf}$ of 26.46(5) T at 5 K is typical of a fully ordered Eu²⁺ moment [13], and the sharp lines are consistent with the Eu being in a single magnetic environment at 5 K. The trigonal $\bar{3}m$. point symmetry of the Eu site leads to the requirement of an axially-symmetric electric-

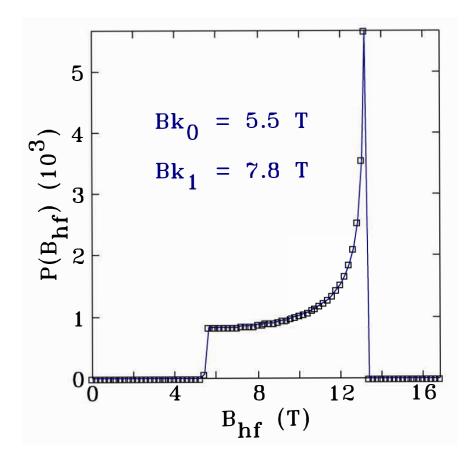

Supplementary Figure 14. Histogram for fitting the T = 16 K Mossbäuer spectrum. $B_{\rm hf}$ is the hyperfine field and $P(B_{\rm hf})$ is the probability distribution of $B_{\rm hf}$.

field-gradient tensor, so the measurements are not sensitive to rotations of μ about c.

Supplementary Figure 12 shows that increasing the temperature not only leads to a gradual reduction in $B_{\rm hf}$, but also to a clear increase in the linewidth. This broadening reflects a distribution of environments for the Eu, and may arise from either dynamic effects (e.g. slow paramagnetic relaxation) or from a static distribution of hyperfine fields. The former is inconsistent with both the observed evolution of the spectral shapes and with the continued observation of well-defined magnetic Bragg peaks in the neutron diffraction data. This leaves a static distribution of hyperfine fields as the source of the line broadening. As Eu^{2+} is the only magnetic species present, a distribution in $B_{\rm hf}$ necessarily reflects a distribution of moment magnitudes μ . We therefore turn to the distribution model given by Supplementary Equation (1) that has been successful in describing the order in a number Eu- and Fe- based compounds [10–12, 14]. The solid lines through the spectra shown in Supplementary Figure 12 for $9 < T \leq 18$ K demonstrate that this model provides an


excellent description of the spectra.

Looking at Supplementary Figure 10d, for T = 6 K only the uniform term is needed and B_{avg} is equivalent to Bk_0 . Thus, at 6 K no modulation of μ is present, in agreement with the magnetic structure determined by neutron diffraction. However, by 11 K a weak modulation is needed to fit the spectrum: Bk_1 is no longer zero and Bk_0 starts to fall below B_{avg} . $Bk_1(T)$ peaks at ≈ 16 K and Bk_0 is only lost by 18 K. Fitting $B_{avg}(T)$ to a $J = \frac{7}{2}$ Brillouin function (appropriate for Eu²⁺) yields 17.5(1) K, while doing the same for $Bk_0(T)$ gives 15.9(1) K, which is also where $Bk_1(T)$ peaks. These two ordering temperatures are in good agreement with $T_{N1} = 17.6(2)$ K and $T_{N2} = 16.2(1)$ K. determined by neutron diffraction. We also remark that $Bk_1(T)$ is finite proximate to the AF phase transitions, suggesting that the inferred modulation in μ may be related to the critical region around these phase transitions.

To summarize, our Mössbauer measurements indicate that the initial AF order that develops on cooling through 17.5 K is dominated by an incommensurate, sine-like, modulation of μ along the direction of the AF propagation vector, but a significant uniform contribution is likely also present. On further cooling, both contributions grow, but at 16 K the modulation starts to decline and the uniform term quickly dominates, until by 9 K only order with a uniform (fixed-size) value of μ remains.

Supplementary Note 4. ADDITIONAL DENSITY FUNCTIONAL THEORY RE-SULTS

Density functional theory (DFT) calculations including spin-orbit coupling were made after adiabatically changing $\phi_{\rm rb}$, in accordance with the magnetic space group constraints $\phi_{\rm rr} + 2\phi_{\rm rb} = 180^{\circ}$ and blue moments alternately pointing along $\pm [\bar{1}10]$, to values spanning the region between pure 60°-helix and A-type order shown in Fig. 2a of the main text. Results of these calculations are shown in Figs. 3b–3d and Supplementary Figures 15a– 15e, where the value of $\phi_{\rm rb}$ for each panel is indicated by the number at the top right. As described in the main text, band-inversion and the electronic-band gap remain over the whole $60^{\circ} \leq \phi_{\rm rb} \leq 180^{\circ}$ region which implies that $\theta = \pi$ over the whole region. Supplementary Figure 15f shows that for ferromagnetic order with the ordered moment lying within the basal plane band inversion remains but degeneracy is lifted and a Fermi surface forms.

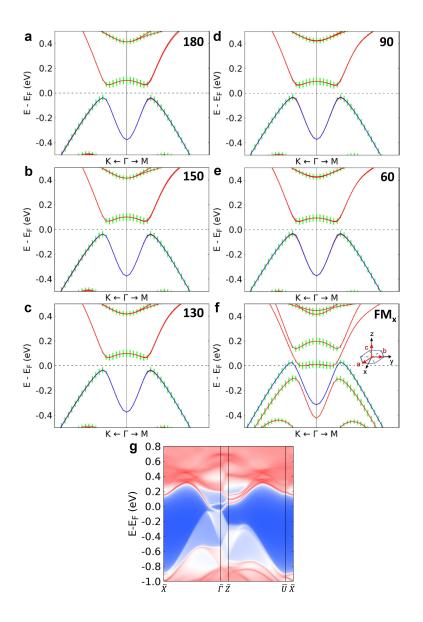

Supplementary Figure 15. Further results from density-functional-theory calculations including spin-orbit coupling. a–e, Results from calculations made after adiabatically changing the turn angle $\phi_{\rm rb}$ associated with the broken-helix ground state. The value for $\phi_{\rm rb}$ is indicated in each panel by the top-right number. The top valence band according to simple band filling is in blue and the rest of the bands are in red. Green vertical bars show As $4p_z$ orbital character and indicate band inversion near the minimal gap. **f**, Results for a ferromagnetic ground state with moments oriented along **x**. The relationship of **x** to the lattice is shown in the included diagram. **g**, Full view of the surface band structure and band gap for the (110) projected surface along high-symmetry lines for $\phi_{\rm rb} = 130^{\circ}$.

A $12 \times 12 \times 3$ k-point mesh was used for the ferromagnetic calculation. Supplementary Figure 15g displays a full view of the surface band structure for the (110) projected surface along high-symmetry lines for $\phi_{\rm rb} = 130^{\circ}$. This extended view complements Figs. 3e and 3f, revealing both the gap at $E_{\rm F}$ and the surface Dirac cone at $E_{\rm F} - 0.061$ eV.

Supplementary Note 5. SYMMETRY ANALYSIS OF THE MAGNETIC PHASES

In this section, we provide a detailed symmetry analysis of the magnetic space groups (MSGs) for the two observed magnetic phases: (i) the pure 60°-helix order emerging upon cooling through $T_{\rm N1} = 17.6(2)$ K, and (ii) the broken-helix order existing for $T \leq T_{\rm N2}$. The material crystallizes according to the crystallographic space group (SG) $P6_3/mmc$ (No. 194) and is built of hexagonal layers of Eu alternating with blocks of In₂As₂ along the crystallographic **c** axis [3, 4], see Fig. 1c. The unit cell contains two Eu layers separated by a distance of c/2. In this section, the **c** axis will also be denoted as $\hat{c} \equiv [001]$ or \hat{z} , and in Supplementary Figure 16a we depict our choice of \hat{x} , \hat{y} , and \hat{z} axes with respect to the in-plane hexagonal directions $\hat{a} \equiv [100]$ and $\hat{b} \equiv [010]$.

The crystallographic space group $P6_3/mmc$ (No. 194) is generated by the following elements: inversion (\mathcal{I}), a $2\pi/3$ rotation around \hat{z} ($C_{3,[001]}$), a π rotation around \hat{z} followed by a $\frac{c}{2}$ translation along \hat{z} ({ $C_{2,[001]} | 00\frac{c}{2}$ }), and a π rotation around [100]: $C_{2,[100]}$. In the paramagnetic phase, the MSG is $P6_3/mmc1'$ (No. 194.264), which is a grey group containing time-reversal [\mathcal{T} (also indicated by the prime symbol)] combined with any symmetry operation of the crystallographic SG.

The two helical magnetically ordered phases are described by a magnetic unit cell that is three times larger along \hat{c} than the crystallographic unit cell, $c_{\text{mag}} = 3c$. As a result, the two additional translations \hat{c} and $2\hat{c}$, which are $\hat{c}_{\text{mag}}/3$ and $2\hat{c}_{\text{mag}}/3$ with respect to the magnetic unit cell, need to be considered. Combined with the crystallographic SG, this leads to additional symmetry operations which are non-symmorphic with respect to the magnetic unit cell. Moreover, while \mathcal{T} by itself is no longer a symmetry element of the magnetically ordered phase, \mathcal{T} combined with some spatial operations of the crystallographic SG are symmetry elements of the magnetic phase, and the MSG is of black-white type. The MSG is defined by the subset of operations generated by the generators of the paramagnetic MSG $P6_3/mmc1'$ combined with the translations { $\hat{c} = \hat{c}_{\text{mag}}/3, 2\hat{c} = \hat{c}_{\text{mag}}/3$ } which leave the magnetic order invariant.

We first analyze the symmetries of the pure 60°-helix phase that appears upon cooling through $T_{\rm N1} = 17.6(2)$ K as shown in Fig. 2b in the main text. The ordered magnetic moments μ are ferromagnetically aligned in each Eu layer. As shown in Supplementary Figure 16, neighboring layers are oriented at an angle of $\pm 60^{\circ}$ to each other such that the structure describes a pure 60° helix propagating along \hat{z} . This magnetic structure repeats every six Eu-layers, leading to a tripling of the chemical unit cell. The ordered moments in layers 3 and 6 point along the high-symmetry directions [$\bar{1}10$] and [$1\bar{1}0$] (denoted in blue), respectively. We verified that there are 12 magnetic symmetry operations that leave the structure invariant. For a helix that rotates counterclockwise around \hat{c} , the corresponding MSG is $P6_12'2'$ (No. 178.159), which is generated by the set

$$\left\{ \mathbb{1}, \left\{ C_{2,[001]} \middle| 00 \frac{c_{\text{mag}}}{2} \right\}, C_{3,[001]} \left\{ \mathbb{1} \middle| 00 \frac{c_{mag}}{3} \right\}, \mathcal{T}C_{2,[100]} \right\} , \qquad (2)$$

where 1 is the identity element. Note that a helix with opposite helicity (i.e. clockwise rotation around \hat{c}) is described by MSG $P6_52'2'$ (No. 179.165).

The symmetry of the pure 60°-helix order can be readily checked graphically, as shown in Supplementary Figure 16. It is important to note that a rotation around an axis different from [001] leads to a *reshuffling* of the Eu-layers as shown in Supplementary Figures 16b and 16c for $C_{2,[100]}$. The reshuffling depends on the choice of origin of the coordinate system. Here, we choose the origin to lie in Eu layer 2. Whereas the form of the generators depends on the choice of origin, the resulting MSG [P6₁2'2' (No. 178.159)] is independent of the origin choice.

Importantly, these MSGs contain the element $\mathcal{T}C_{2,[100]}$, which reverses an odd number of space-time dimensions, and therefore leads to a quantization of the magnetoelectric coupling (axion) angle θ . Further, the magnetic symmetry $\mathcal{T}C_{2,[100]}$ protects exotic unpinned gapless surface Dirac states on the $(2\bar{1}0)$ surface [15]. This MSG contains five more $2' = \mathcal{T}C_2 =$ elements that protect unpinned Dirac cones on five more surfaces. These are the surfaces ($\bar{1}20$) and (110), which are related to ($2\bar{1}0$) by $C_{3,[001]}$ and $C^2_{3,[001]}$ rotations, respectively, as well as the surfaces (100), (010) and ($\bar{1}10$), which are related to each other by $C_{3,[001]}$ rotations. A list of the 2' symmetry axes and surfaces with gapless Dirac cones for the various magnetic phases is given in Fig. 4c.

In the broken-helix state occurring for $T \leq T_{N2} = 16.2(1)$ K, the (blue) ordered magnetic

moments in Eu-layers 3 and 6 continue to point along the high-symmetry directions [$\overline{110}$] and [$1\overline{10}$], respectively. The red ordered moments (red layers), however, are not oriented at $\pm 60^{\circ}$ with respect to the layer immediately above or below as shown in Figs. 1d, 2a, and Supplementary Figure 5. As a result, $C_{3,[001]}$, which is a symmetry element for the 60°-helix order, is lost in the broken-helix state. The broken-helix phase is described by MSG $C2'2'2_1$ (No. 20.33), which is generated by the element set


$$\{\mathbb{1}, \{C_{2,[001]} | 00\frac{c_{\text{mag}}}{2}\}, \mathcal{T}C_{2,[110]}\}.$$
(3)

Here, we have set the origin to lie in Eu layer 3 (blue). Since the MSG contains the element $\mathcal{T}C_{2[110]}$, θ is still quantized. The [110] direction is perpendicular to the high-symmetry direction of the blue moments. Note that, in contrast to the 60°-helix order, here we only have two 2' operations, one 2' axis along [110] and the other along [110]. This has profound consequences on the location of the unpinned gapless surface Dirac cones protected by 2' [15]: they appear only on (110) and (110) surfaces for broken-helix magnetic order, whereas they can also be found on four other surfaces [(100), (010), (210) and (120)] for the pure 60° helix state.


We next consider A-type antiferromagnetic order similar to that discussed in Supplementary Reference [16] for MSG Cmcm (No. 63.457) and ordered moments lying along [100]. Here, the ordered Eu magnetic moments are again ferromagnetically-aligned in each Eulayer, but the stacking along \hat{c} is simply antiferromagnetic. In contrast to Supplementary Reference [16], we consider moments lying parallel to the high-symmetry [$\bar{1}10$] directions and use MSG Cm'c'm. The A-type order is smoothly connected to the experimentally determined broken-helix and pure 60°-helix orders by varying the helical-turn angles $\phi_{\rm rb}$ and $\phi_{\rm rr}$, where $\phi_{\rm rr} = \pi - 2\phi_{\rm rb}$ as shown in Fig. 2a of the main text. $|\phi_{\rm rb}| = |\phi_{\rm rr}| = \pi$ for the A-type state. Since the crystallographic unit cell contains two Eu layers, the magnetic unit cell is equal to the crystallographic one in this case. The MSG of A-type order with ordered moments along [1 $\bar{1}0$] is Cm'c'm (No. 63.462), which is generated by

$$\{\mathbb{1}, \mathcal{I}, \{C_{2,[001]} | 00\frac{c}{2}\}, \mathcal{T}C_{2,[110]}\}.$$
 (4)

We find that gapless surface Dirac cones, which can be shifted away from the center of the surface Brillouin zone, occur on the (110) and ($\overline{1}10$) surfaces. In contrast to the 60°-helix order and the broken-helix order, here the Dirac cones are constrained to occur along the

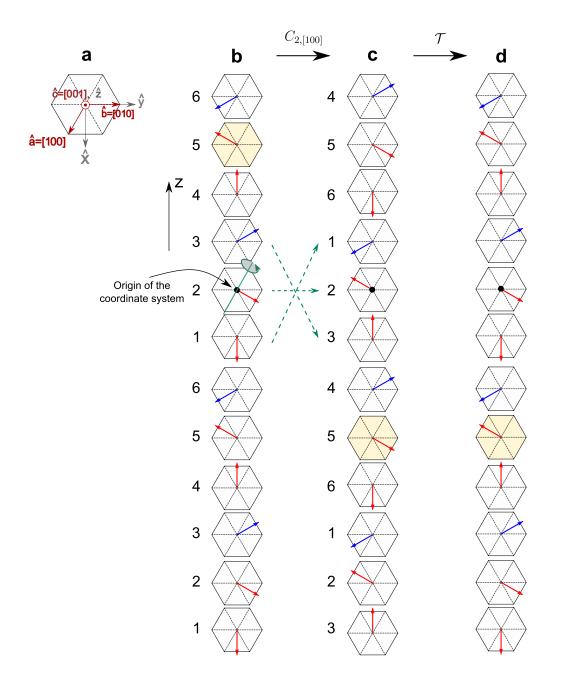

Supplementary Figure 16. Action of $\mathcal{T}C_{2,[100]}$ on pure 60°-helix order. a, Crystallographic \hat{a} , \hat{b} and \hat{c} axes for hexagonal EuIn₂As₂ together with our choice of \hat{x} , \hat{y} and \hat{z} axes. b, 60°-helix order where two magnetic unit cells are shown. c, d, The remaining panels show the action of $\mathcal{T}C_{2,[100]}$ on the 60°-helix phase: a π rotation around the [100] axis (c) followed by a time-reversal operation (d) leaves the initial structure invariant. Therefore, $\mathcal{T}C_{2,[100]}$ is a symmetry operation of the pure 60°-helix order. One of the Eu-layers is highlighted to facilitate the visualization of the action of each of the space-time transformations. Note that we set the origin of the coordinate system in the second Eu layer.

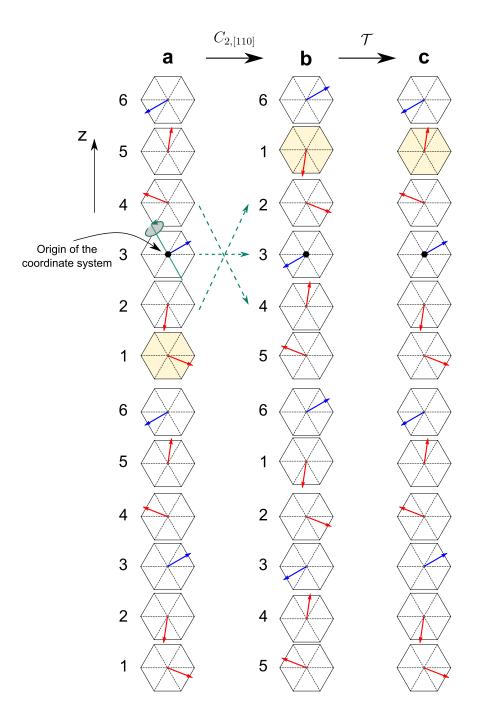


Supplementary Figure 17. Action of $\mathcal{T}C_{2,[110]}$ on broken-helix order. a, Initial magnetic structure, where two magnetic unit cells are shown. b, c, A π rotation around the [110] axis (b) followed by a time-reversal operation (c) leaves the initial structure invariant. Therefore, $\mathcal{T}C_{2,[110]}$ is a symmetry operation of the broken-helix structure. Similar to Supplementary Figure 16, one of the Eu-layers is highlighted to facilitate the visualization of the action of each of the space-time transformations. Here, the origin of the coordinate system is set in the third Eu layer.

 $\overline{\Gamma}$ - \overline{X} direction of the surface Brillouin zones due to the mirror symmetry $\{m_{[001]} | 00\frac{c}{2}\}$ that is preserved on both surfaces.

Importantly, due to the presence of \mathcal{I} the energy bands have well-defined parity. This allows us to easily infer the value of θ by analyzing the parity-based \mathbb{Z}_4 invariant, as explained in the main text. By our DFT calculations, we find $\mathbb{Z}_4 = 2$ for the A-type state, which corresponds to $\theta = \pi$ and an axion insulator (AXI) phase. As our DFT results show that the band gap never closes when we continuously change the angles ϕ_{rb} and ϕ_{rr} from $|\phi_{rr}| = |\phi_{rb}| = \pi$ to their experimentally determined values in the broken- and 60°-helix states, we conclude that both the broken- and pure 60°-helix states also have $\theta = \pi$ and are therefore AXIs. Note that while \mathcal{I} is absent in the experimentally determined helical structures, the combination $\mathcal{T}C_2 = 2'$ guarantees quantization of θ , as it reverses an odd number of space-time coordinates. Finally, we note that, as discussed in Supplementary Reference [16], A-type order with ordered moments along [100] or [010] is described by MSG Cmcm (No. 63.457), whereas A-type order with moments along [001] is described by MSG $P6_{3'}/m'm'c$ (No. 194.268).

Several magnetic phase transitions occur in EuIn₂As₂ upon cooling, which in Landau theory for second-order phase transitions may be related to transitions from a symmetry group to one of its subgroups. Starting from the high-temperature paramagnetic phase, the compound undergoes a transition to pure 60°-helix order below $T_{\rm N1} = 17.6(2)$ K, followed by a second transition to broken-helix order below $T_{\rm N2} = 16.2(1)$ K. From the point of view of group-subgroup relations, there are three different paths the system could follow between the high-temperature MSG $P6_3/mmc1'$ and the low-temperature MSG $C2'2'2_1$ as shown in Supplementary Figure 18. The left path in Supplementary Figure 18 corresponds to the Eu moments first aligning ferromagnetically along [001], followed by a transition to A-type order, and finally by a third transition to the broken-helix phase. This path is ruled out by our neutron diffraction data, since no out-of-plane component of the ordered magnetic moment is observed (see Supplementary Figure 8) and only two ordering transitions were seen.

The other two paths in Supplementary Figure 18 correspond to transitions from the paramagnetic state to pure 60° -helix order and, finally, to the broken-helix state. Based on our experiments, both of these routes are possible with the only difference between the two cases being the handedness (chirality) of the pure 60° helix phases: the moments rotate

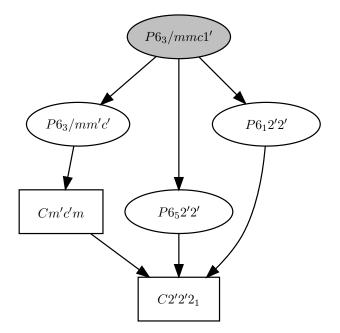

Supplementary Figure 18. Magnetic subgroup tree. Magnetic group–subgroup tree connecting the paramagnetic magnetic space group (MSG) $P6_3/mmc1'$ to MSG $C2'2'2_1$, which corresponds to the broken-helix order. The middle and right paths reach the low-temperature phase via intermediate 60° helical order propagating along **c** with either counterclockwise (right path) or clockwise (center path) chirality. Both of these paths agree with the experimental results. The left path traverses A-type order (Cm'c'm) with moments along [$\bar{1}10$] (or ($1\bar{1}0$]), which is not experimentally realized. This diagram is taken from Supplementary Reference [1].

clockwise around [001] for the center path and counterclockwise around [001] for the right path. It is important to note that the handedness of the helical states cannot be resolved from our data, and it is likely that domains with different handedness coexist in the sample. Also, note that the broken-helix state also exhibits a handedness, yet both right- and lefthanded chiralities are described by MSG $C2'2'_{2_1}$.

Polarizing the Eu moments along a specific direction via applying an external magnetic field offers tuning of the topological properties of the material. As shown in Fig. 4b and Supplementary Figure 11b, at T = 5 K a magnetic field of $\mu_0 H \approx 1$ to 2 T aligns the Eu magnetic moments parallel to the field, which corresponds to a field-polarized state. Below, we study the symmetry and topological consequences of a field-polarized state by considering three orientations for the external field. We first consider a magnetic field along the high-symmetry direction [$\bar{1}10$], which is the direction that the blue Eu ordered magnetic moments lie along. The resulting field-polarized state with all moments aligned along [$\bar{1}10$] is characterized by MSG Cm'cm' (No. 63.464), which is generated by

$$\{\mathbb{1}, \mathcal{I}, \mathcal{T}\{C_{2,[001]} | 00\frac{c}{2}\}, \mathcal{T}C_{2,[110]}\}$$
 (5)

In this phase, there is both $\mathcal{T}C_{2,[110]} \equiv 2'_{[110]}$ and $\mathcal{T}\left\{C_{2,[001]} \middle| 00\frac{c}{2}\right\} \equiv \left\{2'_{[001]} \middle| 00\frac{c}{2}\right\}$. While the former protects a gapless Dirac cone on the (110) surface, the latter is a screw axis that is naturally broken on the (001) surface. Therefore, (110) is the only surface hosting an exotic surface state in this polarized phase. Importantly, because the mirror symmetry $\left\{m_{[\bar{1}10]} \middle| 00\frac{c}{2}\right\}$ is preserved in this surface, the Dirac cone occurs along the $\bar{\Gamma}-\bar{Z}$ direction in the surface Brillouin zone.

Another possibility is to align the Eu moments along [100]. In this case, the MSG is Cmc'm' (No. 63.463), with generators

$$\left\{ \mathbb{1}, \mathcal{I}, C_{2,[100]}, \mathcal{T}\left\{ C_{2,[001]} \middle| 00\frac{c}{2} \right\} \right\}$$
 (6)

The combinations of the generators in Supplementary Equation (6) result in two 2' operations: $\{2'_{[001]} | 00\frac{c}{2}\}$ and $\{2'_{[120]} | 00\frac{c}{2}\}$. As above, the screw operation $\{2'_{[001]} | 00\frac{c}{2}\}$ is naturally broken on the (001) surface. Therefore, here we only have a Dirac surface state on the (010) surface, which is pinned along the $\bar{\Gamma}$ - \bar{Z} direction due to an additional $m_{[100]}$ mirror symmetry.

If we apply a magnetic field perpendicular to the Eu layers so that the moments align parallel to \hat{c} , we obtain a magnetic state belonging to MSG $P6_3/mm'c'$ (No. 194.270). The generators of this group are

$$\{\mathbb{1}, \mathcal{I}, C_{3,[001]}, \{C_{2,[001]} | 00\frac{c}{2}\}, \mathcal{T}C_{2,[100]}\}.$$
 (7)

They give rise to 24 symmetry operations, among which six are combinations of \mathcal{T} and C_2 rotations. These 2' operations can be grouped into two different classes: one class contains the element $2'_{[100]}$ and those related to it by $C_{3,[001]}$. As a consequence, Dirac surface states emerge on the surfaces (210), (120) and (110). The second class contains the element $\left\{2'_{[120]} \middle| 00\frac{c}{2}\right\}$ and those related to it by $C_{3,[001]}$. Note that the direction of these 2' operations are normal to the side faces of the hexagonal crystallographic unit cell, and they protect Dirac surface states on the (100), (010) and (110) surfaces.

	MSG	X_{BS}
Perfect helix	$P6_12'2'$ (No. 178.159)	1
Broken helix	$C2'2'2_1$ (No. 20.33)	1
A-type $\parallel [\bar{1}10]$	Cm'c'm (No. 63.462)	2
Field-pol. $\ [\overline{1}10]$	Cm'cm' (No. 63.464)	(2,2)
Field-pol. $ $ [100] (or [010])	Cmc'm' (No. 63.464)	(2, 2)
Field-pol. [001]	$P6_3/mm'c'$ (No. 194.270)	(3, 6)

Supplementary Table IV. Symmetry-based indicators of band topology. Data taken from Supplementary Reference 17 for all of the magnetic phases described in this section.

Note that the surfaces hosting exotic states are the same as those for pure 60°-helix order. The difference here is that the Dirac cones are no longer completely unpinned, but are constrained to occur along $\bar{\Gamma}-\bar{X}$ because of the additional mirror symmetry $\{m_{[001]} | 00\frac{c}{2}\}$ resulting from the combination of inversion \mathcal{I} and the screw operation $\{C_{2,[001]} | 00\frac{c}{2}\}$.

It becomes evident from the previous analysis that we can use an external magnetic field to either induce or destroy topological states on different surfaces of EuIn₂As₂. For instance, applying a magnetic field along [$\bar{1}10$] inside the pure 60°-helix phase gaps out Dirac cones on (100), (010), (2 $\bar{1}0$) and (1 $\bar{2}0$) surfaces and pins the gapless Dirac cones on (110) and (1 $\bar{1}0$) to the $\bar{\Gamma}$ - \bar{Z} direction in the surface Brillouin zone. If, on the other hand, a field parallel to [001] is applied in the pure 60°-helix phase, the Dirac cones remain gapless on all six surfaces but are now all constrained to lie along the $\bar{\Gamma}$ - \bar{X} direction.

In Supplementary Table IV, we show the symmetry-based indicators X_{BS} of topology for the magnetic helical phases and the field-polarized phases. While symmetry indicators are absent for the MSGs describing the two helical phases, since $X_{BS} = 1$ means that there exist no symmetry indicators, the MSGs of A-type order and the field-polarized phases feature differing symmetry-based indicators.

[2] Qureshi, N. Mag2Pol: A program for the analysis of spherical neutron polarimetry, flipping

Perez-Mato, J. M. et al. Symmetry-based computational tools for magnetic crystallography. *Annual Review of Materials Research* 45, 217-248 (2015).

ratio and integrated intensity data. Journal of Applied Crystallography 52, 175-185 (2019).

- [3] Goforth, A. M., Klavins, P., Fettinger, J. C. & Kauzlarich, S. M. Magnetic properties and negative colossal magnetoresistance of the rare earth zintl phase EuIn₂As₂. *Inorganic Chemistry* 47, 11048-11056 (2008).
- [4] Rosa, P. F. S. et al. Electron spin resonance of the intermetallic antiferromagnet EuIn₂As₂.
 Physical Review B 86, 094408 (2012).
- [5] Busing, W. R. & Levy, H. A. High-speed computation of the absorption correction for singlecrystal diffraction measurements. Acta Crystallographica 10, 180-182 (1957).
- [6] $\tau_2 = (0,0,1)$ is equivalent to $\tau_2 = (0,0,0)$ for $P6_3/mmc$. We use $\tau_2 = (0,0,1)$ to facilitate presentation of the diffraction data.
- [7] Ye, F., Liu, Y., Whitfield, R., Osborn, R. & Rosenkranz, S. Implementation of cross correlation for energy discrimination on the time-of-flight spectrometer CORELLI. *Journal of Applied Crystallography* 51, 315-322 (2018).
- [8] Johnston, D. C. Magnetic structure and magnetization of helical antiferromagnets in high magnetic fields perpendicular to the helix axis at zero temperature. *Physical Review B* 96, 104405 (2017).
- [9] Voyer, C. J. & Ryan, D. H. A complete solution to the Mössbauer problem all in one place. Hyperfine Interact. 170, 91 (2006).
- [10] Bonville, P., Hodges, J., Shirakawa, M., Kasaya, M. & Schmitt, D. Incommensurate modulated magnetic structure in orthorhombic EuPdSb. *The European Physical Journal B-Condensed Matter and Complex Systems* 21, 349-355 (2001).
- [11] Maurya, A., Bonville, P., Thamizhavel, A. & Dhar, S. EuNiGe₃, an anisotropic antiferromagnet. Journal of Physics: Condensed Matter 26, 216001 (2014).
- [12] Ryan, D. H. et al. Modulated ferromagnetic ordering and the magnetocaloric response of Eu₄PdMg. Journal of Applied Physics 117, 17D108 (2015).
- [13] Ryan, D. H. & Cadogan, J. M. ¹⁵¹Eu hyperfine fields, isomer shifts and moments in Eu-based EuT_2X_2 intermetallic compounds. *Hyperfine Interactions* **226**, 243-255 (2014).
- [14] Duttine, M. et al. Modulated magnetic structure in ⁵⁷Fe doped orthorhombic YbMnO₃: A Mössbauer study. AIP Advances 9, 035008 (2019).
- [15] Fang, C. & Fu, L. New classes of three-dimensional topological crystalline insulators: Nonsymmorphic and magnetic. *Physical Review B* 91, 161105 (2015).

- [16] Xu, Y., Song, Z., Wang, Z., Weng, H. & Dai, X. Higher-order topology of the axion insulator EuIn₂As₂. *Physical Review Letters* **122**, 256402 (2019).
- [17] Watanabe, H., Po, H. C. & Vishwanath, A. Structure and topology of band structures in the 1651 magnetic space groups. *Science Advances* 4, (2018).