Enhanced valley polarization in $WS_2/LaMnO_3$ heterostructure

Jianchen Dang, Mingwei Yang, Xin Xie, Zhen Yang, Danjie Dai, and Zhanchun Zuo

Beijing National Laboratory for Condensed Matter Physics,

Institute of Physics, Chinese Academy of Sciences, Beijing 100190, China and

CAS Center for Excellence in Topological Quantum Computation and School of Physical Sciences,

University of Chinese Academy of Sciences, Beijing 100049, China

Can Wang,^{*} Kuijuan Jin,[†] and Xiulai Xu^{\ddagger}

Beijing National Laboratory for Condensed Matter Physics,

Institute of Physics, Chinese Academy of Sciences, Beijing 100190, China

CAS Center for Excellence in Topological Quantum Computation and School of Physical Sciences,

University of Chinese Academy of Sciences, Beijing 100049, China and Songshan Lake Materials Laboratory, Dongguan, Guangdong 523808, China

Monolayer transition metal dichalcogenides have attracted great attentions for potential applications in valleytronics. However, the valley polarization degree is usually not high because of the intervalley scattering. Here, we demonstrate a largely enhanced valley polarization up to 80% in monolayer WS_2 under non-resonant excitation at 4.2 K using $WS_2/LaMnO_3$ thin film heterostructure, which is much higher than that for monolayer WS_2 on SiO_2/Si substrate with a valley polarization of 15%. Furthermore, the greatly enhanced valley polarization can be maintained to a high temperature of about 160 K with a valley polarization of 53%. The temperature dependence of valley polarization is strongly correlated with the thermomagnetic curve of LaMnO₃, indicating an exciton-magnon coupling between WS_2 and $LaMnO_3$. A simple model is introduced to illustrate the underlying mechanisms. The coupling of WS_2 and $LaMnO_3$ is further confirmed with an observation of two interlayer excitons with opposite valley polarizations in the heterostructure, resulting from the spin-orbit coupling induced splitting of the conduction bands in monolayer transition metal dichalcogenides. Our results provide a pathway to control the valleytronic properties of transition metal dichalcogenides by means of ferromagnetic van der Waals engineering, paving a way to practical valleytronic applications.

^{*} canwang@iphy.ac.cn

[†] kjjin@iphy.ac.cn

[‡] xlxu@iphy.ac.cn

I. INTRODUCTION

Monolayer transition metal dichalcogenides (TMD) with a broken inversion symmetry possess two degenerate inequivalent valleys[1, 2], offering a new degree of freedom of electrons, in addition to the charge and spin[3–7]. By selectively pumping one of the two valleys with circularly polarized light, an imbalanced carrier population between +K and -K valleys can be created, leading to the valley-polarized light emission[4, 5]. Realizing a high valley polarization is an essential step and has been pursued many years for developing valleytronic devices[8–11]. So far, the valley polarization of monolayer TMD reported is not high[12, 13], which is mainly attributed to intervalley scattering process from the selectively pumped valley to the opposite one[14, 15]. Several works have been reported to increase the valley polarization by using various methods, such as high magnetic field, low temperature, resonant excitation, optical or electrical doping and so on[4, 5, 16–21]. Most methods require harsh conditions and the improvements are still not good enough. Therefore, more compact and practical approaches are desired for further applications of valleytronics.

Recently, increasing attentions have been gathered in hybrid heterostructure engineering based on TMD[22–25]. By constructing van der Waals heterostructures, the properties of TMD are modulated by the additional layer or substrate, particularly the valley properties[26–31]. The interactions between TMD and the adjacent materials, such as charge transfer, proximity effect, etc.,[25, 28, 29] provide an alternative approach to controlling the valley polarizations in TMD. For example, in a monolayer TMD and graphene heterostructure, a high degree of valley polarization has been achieved due to the fast charge and energy transfer processes from monoalyer TMD to graphene[24, 25]. In addition, magnetic proximity effect from ferromagnetic substrates can yield an interfacial magnetic exchange field in monolayer TMD, offering an effective way for valley control[32–34]. A giant and tunable valley splitting has been predicted theoretically and realized experimentally in monolayer TMD and ferromagnetic substrate heterostructures[28, 29, 35]. More interestingly, a signature of interlayer exciton-magnon coupling has been observed in antiferromagnetsemiconductor van der Waals hetstructures[36]. However, there are few studies reporting on improving valley polarization in monolayer TMD and ferromagnet heterostructures[30], although valley splitting control in this hybrids systems have been intensively discussed[28, 29, 33].

In this work, we demonstrate a greatly enhanced valley polarization up to 80% in monolayer WS₂ at 4.2 K by constructing WS₂/LaMnO₃ heterostructure. The LaMnO₃ (LMO) ferromagnetic film was grown by using a pulsed laser deposition (PLD) system. The polarization-resolved photoluminescence (PL) measurements were carried out for monolayer WS₂ both on LMO and SiO₂

for comparison. The enhanced valley polarization can be maintained to a high temperature, with a high value of 53% at 160 K. More importantly, the temperature dependent valley polarization strongly follows the thermomagnetic curve of LMO, indicating an exciton-magnon coupling. Furthermore, two emerging interlayer excitons with opposite valley polarizations are observed in such hybrid heterostructure, providing a new platform for investigating valley dynamics in monolayer TMD. Our work provides a compact and effective approach to enhancing the valley polarization and to controlling the valley properties.

II. RESULTS AND DISCUSSION

Figure 1a,b show schematic diagrams of the monolayer WS_2 on SiO_2/Si and the ferromagnetic LMO substrates, respectively. After the deposition with PLD, the structure and the thickness of the LMO film are characterized with X-ray diffraction, as shown in Supplementary Information (SI) Fig. S1. The monolayer WS_2 are mechanically exfoliated from bulk and then transferred onto the LMO and SiO_2/Si substrates. The optical microscopy images of the samples are shown in Figs. 1c and d, and the monolayer thickness is also confirmed with the atomic force microscope measurement, as shown in SI Fig. S2. Figure 1e shows the normalized micro-PL spectra of monolayer WS_2 on SiO_2 and LMO substrates under a non-resonant excitation with a 532-nm continuous laser at 4.2 K. Three distinct peaks at 2.089 eV, 2.045 eV and 2.013 eV arise in WS_2/SiO_2 , which can be assigned to exciton (X_0) , trion (X^-) and localized state (L)[37-39], respectively. In contrast, there is only one peak at 2.052 eV presented in WS_2/LMO . This peak originates from X_0 emission, which is confirmed by the reflectance contrast spectra, as shown in SI Fig. S3. Compared to WS_2 on SiO_2 substrate, the peak of WS_2 on LMO exhibits redshift and broadening in both PL and reflectance spectra. The observed red shift is expected from dielectric screening of LMO substrate, which screens the electric field between electrons and holes and leads to a strong reduction in the bandgap but a modest reduction of the exciton binding energy of the monolayer $WS_2[40, 41]$. The absence of X^- and localized state, as well as a 5-fold suppression of the X_0 intensity comparing with WS_2/SiO_2 are observed as shown in Fig. 1e and f, which result from the additional recombination processes such as charge transfer [25, 39, 42]. The linewidth on WS_2/LMO with 39.1 meV is much broader than 17.8 meV on WS_2/SiO_2 , which may result from the enhanced thermal phonon scattering, impurity and charge transfer [43]. Among these factors, the charge transfer may be the dominant factor for the broadening, as discussed in more detail in SI.

In addition, in the lower-energy range compared to intrinsic excitons, two peaks arised at 1.689

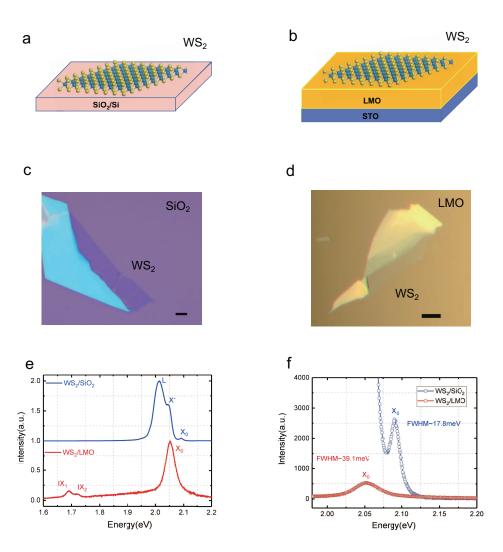


FIG. 1. Characterization of the monolayer WS₂ on the different substrates. (a,b) Schematic diagrams of the monolayer WS₂ on (a) the SiO₂/Si substrate and (b) the ferromagnetic LMO substrate. Optical microscopy images of the samples with a scale bar of 5 μ m on (c) SiO₂/Si substrate and (d) LMO substrate. (e) Normalized PL spectra of monolayer WS₂ measured at 4.2 K with an excitation wavelength of 532 nm. Exciton (X₀), trion (X⁻) and localized state(L) are observed on the SiO₂/Si substrate (blue line); Exciton (X₀) and two interlayer excitons (IX₁ and IX₂) arise on the LMO substrate (red line). The spectra are shifted for clarity. (f) Comparison of PL peaks of X₀ for different substrates. The linewidths (full width at half maximum, FWHM) of the X₀ are 17.8 meV for WS₂/SiO₂ (blue line) and 39.1 meV for WS₂/LMO (red line), respectively.

eV and 1.718 eV on WS_2/LMO heterostructure. The energy separation between the two peaks is about 29 meV, which is in agreement with the conduction band splitting of WS_2 caused by spin-orbit coupling[1, 44]. So the two peaks may originate from the interlayer excitons and the

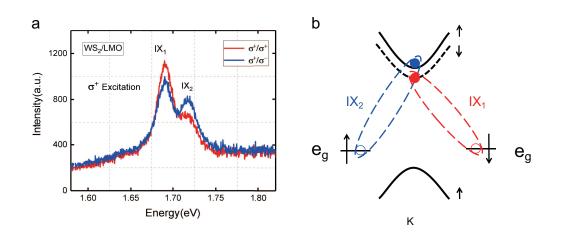


FIG. 2. PL spectra of double interlayer excitons and Schematic diagram of recombination mechanisms. (a) Polarization-resolved PL spectra of double interlayer excitons in monolayer WS_2/LMO heterostructure. (b) Schematic of energy level of the double interlayer excitons in monolayer WS_2/LMO . A small spin-orbit splitting arises in the conduction band of monolayer WS_2 , and e_g represents the energy level of LMO. The arrow directions indicate the spin-up and spin-down states. The red solid (empty) circle represents the electron (hole) of interlayer exciton IX_1 and the blue represents the interlayer exciton IX_2 . The dashed ellipses indicate the formation of the double interlayer excitons with opposite valley polarizations.

splitting can be attributed to the interlayer fine structures [45–47]. To further verify the origin of the double peaks in WS₂/LMO heterostructure, the polarization-resolved PL signals are non-resonantly excited by a σ^+ polarized laser at 532 nm (2.33 eV) and analyzed with configurations of co-polarized σ^+ and cross-polarized σ^- luminescence. Figure 2a shows the polarization-resolved PL spectra. The double peaks exhibit opposite valley polarizations, which is very similar to the behaviour of double interlayer excitons in TMD heterobilayers [45, 46, 48–51]. In WS₂/LMO heterostructure, the splitting of conduction band leads to the formation of the two interlayer excitons with opposite valley polarizations, as indicated by the blue and red dashed ellipses in Fig. 2b. Moreover, photoluminescence excitation measurement is performed to support the assignment of PL emission to the interlayer exciton, as shown in SI Fig. S4. Therefore, the double peaks with opposite valley polarizations originate from the interlayer exciton between LMO and monolayer WS₂. Besides, the double interlayer excitons in such TMD/ferromagnet heterostructures also verifies the existence of charge transfer from WS₂ to LMO substrate, which might enhance the valley polarization of exciton in monolayer WS₂[24, 25].

Figure 3 shows the polarization-resolved PL spectra in monolayer WS_2/SiO_2 and WS_2/LMO . Based on the optical selection rules in monolayer TMD, the valley polarization degree P_c can be

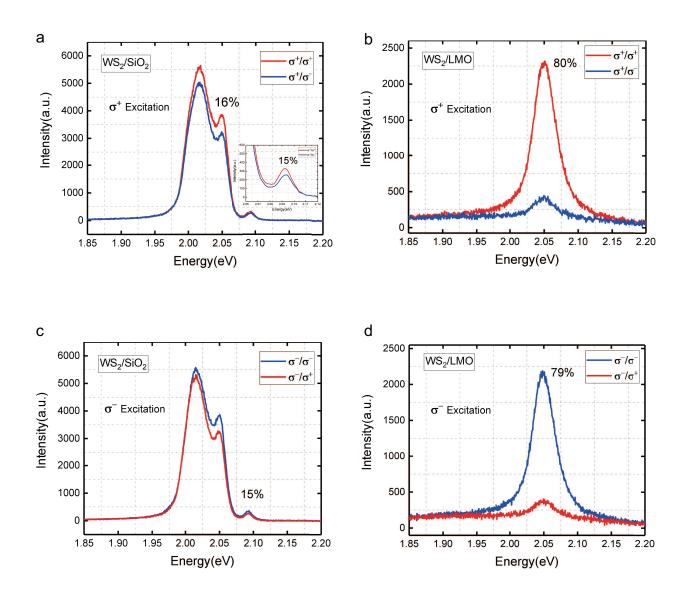


FIG. 3. Polarization-resolved PL spectra of the monolayer WS₂ on the different substrates. Polarizationresolved PL spectra of monolayer WS₂ on (a) SiO₂/Si and (b) LMO substrates under σ^+ excitation. The polarization degree of X₀ for SiO₂/Si and LMO substrates are 15% and 80%, respectively. The polarization degree of X⁻ for SiO₂/Si is about 16%. Polarization-resolved PL spectra of monolayer WS₂ on (c) SiO₂/Si and (d) LMO substrates under σ^- excitation. The polarization degrees of X₀ for SiO₂/Si and LMO substrates are 15% and 79%, respectively. Red lines represent the σ^+ light emission and blue lines represent the σ^- light emission.

depicted by [4, 20],

$$P_c = \frac{I(\sigma^+) - I(\sigma^-)}{I(\sigma^+) + I(\sigma^-)} \tag{1}$$

where I (σ^+) and I (σ^-) are the σ^+ and σ^- PL intensities. Here, we only focus on X₀ emission.

The valley polarization degree of X_0 in WS₂/SiO₂ is about 15%, which is extracted from the polarization-resolved PL spectra in Fig. 3a with σ^+ excitation according to Eq. 1, similar to previous results[12, 52]. In contrast, the valley polarization in WS₂/LMO is largely enhanced, with a high value up to about 80%, as shown in Fig. 3b. The similar results are obtained under σ^- excitation, shown in Figs. 3c and d. Note that no distinguishable valley splitting is observed in our WS₂/LMO heterostructure.

To clarify the underlying mechanisms for the greatly enhanced valley polarization, temperature dependent valley polarization degrees were measured for both two samples, as shown in Fig. 4a. Both samples exhibit a monotonic increase of the valley polarization with decreasing temperature. For WS₂/LMO, the valley polarization increases drastically from 200 K to 100 K, and then maintains a high value of about 80%. In contrast, for WS₂/SiO₂, the valley polarization possesses low values, which is only 15% at 4.2 K. To determine the origin of the enhanced valley polarization, the temperature-dependent magnetization of LMO substrate was also measured using a vibrating sample magnetometer of physical properties measurement system, as indicated by the blue line in Fig. 4a. Remarkably, the temperature dependent valley polarization of WS₂/LMO is strongly correlated with the thermomagnetic curve of LMO when superimposed on each other. It indicates that the enhanced valley polarization in monolayer WS₂ most likely originates from the magnetic proximity effect from LMO substrate. At higher temperatures there is a slight deviation between the two curves.

Next, we will discuss the reasons for the enhanced valley polarization in WS₂/LMO heterostructure. Two mechanisms might be involved. When a σ^+ (σ^-) laser selectively excites the exciton transitions in the +K (-K) valley, the corresponding recombination emission should carry single handedness[4, 5], namely the unity valley polarization, because of the optical selection rule. However, as schematically shown in Fig. 4b, when the +K valley is selectively pumped with σ^+ excitation, the generated PL light emissions contain not only σ^+ component from exciton transitions in +K valley but also σ^- component due to intervalley scattering of excitons from +K to -K valley, generating a non-unity valley polarization[14, 15]. When the monolayer WS₂ is transferred on the LMO substrate, the charge transfer occurs, which is demonstrated by the PL intensity suppression, linewidth broadening (Fig. 1f) and the formation of interlayer excitons (Fig. 1e and Fig. 2). The charge transfer process provides new decay channels for WS₂ excitons. After the generation process of excitons in +K valley pumped by σ^+ light, the exciton populations will now rapidly recombine and transfer the photoexcited energy to LMO substrate non-radiatively or be used to form interlayer excitons instead of being scattered to -K valley. Therefore, the proportion

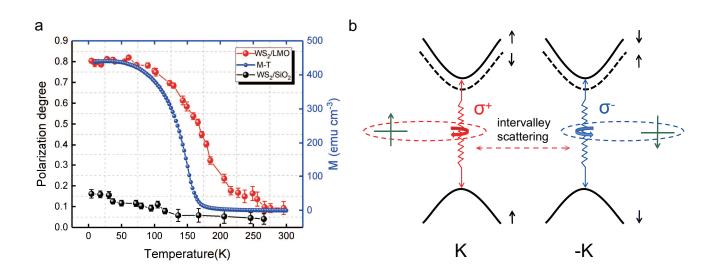


FIG. 4. Temperature dependent valley polarization of the monolayer WS_2 on the different substrates and a simplified model for the enhanced valley polarization. (a) Temperature dependent valley polarization of X_0 in WS_2 on LMO substrate (red solid circles), SiO_2/Si substrate (black solid circles) and temperature dependent magnetization (M-T) of LMO (blue solid circles) superimposed on each other. The left and right vertical axises represent the polarization degree and magnetization (M), respectively. (b) Schematic diagram of transitions in monolayer WS_2/LMO , containing the optical transitions obeying optical selection rules, intervalley scattering process and the coupling between exciton and magnon. The dashed lines in the conduction band depict spin-forbidden state for the ground state of monolayer WS_2 . The black arrows represent the spin states in monolayer WS_2 and the green represent the magnon (quanta of spin wave) in LMO ferromagnetic substrate. The dashed ellipses denote the coupling between exciton and magnon.

of intervalley scattering is reduced, leading to the increase of valley polarization.

On the other hand, interlayer exciton-magnon coupling might be another dominant factor responsible for the enhanced valley polarization. Magnon is defined as quanta of spin wave[53]. The exciton-magnon coupling is essentially one of the mechanisms of the magnetic proximity effect, which can occur at the heterointerface formed by an atomically-thin semiconductor and magnetic materials. For our samples, the temperature dependent valley polarization strongly follows the thermomagnetic curve of LMO. We suggest that it is caused by exciton-magnon coupling, which is related to the locking of valley excitons with different polarizations and magnons with different spin orientations. More specifically, the K valley excitons are locked with the spin-up magnons, and the -K valley excitons are locked with the spin-down magnons, as shown in Fig. 4b. Below the Curie temperature, the spin orientation is fixed and such locking between exciton and magnon will strongly suppress intervalley scattering of exciton, leading to an enhanced valley polarization. Note that the exciton-magnon coupling in LMO substrate might be related to the band structure and lattice match to the WS_2 , the specific termination surface, crystal orientation and the stoichiometry of LMO film as discussed in SI. With the increase of temperature, the spin tends to be chaotic and the coupling of exciton-magnon will weaken. Therefore, the suppression of intervalley scattering due to the exciton-magnon coupling becomes weak, leading to a decrease of the valley polarization. As the temperature further increases, the former mechanism (charge transfer process) dominates, causing a slight deviation between the temperature dependent valley polarization and the thermomagnetic curve of LMO, as shown in Fig. 4a. Similar results are observed in three other monolayer WS₂ samples with random angles on the same LMO, as shown in SI Fig. S5, suggesting the exciton-magnon coupling is not dependent on the rotation alignment between monolayer WS_2 and LMO due to the in-plane magnetic isotropy of LMO (001) film (shown in SI Fig. S6). For the four samples, there exists a little discrepancy in the valley polarization degree, which may result from the quality of the samples or the different heterointerface that occur during the transfer process, thereby affecting the valley polarization degree. Additionally, we also measured the valley polarization degree of monolayer MoS_2 , WSe_2 and $MoSe_2$ on LMO and SiO_2 substrates. Neither obvious increase of valley polarization degree nor interlayer excitons was observed in the three materials with LMO substrate, where the reason need to be investigated further.

In the following, we compare our work with the previous results on valley polarizations in monolayer WS_2 and other TMD materials. Up to now, many methods such as strong magnetic field, resonant excitation, heterostructure engineering and defect and strain engineering have been applied to improve valley polarization, as shown in Fig. 5. With applied out-of-plane magnetic field, the polarization degree exhibits monotonically increasing and has been optimized to 30%under 15 T at 4 K in monolayer $WS_2[21]$. However, this method requires high magnetic field, and the enhancement of polarization degree is not very high. Under resonant excitation, the valley polarization of 40% in monolayer WS₂ at 10 K has been reported, while the valley polarization under off-resonant excitation is only about 16%[12]. Additionally, a near-unity valley polarization has been reported in monolayer MoS_2 with resonant excitation [4, 54]. But with different substrates such as hBN or SiO_2 with different thicknesses, the valley polarizations in monolayer MoS_2 show big difference which may result from the different influences of substrate materials on the optical properties of monolayer $MoS_2[3-5, 54]$. Despite of the difference in different materials, the resonant excitation requires sophisticated measurement setup to filter out the pumping light. By all means, the reported valley polarizations under non-resonant excitation are very low. By heterostructure engineering, the polarization degree of 41% has been reported in WS₂/Graphene (WS₂/Gr) at 4 K,

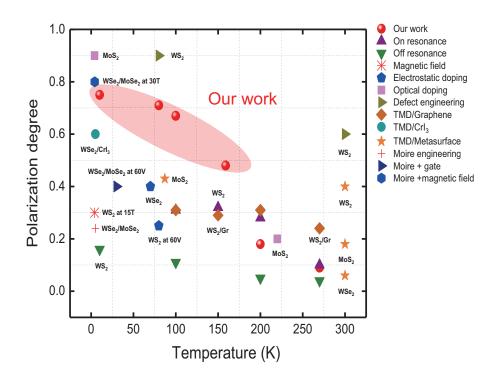


FIG. 5. Comparison on the valley polarization of TMD materials. solid circles denote the average valley polarization degree of the four samples from our work and the rest of dots with other colors and shapes represent the previous reported values, in which different methods have been explored, such as on/off resonance excitation from Ref.[12], applied magnetic field from Ref.[21], electrostatic doping from Refs.[20] and [58], optical doping from Refs.[4] and [55], defect engineering from Ref.[57], heterostructures (TMD/Gr from Ref.[25], TMD/CrI₃ from Ref.[30], and moire patterns from Ref.[48]), moire + gate from Ref.[61], moire + magnetic field from Ref.[54], and TMD/metasurface from Refs.[62], [64] and [65].

and 25% has been reported at room temperature with resonant excitation in WS₂/Gr[25]. However, these heterostuctures are difficult to fabricate and the optimization is not obviously improved. Defect and strain engineering can also tune valley polarization, and 90% valley polarization at 80 K has been reported in CVD-grown monolayer WS₂ single crystals riched in defects[55]. However, the defect and strain engineering are difficult to precisely control and may degrade the valley polarization[56]. In addition, electrostatic doping, moire patterns, and plasmonic architectures based on TMD have also be used to produce and tune valley polarization, as shown in Fig. 5[3– 5, 20, 30, 46, 48, 57–65]. But all these methods either require harsh conditions, such as high magnetic field, sophisticated measurement setup and difficult fabrication processes, or exhibit low-efficiency optimization of valley polarization. Thus an efficient and convenient method is more important and practical on manipulating the valley polarization. By utilizing monolayer WS_2/LMO heterostructure here, the valley polarization exhibits a high value up to 80% under non-resonant excitation at 4.2 K, and keeps at a high value of 53% even when the temperature is increased to about 160 K. Therefore, we believe our method provides an efficient and convenient way to manipulate the valley polarization, making the valleytronic devices more practical.

III. CONCLUSION

In summary, we experimentally demonstrated the greatly enhanced valley polarization up to 80% in monolayer WS₂/LMO heterostructure at 4.2 K with off-resonance excitation by constructing WS₂/LMO heterostructure. And the enhanced valley polarization can be maintained to a higher temperature, up to 160 K (about 53%). Furthermore, the temperature-dependent valley polarization highly follows the thermomagnetic curve of LMO, indicating the exciton-magnon coupling. A simplified model is introduced here, in which two mechanisms are proposed to be responsible for the enhanced valley polarization. In addition, double interlayer excitons with opposite valley polarizations in such hybrid heterostructure were observed, providing a new platform for valleytronics and spintronics. Further studies will be required to fully understand the underlying mechanisms. Nevertheless, we have shown a strong evidence experimentally that utilizing WS₂/LMO heterostructure engineering, the valley polarization can be greatly improved with non-resonant excitation, which provides an effective and convenient approach for valley control, promoting the development of the applications of monolayer TMD valleytronics. Moreover, it can be predicted that the intriguing phenomena will motivate more studies on the heterostructure formed by the ferromagnetic materials and monolayer TMD.

ACKNOWLEDGMENTS

This work was supported by the National Key Research and Development Program of China (Grant No. 2021YFA1400700), the National Natural Science Foundation of China (Grants Nos. 62025507, 11934019, 11721404, 11874419, 61775232, 11874412, and 12174437), the Key R&D Program of Guangdong Province (Grant No. 2018B030329001), the Strategic Priority Research Program (Grant No. XDB28000000) of the Chinese Academy of Sciences.

^[1] D. Xiao, G.-B. Liu, W. Feng, X. Xu, W. Yao, Phys. Rev. Lett. 2012, 108, 19 196802.

- [2] Z. Y. Zhu, Y. C. Cheng, U. Schwingenschloegl, *Phys. Rev. B* 2011, 84, 15 153402.
- [3] T. Cao, G. Wang, W. Han, H. Ye, C. Zhu, J. Shi, Q. Niu, P. Tan, E. Wang, B. Liu, J. Feng, Nat. Commun. 2012, 3 887.
- [4] K. F. Mak, K. He, J. Shan, T. F. Heinz, Nat. Nanotechnol. 2012, 7, 8 494.
- [5] H. Zeng, J. Dai, W. Yao, D. Xiao, X. Cui, Nat. Nanotechnol. 2012, 7, 8 490.
- [6] J. Dang, S. Sun, X. Xie, Y. Yu, K. Peng, C. Qian, S. Wu, F. Song, J. Yang, S. Xiao, L. Yang, Y. Wang, M. A. Rafiq, C. Wang, X. Xu, *npj 2D Mater. Appl.* 2020, 4 2.
- S. Sun, Y. Yu, J. Dang, K. Peng, X. Xie, F. Song, C. Qian, S. Wu, H. Ali, J. Tang, J. Yang, S. Xiao,
 S. Tian, M. Wang, X. Shan, M. A. Rafiq, C. Wang, X. Xu, *Appl. Phys. Lett.* **2019**, *114* 113104.
- [8] D. Xiao, W. Yao, Q. Niu, Phys. Rev. Lett. 2007, 99, 23 236809.
- [9] W. Yao, D. Xiao, Q. Niu, Phys. Rev. B 2008, 77, 23 235406.
- [10] M. Eginligil, B. Cao, Z. Wang, X. Shen, C. Cong, J. Shang, C. Soci, T. Yu, Nat. Commun. 2015, 6 7636.
- W. Yang, J. Shang, J. Wang, X. Shen, B. Cao, N. Peimyoo, C. Zou, Y. Chen, Y. Wang, C. Cong, W. Huang, T. Yu, *Nano Lett.* 2016, 16, 3 1560.
- [12] B. Zhu, H. Zeng, J. Dai, Z. Gong, X. Cui, Proc. Natl. Acad. Sci. U. S. A. 2014, 111, 32 11606.
- [13] J. Huang, T. B. Hoang, M. H. Mikkelsen, Sci. Rep. 2016, 6 22414.
- [14] T. Yan, X. Qiao, P. Tan, X. Zhang, Sci. Rep. 2015, 5 15625.
- [15] G. Kioseoglou, A. T. Hanbicki, M. Currie, A. L. Friedman, D. Gunlycke, B. T. Jonker, Appl. Phys. Lett. 2012, 101, 22 221907.
- [16] A. Srivastava, M. Sidler, A. V. Allain, D. S. Lembke, A. Kis, A. Imamoglu, Nat. Phys. 2015, 11, 2 141.
- [17] Y. Li, J. Ludwig, T. Low, A. Chernikov, X. Cui, G. Arefe, Y. D. Kim, A. M. van der Zande, A. Rigosi,
 H. M. Hill, S. H. Kim, J. Hone, Z. Li, D. Smirnov, T. F. Heinz, *Phys. Rev. Lett.* 2014, *113*, 26 266804.
- [18] A. T. Hanbicki, K. M. McCreary, G. Kioseoglou, M. Currie, C. S. Hellberg, A. L. Friedman, B. T. Jonker, AIP Adv. 2016, 6, 5 055804.
- [19] A. Arora, R. Schmidt, R. Schneider, M. R. Molas, I. Breslavetz, M. Potemski, R. Bratschitsch, Nano Lett. 2016, 16, 6 3624.
- [20] S. Feng, C. Cong, S. Konabe, D. Zhang, J. Shang, Y. Chen, C. Zou, B. Cao, L. Wu, N. Peimyoo,
 B. Zhang, T. Yu, Small 2019, 15, 12 1805503.
- [21] G. Plechinger, P. Nagler, A. Arora, A. G. del Aguila, M. V. Ballottin, T. Frank, P. Steinleitner, M. Gmitra, J. Fabian, P. C. M. Christianen, R. Bratschitsch, C. Schueller, T. Korn, *Nano Lett.* 2016, 16, 12 7899.
- [22] L. Du, Q. Zhang, B. Gong, M. Liao, J. Zhu, H. Yu, R. He, K. Liu, R. Yang, D. Shi, L. Gu, F. Yan, G. Zhang, Q. Zhang, *Phys. Rev. B* **2018**, *97*, 11 115445.
- [23] F. Cadiz, E. Courtade, C. Robert, G. Wang, Y. Shen, H. Cai, T. Taniguchi, K. Watanabe, H. Carrere, D. Lagarde, M. Manca, T. Amand, P. Renucci, S. Tongay, X. Marie, B. Urbaszek, *Phys. Rev. X* 2017,

7, 2 021026.

- [24] E. Lorchat, S. Azzini, T. Chervy, T. Taniguchi, K. Watanabe, T. W. Ebbesen, C. Genet, S. Berciaud, ACS Photonics 2018, 5, 12 5047.
- [25] I. Paradisanos, K. M. McCreary, D. Adinehloo, L. Mouchliadis, J. T. Robinson, H.-J. Chuang, A. T. Hanbicki, V. Perebeinos, B. T. Jonker, E. Stratakis, G. Kioseoglou, *Appl. Phys. Lett.* 2020, 116, 20 203102.
- [26] C. Tang, Z. Zhang, S. Lai, Q. Tan, W.-b. Gao, Adv. Mater. 2020, 32, 16 1908498.
- [27] P. Wei, S. Lee, F. Lemaitre, L. Pinel, D. Cutaia, W. Cha, F. Katmis, Y. Zhu, D. Heiman, J. Hone, J. S. Moodera, C.-T. Chen, *Nat. Mater.* **2016**, *15*, 7 711.
- [28] C. Zhao, T. Norden, P. Zhang, P. Zhao, Y. Cheng, F. Sun, J. P. Parry, P. Taheri, J. Wang, Y. Yang, T. Scrace, K. Kang, S. Yang, G.-x. Miao, R. Sabirianov, G. Kioseoglou, W. Huang, A. Petrou, H. Zeng, *Nat. Nanotechnol.* 2017, 12, 8 757.
- [29] T. Norden, C. Zhao, P. Zhang, R. Sabirianov, A. Petrou, H. Zeng, Nat. Commun. 2019, 10 4163.
- [30] D. Zhong, K. L. Seyler, X. Linpeng, R. Cheng, N. Sivadas, B. Huang, E. Schmidgall, T. Taniguchi,
 K. Watanabe, M. A. McGuire, W. Yao, D. Xiao, K.-M. C. Fu, X. Xu, Sci. Adv. 2017, 3, 5 e1603113.
- [31] K. L. Seyler, D. Zhong, B. Huang, X. Linpeng, N. P. Wilson, T. Taniguchi, K. Watanabe, W. Yao, D. Xiao, M. A. McGuire, K.-M. C. Fu, X. Xu, *Nano Lett.* **2018**, *18*, 6 3823.
- [32] K. Tivakornsasithorn, T. Yoo, H. Lee, S. Lee, S. Choi, S.-K. Bac, K. J. Lee, S. Lee, X. Liu, M. Dobrowolska, J. K. Furdyna, *Sci. Rep.* 2018, 8 10570.
- [33] X. Liang, L. Deng, F. Huang, T. Tang, C. Wang, Y. Zhu, J. Qin, Y. Zhang, B. Peng, L. Bi, Nanoscale 2017, 9, 27 9502.
- [34] T. P. Lyons, D. Gillard, A. Molina-Sanchez, A. Misra, F. Withers, P. S. Keatley, A. Kozikov, T. Taniguchi, K. Watanabe, K. S. Novoselov, J. Fernandez-Rossier, A. I. Tartakovskii, *Nat. Commun.* 2020, 11, 1 6021.
- [35] Q. Zhang, S. A. Yang, W. Mi, Y. Cheng, U. Schwingenschloegl, Adv. Mater. 2016, 28, 5 959.
- [36] M. Onga, Y. Sugita, T. Ideue, Y. Nakagawa, R. Suzuki, Y. Motome, Y. Iwasa, Nano Lett. 2020, 20, 6 4625.
- [37] J. Shang, X. Shen, C. Cong, N. Peimyoo, B. Cao, M. Eginligil, T. Yu, ACS Nano 2015, 9, 1 647.
- [38] G. Plechinger, P. Nagler, J. Kraus, N. Paradiso, C. Strunk, C. Schueller, T. Korn, *Phys. Status Solidi RRL* 2015, 9, 8 457.
- [39] C. Cong, J. Shang, Y. Wang, T. Yu, Adv. Opt. Mater. 2018, 6, 1 1700767.
- [40] A. Chernikov, T. C. Berkelbach, H. M. Hill, A. Rigosi, Y. Li, O. B. Aslan, D. R. Reichman, M. S. Hybertsen, T. F. Heinz, *Phys. Rev. Lett.* **2014**, *113*, 7 076802.
- [41] A. Raja, A. Chaves, J. Yu, G. Arefe, H. M. Hill, A. F. Rigosi, T. C. Berkelbach, P. Nagler, C. Schueller, T. Korn, C. Nuckolls, J. Hone, L. E. Brus, T. F. Heinz, D. R. Reichman, A. Chernikov, *Nat. Commun.* 2017, 8 15251.

- [42] C. E. Giusca, I. Rungger, V. Panchal, C. Melios, Z. Lin, Y.-C. Lin, E. Kahn, A. L. Elias, J. A. Robinson, M. Terrones, O. Kazakova, ACS Nano 2016, 10, 8 7840.
- [43] A. F. Rigos, H. M. Hill, Y. Li, A. Chernikov, T. F. Heinz, Nano Lett. 2015, 15, 8 5033.
- [44] G.-B. Liu, W.-Y. Shan, Y. Yao, W. Yao, D. Xiao, *Phys. Rev. B* 2013, 88, 8 085433.
- [45] T. Wang, S. Miao, Z. Li, Y. Meng, Z. Lu, Z. Lian, M. Blei, T. Taniguchi, K. Watanabe, S. Tongay, D. Smirnov, S.-F. Shi, *Nano Lett.* **2020**, 20, 1 694.
- [46] A. T. Hanbicki, H.-J. Chuang, M. R. Rosenberger, C. S. Hellberg, S. V. Sivaram, K. M. McCreary, I. I. Mazin, B. T. Jonker, ACS Nano 2018, 12, 5 4719.
- [47] H. Yu, G.-B. Liu, W. Yao, 2D Mater. 2018, 5, 3 035021.
- [48] A. Ciarrocchi, D. Unuchek, A. Avsar, K. Watanabe, T. Taniguchi, A. Kis, Nat. Photonics 2019, 13, 2 131.
- [49] L. Zhang, R. Gogna, G. W. Burg, J. Horng, E. Paik, Y.-H. Chou, K. Kim, E. Tutuc, H. Deng, *Phys. Rev. B* 2019, 100, 4 041402.
- [50] B. Miller, A. Steinhoff, B. Pano, J. Klein, F. Jahnke, A. Holleitner, U. Wurstbauer, Nano Lett. 2017, 17, 9 5229.
- [51] E. Calman, V, L. H. Fowler-Gerace, D. J. Choksy, L. Butov, V, D. E. Nikonov, I. A. Young, S. Hu, A. Mishchenko, A. K. Geim, *Nano Lett.* **2020**, *20*, 3 1869.
- [52] A. T. Hanbicki, G. Kioseoglou, M. Currie, C. S. Hellberg, K. M. McCreary, A. L. Friedman, B. T. Jonker, Sci. Rep. 2016, 6 18885.
- [53] C. Gong, X. Zhang, *Science* **2019**, *363*, 6428.
- [54] G. Sallen, L. Bouet, X. Marie, G. Wang, C. R. Zhu, W. P. Han, Y. Lu, P. H. Tan, T. Amand, B. L. Liu, B. Urbaszek, *Phys. Rev. B* 2012, *86*, 8 081301.
- [55] W.-H. Lin, W.-S. Tseng, C. M. Went, M. L. Teague, G. R. Rossman, H. A. Atwater, N.-C. Yeh, ACS Nano 2020, 14, 2 1350.
- [56] K. M. McCreary, M. Currie, A. T. Hanbicki, H.-J. Chuang, B. T. Jonker, ACS Nano 2017, 11, 8 7988.
- [57] K. Shinokita, X. Wang, Y. Miyauchi, K. Watanabe, T. Taniguchi, K. Matsuda, Adv. Funct. Mater. 2019, 29, 26 1900260.
- [58] C. Jiang, W. Xu, A. Rasmita, Z. Huang, K. Li, Q. Xiong, W.-b. Gao, Nat. Commun. 2018, 9 753.
- [59] Z. Li, C. Liu, X. Rong, Y. Luo, H. Cheng, L. Zheng, F. Lin, B. Shen, Y. Gong, S. Zhang, Z. Fang, Adv. Mater. 2018, 30, 34 1801908.
- [60] P. Rivera, K. L. Seyler, H. Yu, J. R. Schaibley, J. Yan, D. G. Mandrus, W. Yao, X. Xu, Science 2016, 351, 6274 688.
- [61] Z. Wu, J. Li, X. Zhang, J. M. Redwing, Y. Zheng, Adv. Mater. 2019, 31, 49 1904132.
- [62] K. Tran, G. Moody, F. Wu, X. Lu, J. Choi, K. Kim, A. Rai, D. A. Sanchez, J. Quan, A. Singh, J. Embley, A. Zepeda, M. Campbell, T. Autry, T. Taniguchi, K. Watanabe, N. Lu, S. K. Banerjee, K. L. Silverman, S. Kim, E. Tutuc, L. Yang, A. H. MacDonald, X. Li, *Nature* 2019, 567, 7746 71.

- [63] P. Nagler, M. V. Ballottin, A. A. Mitioglu, F. Mooshammer, N. Paradiso, C. Strunk, R. Huber, A. Chernikov, P. C. M. Christianen, C. Schuller, T. Korn, *Nat. Commun.* **2017**, 8 1551.
- [64] L. Sun, C.-Y. Wang, A. Krasnok, J. Choi, J. Shi, J. S. Gomez-Diaz, A. Zepeda, S. Gwo, C.-K. Shih, A. Alu, X. Li, *Nat. Photonics* **2019**, *13*, 3 180.
- [65] T. Chervy, S. Azzini, E. Lorchat, S. Wang, Y. Gorodetski, J. A. Hutchison, S. Berciaud, T. W. Ebbesen, C. Genet, ACS Photonics 2018, 5, 4 1281.