Spin-density-wave transition in double-layer nickelate La₃Ni₂O₇

Zhao Dan^{1‡}, Yanbing Zhou^{1‡}, Mengwu Huo^{2‡}, Yu Wang¹, Linpeng Nie¹, Meng Wang^{2,*}, Tao Wu^{1,3,4,5,*} and Xianhui Chen^{1,3,4,5,*}

1. Hefei National Research Center for Physical Sciences at the Microscale, University of Science and Technology of China, Hefei, Anhui 230026, China

2. Center for Neutron Science and Technology, Guangdong Provincial Key Laboratory of Magnetoelectric Physics and Devices, School of Physics, Sun Yat-Sen University, Guangzhou, China

3. CAS Key Laboratory of Strongly Coupled Quantum Matter Physics, Department of Physics, University of Science and Technology of China, Hefei, Anhui 230026, China

4. Collaborative Innovation Center of Advanced Microstructures, Nanjing University, Nanjing 210093, China

5. Hefei National Laboratory, University of Science and Technology of China, Hefei 230088, China

‡These authors contributed equally to this work

*Correspondence to: wangmeng5@mail.sysu.edu.cn, wutao@ustc.edu.cn, chenxh@ustc.edu.cn

Abstract:

Recently, a signature of high-temperature superconductivity above the liquid nitrogen temperature (77 K) was reported for La₃Ni₂O₇ under pressure. This finding immediately stimulates intense interest in the possible high- T_c superconducting mechanism in double-layer nickelates. Interestingly, the pressure-dependent phase diagram inferred from transport measurements indicates that superconductivity under high pressure emerges from the suppression of a density-wave-like transition at ambient pressure, which is similar to high-temperature superconductors. Therefore, clarifying the exact nature of the density-wave-like transition is important for determining the mechanism of superconductivity in double-layer nickelates. Here, nuclear magnetic resonance (NMR) spectroscopy of ¹³⁹La nuclei was performed to study the density-wave-like transition in a single crystal of La₃Ni₂O₇. The temperature-dependent ¹³⁹La NMR spectrum and nuclear spin-lattice relaxation rate ($1/T_i$) provide unambiguous evidence for a spin-density-wave (SDW) transition with a transition temperature T_{SDW} of ~ 150 K. Furthermore, the anisotropic splitting of the NMR spectrum suggests a possible double spin stripe with magnetic moments along the *c* axis. In addition, the present NMR

measurements also revealed spatial inhomogeneity of magnetism due to inner apical oxygen vacancies. All these results will be helpful for building a connection between superconductivity and magnetic interactions in double-layer nickelates.

The origin of high-temperature superconductivity remains a conundrum in condensed matter physics [1, 2]. The discovery of superconductivity up to 15 K in infinite-layer nickelate NdNiO₂ thin films has drawn extensive interest for the pursuit of high-T_c superconducting mechanisms in nickelate materials [3]. Recent resonant inelastic X-ray scattering (RIXS) experiments revealed significant antiferromagnetic interactions in superconducting Nd_{1-x}Sr_xNiO₂ thin films [4]. Moreover, muon spin rotation/relaxation (μ SR) experiments also reveal intrinsic magnetism in a series of superconducting infinite-layer nickelate thin films [5]. All these results are similar to those of cuprate superconductors [6-13], suggesting the key role of antiferromagnetic interactions in superconducting infinite-layer nickelates [14]. Very recently, a signature of high-temperature superconductivity at approximately 80 K was observed for the double-layer nickelate La₃Ni₂O_{7- δ} under high pressure [15]. Although characterization of the superconducting state is still limited due to the high-pressure environment, these findings have stimulated wide discussions on the electronic correlations and possible high-T_c mechanism [16-31].

Experimentally, a density-wave-like transition at approximately 150 K was previously observed in La₃Ni₂O_{7- δ} at ambient pressure [32-37]. Due to the absence of detectable magnetic and charge ordering below 150 K in earlier experiments, the exact nature of this density-wave-like transition has not been determined [38]. In contrast, a similar density-wave-like transition has also been observed in the trilayer nickelate La₄Ni₃O₁₀, in which an intertwined density wave with both charge and spin order is experimentally revealed below the transition temperature (~ 136 K) [39]. Considering the similar band structures observed by angle-resolved photoemission spectroscopy (ARPES) [40, 25], understanding the different experimental results of density-wave-like transitions between La₃Ni₂O_{7- δ} and La₄Ni₃O₁₀ is not straightforward. More importantly, recent high-pressure transport measurements indicate that the density-wave-like transition in La₃Ni₂O_{7- δ} is continuously suppressed as the pressure increases and finally disappears when high-*T_c* superconductivity occurs [15, 41, 42]. These results suggest an important correlation between superconductivity and density-wave-like order. Therefore, identifying the exact nature of the density-wave-like transition is a prerequisite for understanding the high- T_c superconductivity in La₃Ni₂O_{7- δ} under high pressure. Nuclear magnetic resonance (NMR) is a sensitive local probe for detecting both spin and charge orders in high- T_c superconductors [43, 44]. Here, we performed a systematic NMR measurement on ¹³⁹La nuclei in a single crystal of La₃Ni₂O_{7- δ}. Our results provide clear evidence for a spin-density-wave (SDW) transition at ~ 150 K.

Site-selective ¹³⁹La NMR

As shown in Fig. 1a, the structure of La₃Ni₂O_{7-δ} at ambient pressure crystallizes into an orthorhombic phase (space group Amam) with a corner-connected NiO₆ octahedral layer separated by a La–O fluorite-type layer stacking along the c axis [36]. The La sites inside the corner-connected NiO₆ octahedral layer are defined as La(1), and the other La sites in the La-O fluorite-type layer are defined as La(2). In previous ¹³⁹La NMR measurements of polycrystalline samples, the quadrupole frequencies (v_Q) of these two La sites were found to be quite different, with 2.2 MHz for La(1) and 5.6 MHz for La(2) [37, 45, 46]. This is useful for obtaining site-selective ¹³⁹La NMR spectra of single crystals. As shown in the inset of Fig. 1d, one piece of a La₃Ni₂O_{7- δ} single crystal with a size of ~ 2 mm × 1 mm was selected for ¹³⁹La NMR measurement (see Sec. S1 in the Supplementary Materials for detailed sample information,). The full NMR spectra with magnetic fields (B) perpendicular and parallel to the *ab* plane were measured. The nuclear spin number for ¹³⁹La nuclei is 7/2. In principle, due to nonzero quadrupole interactions, there should be seven NMR transition lines for each La(1) and La(2) site. As shown in Fig. 1(b) and 1(c), only one set of sharp 139 La NMR peaks with $v_0 \sim 2.2$ MHz is well resolved and assigned to La(1) sites. In contrast, the NMR signal from the La(2) site contributes a broad background to the full NMR spectrum, suggesting that the La(2) site is strongly inhomogeneous. This inhomogeneity might be related to the low superconducting volume suggested by very recent *ac* susceptibility measurements on single crystals from the same batch [47]. However, the origin of such an inhomogeneity requires additional microscopic characterization of the structure and ingredients. In the following, we will only focus on the sharp NMR signals for the La(1) sites. In addition, we also found that there is an unexpected splitting on each La(1) NMR transition line above the density-wave-like transition temperature (~ 150 K), which is well resolved with B//c, as shown in Fig. 1d. The twinning due to the orthorhombic structure, which should not split with B//c, can be excluded from our angle-dependent NMR spectra (see Sec. S2 in the Supplementary Materials).

Therefore, the splitting of the NMR spectrum with B//c suggested a more complicated structural modulation beyond the perfect structure with the space group Amam [48]. In fact, the nearest neighboring sites to La(1) are the four inner apical oxygens. Therefore, the NMR spectrum of La(1) should be very sensitive to the presence of inner apical oxygen vacancies, which provides a natural explanation for the NMR splitting of La(1). As shown in Fig. 1e, La(1)a and La(1)b are attributed to La(1) without inner apical oxygen vacancy and with a single inner apical oxygen vacancy at the nearest neighboring sites, respectively. By considering a random distribution of inner apical oxygen vacancies, the ratio of oxygen vacancies at the inner apical oxygen site is estimated to be approximately 20% (see Sec. S3 in the Supplementary Materials). This result is also consistent with recent results from multislice electron ptychography [49], suggesting the key role of inner apical oxygen vacancies in the superconducting properties of La₃Ni₂O₇₋₈ single crystals.

Evidence for an SDW transition at 150 K

Next, we systematically studied the temperature-dependent evolution of NMR central transition lines, which are sensitive to magnetic transitions. As shown in Fig. 2, the central NMR lines exhibit a remarkable change below 150 K with magnetic fields applied along different crystalline axes. When an external magnetic field B is applied along the (001) direction, the central NMR lines exhibit significant broadening below 150 K, as shown in Fig. 2(a). However, when an external magnetic field B is applied along the (110) direction, the central NMR lines clearly split below 150 K, as shown in Fig. 2(b), which is a hallmark of magnetic transition. By further checking the field-dependent broadening and splitting (see Sec. S4 in the Supplementary Materials), we conclude that an SDW transition occurs below 150 K. The temperature-dependent broadening and splitting are shown in Fig. 2(c) and (d), which exhibit a second-order SDW transition with a transition temperature T_{SDW} of ~ 150 K. This result is also consistent with recent µSR and RIXS experiments [50, 51]. In addition, it should be noted that the SDW transition produces quite different hyperfine fields at La(1)a and La(1)b (Fig. 2(c)), which implies the possible role of inner apical oxygen in magnetism. Based on a recent density functional theory calculation [52], the magnitude of magnetic moments is strongly affected by the absence of inner apical oxygens in La₃Ni₂O₇. This finding is in line with our present observation (see the next section for more discussion). Furthermore, the temperature-dependent nuclear spin-lattice

relaxation rate $(1/T_1)$ also confirms the SDW transition at ~150 K. As shown in Fig. 3(a), the temperature-dependent $1/T_1T$ of La(1)a and La(1)b exhibit similar SDW transitions at ~ 150 K, which is quite consistent with previous NMR investigations of polycrystalline samples [37,46]. Interestingly, the present NMR measurements of single crystals reveal additional site-dependent behavior for $1/T_1T$ above 150 K. For La(1)a, the critical behavior of spin fluctuations due to the SDW transition can extend much above T_{SDW} up to 200 K, which has not been observed in previous La(1) NMR results on polycrystalline samples [37,46]. However, for La(1)b, a similar critical behavior appears only within a narrow temperature range of a few Kelvins around the T_{SDW} . Moreover, the overall temperaturedependent behaviors for La(1)a and La(1)b are also different above 150 K. All these results suggest that the nature of fluctuating magnetic moments above the SDW transition is also strongly affected by the inner apical oxygens, which might also be pivotal for superconductivity under pressure. More theoretical investigations are needed to clarify the site-dependent spin susceptibility of La₃Ni₂O₇, which is beyond the scope of the present study. Below 150 K, the $1/T_1T$ of both La(1)a and La(1)b are strongly suppressed as the temperature decreases to 50 K. This behavior is well understood by the formation of the SDW order. Moreover, the stretched exponent, which is extracted from the fitting of T_l decay and depicts the inhomogeneity of T_l , shows a continuous decrease below 150 K (Fig. 3(b)). This indicates inhomogeneous spin dynamics in the SDW state. This might be related to the abovementioned inner apical oxygen vacancies. Below 50 K, additional spin dynamics appear in the temperature-dependent $1/T_1T$ and lead to field-dependent peak behavior at lower temperatures (Fig. 3(c)). This field-dependent behavior can be ascribed to the dynamic slowing down of fluctuating magnetic moments, which is usually observed in glassy magnetism [12, 53-55]. Considering the sensitivity of magnetism to inner apical oxygens, whether the observed glassy spin dynamics are intrinsic or extrinsic is still unclear.

Possible magnetic structure

Finally, we discuss the possible magnetic structure based on the present NMR results. In a previous study on the trilayer nickelate La₄Ni₃O₁₀, an intertwined density wave with both spin and charge order was observed at ambient pressure [39]. Considering the similar band structures in both La₃Ni₂O₇ and La₄Ni₃O₁₀ [25, 40], a similar intertwined density wave order might also be shared in

La₃Ni₂O₇. However, the temperature-dependent ¹³⁹La NMR satellites, which are sensitive to charge ordering [55, 56], do not show any signature for charge ordering at approximately 150 K (see Sec. S5 in the Supplementary Materials). Therefore, we believe that if there is any charge order accompanied by an SDW order in La₃Ni₂O₇, the order should be very weak and beyond the sensitivity of the present NMR measurements. Below, we only consider pure SDW models to explain our NMR results. By careful in-plane rotation, two orthorhombic domains were identified by the present NMR measurements (see Sec. S6 in the Supplementary Materials). Furthermore, all these NMR spectra with magnetic fields along different directions (Fig. 2 and Fig. S8) can be used to constrain the possible magnetic structure below 150 K. As shown in Fig. 4(a), by considering an approximate square lattice of Ni, a double spin stripe model with a wavevector $q = (\pi/2, \pi/2)$ is finally proposed to account for the present NMR results, which are quite consistent with recent RIXS and neutron scattering experiments [51, 57]. Here, we consider an antiferromagnetic coupling between the neighboring Ni-O planes in each bilayer, and the spin polarization is along the out-of-plane direction. According to this model, the hyperfine fields transferred at La sites from the nearest neighboring Ni sites can explain the ¹³⁹La NMR spectra shown in Fig. 2 and Fig. S8. More discussion on the possible magnetic structure can be found in the supplementary materials (see Sec. S7 in the Supplementary Materials). It should be emphasized that the transferred hyperfine fields at La sites are quite different for La(1)a and La(1)b. Based on the results of hyperfine fields, we can estimate the magnetic moments at Ni sites, which are approximately 0.08 Bohr magneton (μ_B) for Ni with inner apical oxygen and 0.018 μ_B for Ni without inner apical oxygen (see Sec. S8 in the Supplementary Materials). This result suggests that the inner apical oxygen is helpful for stabilizing static magnetic moments at Ni sites in the SDW state.

In summary, the present NMR study successfully identified an SDW transition at ~150 K and strongly constrained the possible magnetic structure of the bilayer nickelate $La_3Ni_2O_7$ at ambient pressure. A double spin stripe model with magnetic moments along the *c*-axis is proposed to account for the observed ¹³⁹La NMR spectra. These results strongly suggest a possible twist of the SDW and superconductivity under pressure, but further experiments are needed to clarify this picture. In addition, the role of the inner apical oxygen in magnetic properties was also revealed by site-selective ¹³⁹La NMR, which might also be important for superconductivity under pressure.

Acknowledgments

We thank the valuable discussion with Kun Jiang. This work is supported by the National Key R&D Program of the MOST of China (Grant Nos. 2022YFA1602601, 2023YFA1406500), the National Natural Science Foundation of China (Grants No. 11888101, 12034004, 12161160316, 12325403, 12174454), the Strategic Priority Research Program of Chinese Academy of Sciences (Grant No. XDB25000000), the Chinese Academy of Sciences under contract No. JZHKYPT-2021-08, the CAS Project for Young Scientists in Basic Research (Grant No.YBR-048), the Innovation Program for Quantum Science and Technology (Grant No. 2021ZD0302800),the Guangdong Basic and Applied Basic Research Funds (Grant No. 2021B1515120015), the Guangzhou Basic and Applied Basic Research Funds (Grant No. 2022B1212010008).

Reference

[1] Patrick A. Lee, Naoto Nagaosa, and Xiao-Gang Wen, Doping a Mott insulator: Physics of high-temperature superconductivity, Rev. Mod. Phys. **78**, 17 (2006)

[2] Keimer, B., Kivelson, S. A., Norman, M. R., Uchida, S., and Zaanen, J. From quantum matter to high-temperature superconductivity in copper oxides. Nature **518**, 179 (2015).

[3] Danfeng Li, Kyuho Lee, Bai Yang Wang, Motoki Osada, Samuel Crossley, Hye Ryoung Lee, Yi Cui, Yasuyuki Hikita, and Harold Y. Hwang, Superconductivity in an infinite-layer nickelate, Nature **572**, 624 (2019).

[4] H. Lu, M. Rossi, A. Nag, M. Osada, D.F.Li, K. Lee, B. Y. Wang, M. Garcia-Fernandez, S. Agrestini, Z. X. Shen, E. M. Been, B. Moritz, T. P. Devereaux, J. Zaanen, H. Y. Hwang, Ke-Jin Zhou, and W.S.Lee, Magnetic excitations in infinite-layer nickelates, Science **373**, 213 (2021).

[5] Jennifer Fowlie, Marios Hadjimichael, Maria M. Martins, Danfeng Li, Motoki Osada, Bai Yang Wang, Kyuho Lee, Yonghun Lee, Zaher Salman, Thomas Prokscha, Jean-Marc Triscone, Harold Y. Hwang, and Andreas Suter, Intrinsic magnetism in superconducting infinite-layer nickelates, Nat. Phys. **18**, 1043 (2022).

[6] Julien, M.-H. Magnetic order and superconductivity in La_{2-x}Sr_xCuO₄: a review. Phys. B **329**, 693 (2003).

[7] Ch. Niedermayer, C. Bernhard, T. Blasius, A. Golnik, A. Moodenbaugh, and J. I. Budnick, Common phase diagram for antiferromagnetism in $La_{2-x}Sr_xCuO_4$ and $Y_{1-x}Ca_xBa_2Cu_3O_6$ as seen by muon spin rotation, Phys. Rev. Lett. **80**, 3843 (1998).

[8] M.-H. Julien, F. Borsa, P. Carretta, M. Horvatić, C. Berthier, and C. T. Lin, Charge segregation, cluster spin glass, and superconductivity in La_{1.94}Sr_{0.06}CuO₄, Phys. Rev. Lett. **83**, 604 (1999).

[9] C. Panagopoulos, J. L. Tallon, B. D. Rainford, J. R. Cooper, C.A Scott, and T. Xiang, Low-frequency spins and the ground state in high-T_c cuprates. Solid State Communications, **126**, 47 (2003). [10] D Haug, V Hinkov, Y Sidis, P Bourges, N B Christensen, A Ivanov, T Keller, C T Lin, and B Keimer. Neutron scattering study of the magnetic phase diagram of underdoped $YBa_2Cu_3O_{6+x}$. New J. Phys, **12**, 105006 (2010).

[11] Risdiana, T. Adachi, N. Oki, S. Yairi, Y. Tanabe, K. Omori, Y. Koike, T. Suzuki, I. Watanabe, A. Koda, and W. Higemoto, Cu spin dynamics in the overdoped regime of La_{2-x}Sr_xCu_{1-y}Zn_yO₄ probed by muon spin rotation. Phys. Rev. B. **77**, 054516 (2008).

[12] T. Wu, H. Mayaffre, S. Krämer, M. Horvatić, C. Berthier, C. T. Lin, D. Haug, T. Loew, V. Hinkov,

B. Keimer, and M.-H. Julien, Magnetic-field-enhanced spin freezing on the verge of charge ordering in YBa₂Cu₃O_{6.45}, Phys. Rev. B **88**, 014511 (2013).

[13] Mehdi Frachet, Igor Vinograd, Rui Zhou, Siham Benhabib, Shangfei Wu, Hadrien Mayaffre, Steffen Krämer, Sanath K. Ramakrishna, Arneil P. Reyes, Jérôme Debray, Tohru Kurosawa, Naoki Momono, Migaku Oda, Seiki Komiya, Shimpei Ono, Masafumi Horio, Johan Chang, Cyril Proust, David LeBoeuf, and Marc-Henri Julien, Hidden magnetism at the pseudogap critical point of a cuprate superconductor, Nature Phys. **16**, 1064 (2020)

[14] D. Zhao, Y. B. Zhou, Y. Fu, L. Wang, X. F. Zhou, H. Cheng, J. Li, D. W. Song, S. J. Li, B. L. Kang, L. X. Zheng, L. P. Nie, Z. M. Wu, M. Shan, F. H. Yu, J. J. Ying, S. M. Wang, J. W. Mei, T. Wu, and X. H. Chen, Intrinsic Spin Susceptibility and Pseudogaplike Behavior in Infinite-Layer LaNiO₂, Phys. Rev. Lett., **126**, 197001 (2021).

[15] Hualei Sun, Mengwu Huo, Xunwu Hu, Jingyuan Li, Zengjia Liu, Yifeng Han, Lingyun Tang, Zhongquan Mao, Pengtao Yang, Bosen Wang, Jinguang Cheng, Dao-Xin Yao, Guang-Ming Zhang, and Meng Wang, Signatures of superconductivity near 80 K in a nickelate under high pressure, Nature **621**, 493 (2023).

[16] Y. Gu, C. Le, Z. Yang, X. Wu, and J. Hu, Effective model and pairing tendency in bilayer Nibased superconductor La3Ni2O7 (2023), arXiv:2306.07275.

[17] H. Sakakibara, N. Kitamine, M. Ochi, and K. Kuroki, Possible high-Tc superconductivity in La3Ni2O7 under high pressure through manifestation of a nearly-half-filled bilayer Hubbard model (2023), arXiv:2306.06039.

[18] Yi-feng Yang, Guang-Ming Zhang, and Fu-Chun Zhang, Interlayer valence bonds and twocomponent theory for high-Tc superconductivity of La₃Ni₂O₇ under pressure, Phys. Rev. B **108**, L201108 (2023)

[19] Qiong Qin and Yi-feng Yang, High-Tc superconductivity by mobilizing local spin singlets and possible route to higher Tc in pressurized La₃Ni₂O₇, Phys. Rev. B **108**, L140504 (2023).

[20] Yang Shen, Mingpu Qin, and Guang-Ming Zhang, Effective Bi-Layer Model Hamiltonian and Density-Matrix Renormalization Group Study for the High-Tc Superconductivity in La₃Ni₂O₇ under High Pressure, Chin. Phys. Lett. **40** 127401 (2023).

[21] Qing-Geng Yang, Da Wang, and Qiang-Hua Wang, Possible s[±]-wave superconductivity in La₃Ni₂O₇, Phys. Rev. B **108**, L140505 (2023).

[22] Xing-Zhou Qu, Dai-Wei Qu, Jialin Chen, Congjun Wu, Fan Yang, Wei Li, and Gang Su, Bilayer $t-J-J_{\perp}$ Model and Magnetically Mediated Pairing in the Pressurized Nickelate La₃Ni₂O₇, Phys. Rev. Lett. **132**, 036502 (2024).

[23] Yang Zhang, Ling-Fang Lin, Adriana Moreo, and Elbio Dagotto, Electronic structure, dimer physics, orbital-selective behavior, and magnetic tendencies in the bilayer nickelate superconductor La₃Ni₂O₇ under pressure, Phys. Rev. B **108**, L180510 (2023).

[24] Yu-Bo Liu, Jia-Wei Mei, Fei Ye, Wei-Qiang Chen, and Fan Yang, s^{\pm}-Wave Pairing and the Destructive Role of Apical-Oxygen Deficiencies in La₃Ni₂O₇ under Pressure, Phys. Rev. Lett. **131**, 236002 (2023).

[25] Jiangang Yang, Hualei Sun, Xunwu Hu, Yuyang Xie, Taimin Miao, Hailan Luo, Hao Chen, Bo Liang, Wenpei Zhu, Gexing Qu, Cui-Qun Chen, Mengwu Huo, Yaobo Huang, Shenjin Zhang, Fengfeng Zhang, Feng Yang, Zhimin Wang, Qinjun Peng, Hanqing Mao, Guodong Liu, Zuyan Xu, Tian Qian, Dao-Xin Yao, Meng Wang, Lin Zhao, X. J. Zhou, Orbital-Dependent Electron Correlation in Double-Layer Nickelate La₃Ni₂O₇, arXiv:2309.01148 (2023).

[26] Chen Lu, Zhiming Pan, Fan Yang, and Congjun Wu, Interplay of two eg orbitals in

superconducting La₃Ni₂O₇ under pressure, arXiv:2310.02915 (2023).

[27] Zhihui Luo, Xunwu Hu, Meng Wang, Wéi Wú, and Dao-Xin Yao, D.-X. Bilayer two-orbital model of La₃Ni₂O₇ under pressure. Phys. Rev. Lett. 131, 126001 (2023).

[28] Yi-Heng Tian, Yin Chen, Jia-Ming Wang, Rong-Qiang He, and Zhong-Yi Lu, Correlation Effects and Concomitant Two-Orbital s^{\pm} -Wave Superconductivity in La₃Ni₂O₇ under High Pressure. arXiv:2308.09698 (2023).

[29] Zhe Liu, Mengwu Huo, Jie Li, Qing Li, Yuecong Liu, Yaomin Dai, Xiaoxiang Zhou, Jiahao Hao, Yi Lu, Meng Wang, and Hai-Hu Wen, Electronic correlations and spectral weight redistribution in the bilayer nickelate La₃Ni₂O₇, arXiv:2307.02950 (2023).

[30] Viktor Christiansson, Francesco Petocchi, and Philipp Werner. Correlated electronic structure of La₃Ni₂O₇ under pressure. Phys. Rev. Lett. **131**, 206501 (2023).

[31] Jialin Chen, Fan Yang, and Wei Li, Orbital-selective superconductivity in the pressurized bilayer nickelate La₃Ni₂O₇: An infinite projected entangled-pair state study, arXiv:2311.05491 (2023).

[32] K. Sreedhar, M. McElfresh, D. Perry, D. Kim, P. Metcalf, and J. Honig, Low-Temperature Electronic Properties of the $La_{n+1}Ni_nO_{3n+1}$ (n = 2, 3, and ∞) System: Evidence for a Crossover from Fluctuating-Valence to Fermi-Liquid-like Behavior, J. Solid State Chem. **110**, 208 (1994).

[33] Z. Zhang, M. Greenblatt, and J. Goodenough, Synthesis, Structure, and Properties of the Layered Perovskite La₃Ni₂O_{7-δ}, Journal of Solid State Chemistry **108**, 402 (1994).

[34] S. Taniguchi, T. Nishikawa, Y. Yasui, Y. Kobayashi, J. Takeda, S. ichi Shamoto, and M. Sato, Transport, Magnetic and Thermal Properties of La₃Ni₂O_{7-δ}, J. Phys. Soc. Jpn. **64**, 1644 (1995).

[35] Y. Kobayashi, S. Taniguchi, M. Kasai, M. Sato, T. Nishioka, and M. Kontani, Transport and Magnetic Properties of La₃Ni₂O_{7-δ} and La₄Ni₃O_{10-δ}, J. Phys. Soc. Jpn. **65**, 3978 (1996).

[36] Christopher D. Ling, Dimitri N. Argyriou, Guoqing Wu and J. J. Neumeier. Neutron diffraction study of La₃Ni₂O₇: Structural relationships among n=1, 2, and 3 phases La_{n+1}Ni_nO_{3n+1}, J. Solid State Chem. **152**, 517 (2000).

[37] T Fukamachi, Y Kobayashi, T Miyashita, M Sato, ¹³⁹La NMR studies of layered perovskite systems $La_3Ni_2O_{7-\delta}$ and $La_4Ni_3O_{10}$, J. Phys. Chem. Solids **62**, 195 (2001).

[38] Zengjia Liu, Hualei Sun, Mengwu Huo, Xiaoyan Ma, Yi Ji, Enkui Yi, Lisi Li, Hui Liu, Jia Yu, Ziyou Zhang, Zhiqiang Chen, Feixiang Liang, Hongliang Dong, Hanjie Guo, Dingyong Zhong, Bing Shen, Shiliang Li, Meng Wang, Evidence for charge and spin density waves in single crystals of La₃Ni₂O₇ and La₃Ni₂O₆, Sci. China Phys. Mech. Astron. **66**, 217411 (2023).

[39] Junjie Zhang, D. Phelan, A. S. Botana, Yu-Sheng Chen, Hong Zheng, M. Krogstad, Suyin Grass Wang, Yiming Qiu, J. A. Rodriguez-Rivera, R. Osborn, S. Rosenkranz, M. R. Norman, and J. F. Mitchell, Intertwined density waves in a metallic nickelate, Nat. Commun **11**, 6003 (2020).

[40] Haoxiang Li, Xiaoqing Zhou, Thomas Nummy, Junjie Zhang, Victor Pardo, Warren E. Pickett, J.
F. Mitchell, and D. S. Dessau, Fermiology and electron dynamics of trilayer nickelate La₄Ni₃O₁₀, Nat.
Commun 8, 704 (2017).

[41] Yanan Zhang, Dajun Su, Yanen Huang, Hualei Sun, Mengwu Huo, Zhaoyang Shan, Kaixin Ye, Zihan Yang, Rui Li, Michael Smidman, Meng Wang, Lin Jiao, and Huiqiu Yuan, High-temperature superconductivity with zero-resistance and strange metal behavior in La₃Ni₂O₇, arXiv:2307.14819 (2023).

[42] Gang Wang, Ningning Wang, Jun Hou, Liang Ma, Lifen Shi, Zhian Ren, Yadong Gu, Xiaoling Shen, Hanming Ma, Pengtao Yang, Ziyi Liu, Haizhong Guo, Jianping Sun, Guangming Zhang, Jiaqiang Yan, Bosen Wang, Yoshiya Uwatoko, and Jinguang Cheng, Pressure-induced superconductivity in polycrystalline La₃Ni₂O₇, arXiv:2309.17378 (2023).

[43] Kentaro Kitagawa, Naoyuki Katayama, Kenya Ohgushi, Makoto Yoshida, and Masashi Takigawa,

Commensurate itinerant antiferromagnetism in BaFe₂As₂: ⁷⁵As-NMR studies on a self-flux grown single crystal, J. Phys. Soc. Jpn. **77**,114709 (2008)

[44] T. Wu, H. Mayaffre, S. Krämer, M. Horvatić, C. Berthier, W. N. Hardy, R. Liang, D. A. Bonn, and M.-H. Julien, Incipient charge order observed by NMR in the normal state of YBa₂Cu₃O_y, Nature **477**, 191 (2011).

[45] Toshihiko Fukamachi, Keisuke Oda, Yoshiaki Kobayashi, Takeshi Miyashita, and Masatoshi Sato, Studies on Successive Electronic State Changes in Systems with NiO₂ Planes –¹³⁹La-NMR/NQR, J. Phys. Soc. Jpn., **70**, 2757 (2001).

[46] Masataka Kakoi, Takashi Oi, Yujiro Ohshita, Mitsuharu Yashima, Kazuhiko Kuroki, Yoshinobu Adachi, Naoyuki Hatada, Tetsuya Uda, Hidekazu Mukuda, Multiband Metallic Ground State in Multilayered Nickelates La₃Ni₂O₇ and La₄Ni₃O₁₀ Revealed by ¹³⁹La-NMR at Ambient Pressure, arXiv:2312.11844 (2023).

[47] Yazhou Zhou, Jing Guo, Shu Cai, Hualei Sun, Pengyu Wang, Jinyu Zhao, Jinyu Han, Xintian Chen, Qi Wu, Yang Ding, Meng Wang, Tao Xiang, Ho-kwang Mao, Liling Sun, Evidence of filamentary superconductivity in pressurized La₃Ni₂O₇ single crystals, arXiv:2311.12361 (2023).

[48] E. A. Kiseleva, P. Gaczynskib, G. Eckoldc, A. Feldhoffd, K.-D. Beckerb, V. A. Cherepanova, Investigations into the structure of $La_3Ni_{2-x}Fe_xO_{7\pm\delta}$, Chimica Techno Acta 6, 51 (2019).

[49] Zehao Dong, Mengwu Huo, Jie Li, Jingyuan Li, Pengcheng Li, Hualei Sun, Yi Lu, Meng Wang, Yayu Wang, Zhen Chen, Visualization of Oxygen Vacancies and Self-doped Ligand Holes in La₃Ni₂O_{7-δ}, arXiv:2312.15727 (2023).

[50] Kaiwen Chen, Xiangqi Liu, Jiachen Jiao, Myyuan Zou, Yixuan Luo, Qiong Wu, Ningyuan Zhang, Yanfeng Guo, Lei Shu, Evidence of spin density waves in La₃Ni₂O_{7-δ}, arXiv:2311.15717 (2023).

[51] Xiaoyang Chen, Jaewon Choi, Zhicheng Jiang, Jiong Mei, Kun Jiang, Jie Li, Stefano Agrestini, Mirian Garcia-Fernandez, Xing Huang, Hualei Sun, Dawei Shen, Meng Wang, Jiangping Hu, Yi Lu, Ke-Jin Zhou, Donglai Feng, Electronic and magnetic excitations in La₃Ni₂O₇, arXiv:2401.12657 (2023).

[52] Yuxin Wang, Kun Jiang, Ziqiang Wang, Fu-Chun Zhang, Jiangping Hu, Electronic structure and superconductivity in bilayer La₃Ni₂O₇, arXiv:2401.15097 (2023).

[53] N. J. Curro, P. C. Hammel, B. J. Suh, M. Hücker, B. Büchner, U. Ammerahl, and A. Revcolevschi, Inhomogeneous Low Frequency Spin Dynamics in La_{1.65}Eu_{0.2}Sr_{0.15}CuO₄, Phys. Rev. Lett. **85**, 642 (2000).

[54] M.-H. Julien, A. Campana, A. Rigamonti, P. Carretta, F. Borsa, P. Kuhns, A. P. Reyes, W. G. Moulton, M. Horvatic', C. Berthier, A. Vietkin, and A. Revcolevschi, Glassy spin freezing and NMR wipeout effect in the high-Tc superconductor La_{1.90}Sr_{0.10}CuO₄: Critical discussion of the role of stripes, Phys. Rev. B **63**, 144508 (2001).

[55] A. Arsenault, S. K. Takahashi, T. Imai, W. He, Y. S. Lee, and M. Fujita, ¹³⁹La NMR investigation of the charge and spin order in a La_{1.885}Sr_{0.115}CuO₄ single crystal, Phys. Rev. B **97**, 064511 (2018).

[56] T. Imai and Y. S. Lee, ¹³⁹La and ⁶³Cu NMR investigation of charge order in La₂CuO_{4+y} (T_c =42 K), Phys. Rev. B **97**, 104506 (2018)

[57] Tao Xie, Mengwu Huo, Xiaosheng Ni, Feiran Shen, Xing Huang, Hualei Sun, Helen C. Walker, Devashibhai Adroja, Dehong Yu, Bing Shen, Lunhua He, Kun Cao, and Meng Wang, Neutron Scattering Studies on the High-T_c Superconductor La₃Ni₂O_{7– δ} at Ambient Pressure, arXiv:2401.12635 (2024).

Figures

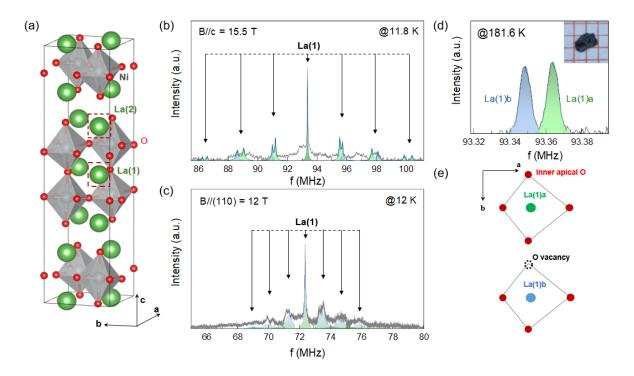


FIG. 1 (a) Sketch of the crystal structure of La₃Ni₂O₇. (b) and (c) Full NMR spectra of ¹³⁹La nuclei with spin number I = 7/2 for external fields $B \parallel c$ and $B \parallel (110)$; (d) The central line of ¹³⁹La above the SDW transition temperature. The inset shows the single crystal of La₃Ni₂O₇ used for the present NMR study; (e) Illustration of La(1)a without an inner apical oxygen vacancy and La(1)b with a single inner apical oxygen vacancy.

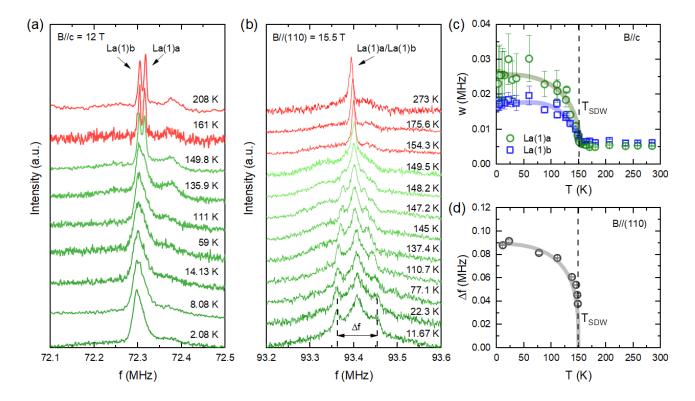


FIG. 2 Temperature dependence of the ¹³⁹La central transition lines for the (a) $B \parallel c$ axis and (b) $B \parallel$ (110) direction. (c) Temperature-dependent linewidth for the La(1)a and La(1)b sites. (d) Temperature-dependent magnetic splitting (Δf) of the La(1)b site for $B \parallel$ (110). The dash lines in (c) and (d) represent the SDW transition temperature at ~ 150 K.

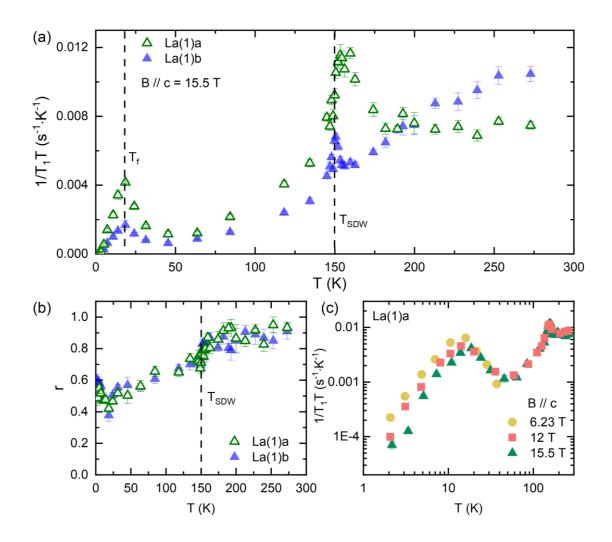


FIG. 3 (a) Temperature dependences of $1/T_1T$ for both the La(1)a and La(1)b sites for *the B* || *c* axis. The value of T_1 is extracted by fitting with the following formula $m(t) = m_0 + m_1 \left[\frac{1}{84}e^{-\left(\frac{t}{T_1}\right)^r} + \frac{3}{44}e^{-\left(\frac{6t}{T_1}\right)^r} + \frac{75}{364}e^{-\left(\frac{15t}{T_1}\right)^r} + \frac{1225}{1716}e^{-\left(\frac{28t}{T_1}\right)^r}\right]$, where *r* is the stretch exponent. (b) The temperature-dependent stretch exponent *r* of ¹³⁹La. (c) Field and temperature dependence of $1/T_1T$ for La(1)(a).

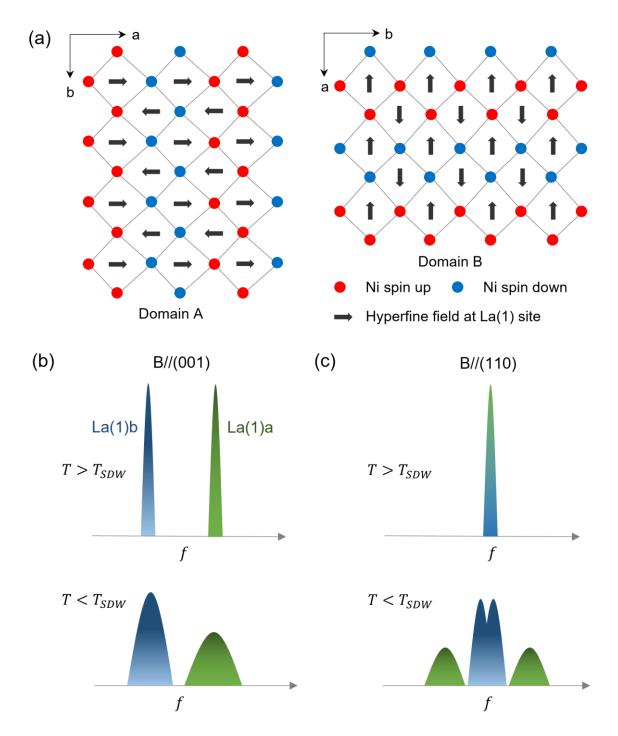


FIG. 4 (a) Illustration of the double spin stripe model, as well as the transferred hyperfine fields at the La(1) sites. (b-c) The evolution of the NMR spectra before and after the SDW transition. When the external field (*B*) is parallel to the *c*-axis, the hyperfine field h_f at the La(1) sites is perpendicular to the external field h_0 . The effective external field at the La(1) sites is expressed as $h_{eff} = \sqrt{h_f^2 + h_0^2}$, where h_0 is the applied external field and h_f is the transferred hyperfine field. Only spectral line broadening can be observed in this case. In contrast, when $B \parallel (110)$, the effective external field at the La(1) sites is expressed as $h_{eff} = h_0 \pm h_f$. A clear spectral splitting can be observed in this case.