

Superfluid transition temperature of bond bipolarons with Coulomb interaction

Chao Zhang^{1,*}

¹*Department of Physics, Anhui Normal University, Wuhu, Anhui 241000, China*

Utilizing an exactly sign-problem-free quantum Monte Carlo method, we explore the influence of long-range Coulomb interaction on the superfluid transition temperature of bipolarons in a two dimensional square lattice. The model studied here is the bond Su-Schrieffer-Heeger model with phonon-modulated electron hopping. Previously, in the absence of long-range Coulomb interaction, this model demonstrated the emergence of small-size, light-mass bipolarons that undergo a superfluid transition at high values of the transition temperature T_c [Physical Review X 13, 011010, (2023)]. Our findings indicate that with the long-range Coulomb interaction, T_c remains relatively high, even in the deep adiabatic regime where the phonon frequency $\omega/t = 0.5$ and the Coulomb interaction $V = U/10$. This result suggests a relatively high superfluid transition temperature for bond bipolarons with long range Coulomb interaction in the low-density regime, which could provide a new insights for the future experiments on dilute superconductors.

I. INTRODUCTION

Electron-phonon coupling is a fundamental interaction within condensed matter physics, giving rise to a variety of intriguing phenomena. This coupling reflects the intricate relationship between the dynamic behavior of electrons, which are the charge carriers, and the vibrational modes of the crystal lattice, known as phonons. The consequences of this interaction lead to significant modifications in electronic properties, such as the formation of polaron and bipolaron [1–7], changes in the effective mass of charge carriers [8–10], and variations in charge carrier mobility and scattering [11]. The polaron, formed through electron-phonon coupling, is particularly significant due to its connection to the mechanism of high-temperature superconductivity in the dilute-density regime. Under low-density conditions, electron-phonon interactions can pair two electrons into a single bipolaron, akin to the formation of a Bose-Einstein condensate-like superconductor. For such a superconducting state to occur, specific conditions must be met, including the presence of a bipolaron with a light effective mass, compact size, and a strong phonon-mediated pairing potential [12, 13].

Depending on whether the phonon vibrations are coupled to the electron density or the hopping motion of the electron, two primary types of electron-phonon coupling exist: the Holstein and bond Su-Schrieffer-Heeger (SSH) models. Extensive prior research has revealed that in the Holstein model, where phonons couple to electrons through density, the effective mass of both polaron and bipolaron grows exponentially at higher electron-phonon coupling strengths [9, 10, 14, 15]. In stark contrast, the scenario changes significantly when considering the bond SSH model, where phonons couple to electrons through the hopping of electrons. Recent investigations into bond SSH polarons have garnered substantial interest, chiefly due to the remarkable characteristic of a rela-

tively light effective mass even in strong coupling regimes, resulting in a lightweight polaron [15–19]. Moreover, the bond SSH type of electron-phonon coupling holds significant promise for bipolaronic superconductivity because, for a single polaron, the effective mass remains light even in the presence of Holstein-type electron-phonon coupling [20] and with dispersive phonons [21], which are more relevant to real materials. The light effective mass of the polaron in the strong electron-phonon coupling regime suggests the possibility of a light effective mass bipolaron, which could lead to the formation of a Bose-Einstein condensate-like superconductor in the low-density limit.

References [12, 13] investigate the Bose-Einstein condensation of bipolarons using the bond SSH model. In the absence of long-range Coulomb repulsion, this model has recently been shown to form small-size, light-mass bipolarons that undergo a superfluid transition at high values of the critical transition temperature T_c [12] in two dimensions. Reference [13] demonstrates that in three dimensions, even with the inclusion of long-range Coulomb repulsion, T_c remains significantly higher than that of Holstein bipolaron and can be on the order of, or greater than, the typical upper bounds for phonon-mediated T_c based on McMillan approximations. However, it raises the question of the extent to which the high T_c for bond bipolaron persists in two dimensions with long-range Coulomb interaction. Additionally, it is important to know the adiabatic regimes in which this high T_c could exist and the strength of the Coulomb interaction that can be tolerated while maintaining a high T_c . These considerations are crucial for understanding the bond SSH bipolaron model as a mechanism for high-temperature superconductivity in low-dimensional systems for real materials since in real materials, the Coulomb interaction between electrons can not be neglected.

In this paper, we investigate the effects of long-range Coulomb interaction on the superfluid transition temperature of the bond SSH bipolaron model in two dimensions using a newly developed Quantum Monte Carlo method. Our approach is based on the path-integral formulation

* chaozhang@ahnu.edu.cn

of the particle sector combined with real space diagrammatic techniques for the phonon sector [22]. The results show that, in general, the long-range Coulomb interaction reduces T_c . Despite this reduction, T_c remains relatively high at $\omega/t = 1.0$ and 0.5 with $V = U/10$. The combination of light mass and relatively small size of bipolarons, even in the presence of long-range Coulomb repulsion, accounts for the robustness of this mechanism and the relatively high values of T_c observed.

The rest of this paper is organized as follows. In Sec. II, we present the Hamiltonian of the bond SSH model. In Sec. III, we introduce the method and the properties measured for the bipolaron. In Sec. IV, we present the expression for the superfluid transition temperature of the bipolaron model. In Sec. V, we discuss the results, and Sec. VI concludes the paper.

II. HAMILTONIAN

We consider a bond SSH electron-phonon coupling on a two-dimensional square lattice. In this model, the electronic hopping between two sites is modulated by a single oscillator centered on the bond connecting these two sites. The model is described by the Hamiltonian [23–26]:

$$\begin{aligned}
 H &= H_e + H_{ph} + H_{int} \\
 H_e &= -t \sum_{\langle ij \rangle, \sigma} (c_{j, \sigma}^\dagger c_{i, \sigma} + \text{H.c.}) + U \sum_i n_{i, \uparrow} n_{i, \downarrow} \\
 &\quad + \frac{1}{2} \sum_{i \neq j} V_{ij} n_i n_j \\
 H_{ph} &= \omega \sum_{\langle ij \rangle} (b_{\langle ij \rangle}^\dagger b_{\langle ij \rangle} + 1/2) \\
 H_{int} &= g \sum_{\langle ij \rangle, \sigma} (c_{j, \sigma}^\dagger c_{i, \sigma} + \text{H.c.}) X_{\langle ij \rangle} \\
 X_{\langle ij \rangle} &= b_{\langle ij \rangle} + b_{\langle ij \rangle}^\dagger
 \end{aligned} \tag{1}$$

with t the hopping amplitude of the electron. $\langle \dots \rangle$ denotes the nearest neighbor sites. $c_{i, \sigma}^\dagger$ ($c_{i, \sigma}$) is the electron creation (annihilation) operators on site i with spin $\sigma \in \{\uparrow, \downarrow\}$, and $b_{\langle ij \rangle}^\dagger$ ($b_{\langle ij \rangle}$) is the phonon creation (annihilation) operators on bond connected site i and site j . U is the on-site Hubbard repulsion and if not mentioned specifically, $U/t = 8.0$ is fixed. V is the nearest neighbor repulsion, and the long-range repulsive $V_{ij} = \frac{V_a}{|r_i - r_j|}$. $n_i = n_{i, \uparrow} + n_{i, \downarrow}$ and $n_{i, \sigma} = c_{i, \sigma}^\dagger c_{i, \sigma}$ at site i , and a is the lattice constant. ω is the phonon frequency and g is the electron-phonon coupling strength of the bond SSH type. $X_{\langle ij \rangle}$ is the oscillator associated with the bond connecting site i and j .

The properties of the bond SSH polaron and bipolaron is controlled by two parameters: (i) the effective coupling $\lambda = g^2/D/\omega$ with D the dimensionality of the system and

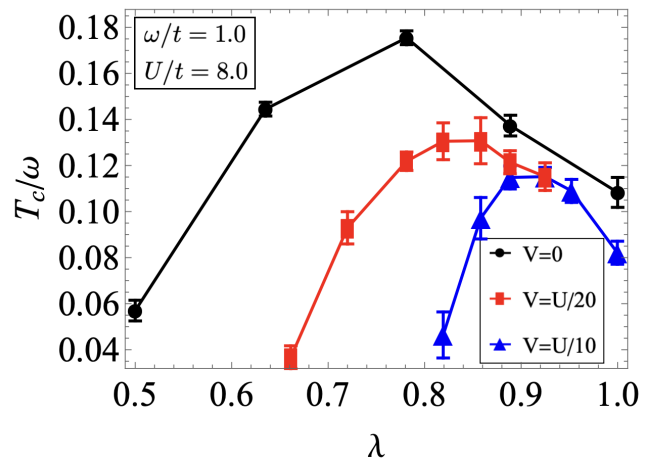


FIG. 1. Estimates of T_c/ω of the bond bipolaronic superconductor as a function of $\lambda = g^2/2/\omega$ for different Coulomb repulsion $V = 0$ (black dots), $V = U/20$ (red rectangles), and $V = U/10$ (blue up-triangles), at fixed phonon frequency $\omega/t = 1.0$ and on-site Hubbard repulsion $U/t = 8.0$, computed according to Eq. 5 from QMC simulations of the bipolaron effective mass m_{BP}^* and mean-square radius R_{BP}^2 . Error bars denote one standard deviation of statistical errors from the QMC simulations.

$D = 2$, λ is a dimensionless parameter, and (ii) the adiabaticity ratio ω/t . The most interesting adiabatic regime is $\omega/t \leq 1.0$, where the phonon degree of freedom is considered comparable or slow with respect to the electron motion. We analyze the model's behavior for two values of $\omega/t = 0.5$ and 1.0 which are significantly smaller than the bare electronic bandwidth $W = 8t$ in 2D. Simulating values of ω/t smaller than 0.5 , as well as larger Coulomb interaction $V > U/10$ poses a computational challenge since with this lower phonon frequency or larger Coulomb interaction, the bipolaron effective masses are found to be extremely large and hard to determine reliably. In the following, we focus on results for $\omega/t = 0.5$ and 1.0 . Without specific explanation, we choose $U/t = 8.0$ based on the findings in Ref. [12], which demonstrates that T_c/ω exhibits a dome-like dependence on U/t . For a given electron-phonon coupling λ , T_c/ω peaks around the value of $U/t = 8.0$, which shows minimal variation with ω in two dimensions. Additionally, $U/t = 8.0$ represents a regime where there is strong competition between the on-site Hubbard repulsion and the electronic kinetic energy.

III. METHOD

By employing a Quantum Monte Carlo (QMC) approach based on a path-integral formulation for the electronic sector and utilizing a real-space diagrammatic representation for the phonon sector [22], we investigate the singlet bipolaron formation in the two-electron sector of the model 1. The study of this specific bipolaron model is

free from the sign problem, allowing us to achieve numerically exact results with minimal statistical errors on large lattices, even in the challenging regime where $\omega/t \leq 1.0$. We simulate the model on a two-dimensional square lattice with a linear size of $L = 140$ sites and open boundary conditions. This system size is sufficient to reach the thermodynamic limit and eliminate boundary effects.

The bipolaron energy $E_{\text{BP}}(\mathbf{k})$ at momentum \mathbf{k} and its typical size can be extracted from the pair Green's function

$$G_{\text{BP}}(\mathbf{R}, \mathbf{r}, \tau) = \langle c_{\mathbf{r}_1, \uparrow}(\tau) c_{\mathbf{r}_2, \downarrow}(\tau) c_{0, \downarrow}^\dagger(0) c_{0, \uparrow}^\dagger(0) \rangle. \quad (2)$$

where $\mathbf{R} = (\mathbf{r}_1 + \mathbf{r}_2)/2$ and $\mathbf{r} = \mathbf{r}_1 - \mathbf{r}_2$ are the center of mass and relative distance between the two electrons, respectively. In the asymptotic $\tau \rightarrow \infty$ limit, the Green's function is projected to the ground state in the corresponding momentum sector, as follows from the spectral Lehman representation. For the stable (non-decaying) quasiparticle state, we have

$$G_{\text{BP}}(\mathbf{k}, \mathbf{p} = 0, \tau \rightarrow \infty) \propto e^{-[E_{\text{BP}}(\mathbf{k}) - \mu]\tau}. \quad (3)$$

In this paper, we measure the properties of the bipolaron like the binding energy, effective mass, and bipolaron size.

Binding energy: the binding energy is defined as $\Delta_{\text{BP}}(\mathbf{k}) = 2E_{\text{p}}(\mathbf{k}) - E_{\text{BP}}(\mathbf{k})$ with $E_{\text{p}}(\mathbf{k})$ the single polaron energy.

Effective mass: the bipolaron effective mass is defined as $m_{\text{BP}}^* = \{[\partial E_{\text{BP}}(\mathbf{k})/\partial \mathbf{k}^2]|_{\mathbf{k}=0}\}^{-1}$ at momentum \mathbf{k} .

Mean-square radius: the bipolaron mean-square radius is defined as $R_{\text{BP}}^2 = \langle \Psi_{\text{BP}} | \mathbf{R}^2 | \Psi_{\text{BP}} \rangle$ with Ψ_{BP} the bipolaron ground-state wave function. To get the structure of the bound state, in simulations, we simply collect statistics for finding two electrons at a distance \mathbf{r} in the middle of the large- τ pair trajectory. The bipolaron mean squared-radius is then defined as $R_{\text{BP}}^2 = \langle (r/2)^2 \rangle = \sum_{\mathbf{r}} (r/2)^2 P(\mathbf{r})$, where $P(\mathbf{r})$ is the probability of finding two electrons at a given distance in the ground state.

IV. SUPERFLUID TRANSITION TEMPERATURE OF BIPOLARONS

A dilute system of electrons, at strong enough electron-phonon coupling, is unstable to the formation of bipolaron, leading to the formation of a gas of interacting bosons. These interacting bosons undergo a superfluid transition at the critical temperature T_c . Remarkably, when only the short-range/onsite interactions between bipolarons are considered, this temperature dependence exhibits a weak double-logarithmic relationship with the effective bipolaron-bipolaron interactions [27–29]. In the presence of long-range Coulomb interaction, the value of T_c is reduced by around 15% [30]. Hence, unless competing instabilities such as phase separation or Wigner crystallization are present (based on previous research, these instabilities are improbable), we can safely assume

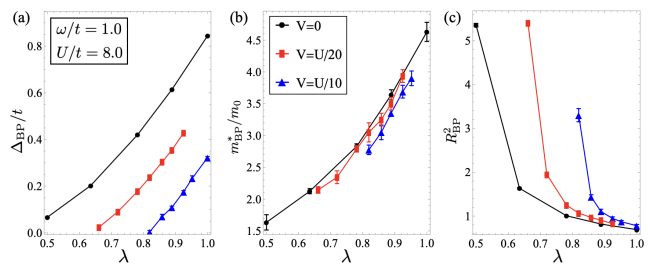


FIG. 2. Bipolaron properties computed from QMC calculations performed on Eq. 1 at phonon frequency $\omega/t = 1.0$ as a function of the electron-phonon coupling λ for on-site Hubbard repulsion $U/t = 8.0$ with different Coulomb interaction $V = 0$ (black dots), $V = U/20$ (red rectangles), and $V = U/10$ (blue up-triangles). (a) Bipolaron binding energy Δ_{BP} in units of the electron hopping t . (b) Bipolaron effective mass m_{BP}^* in units of the mass of two free electrons $m_0 = 2m_e = 1/t$. (c) Bipolaron mean-square radius R_{BP}^2 . Error bars denote one standard deviation of statistical errors from the QMC simulations.

a 15% reduction in T_c when considering the Coulomb interaction between bipolarons.

With these considerations in mind, our focus shifts to analyzing the superfluidity of a gas comprising hardcore bipolarons with long-range Coulomb interactions in a two-dimensional lattice. Here, the critical temperature T_c is approximated by the expression

$$T_c \approx C \cdot 1.84 \cdot \frac{\rho_{\text{BP}}}{m_{\text{BP}}^*}, \quad (4)$$

where ρ_{BP} represents the density of bipolarons and m_{BP}^* denotes the effective mass of the bipolaron. The coefficient $C = 0.85$ accounts for the reduction in T_c due to the long-range Coulomb interaction between bipolarons [30]. This formula holds true across a wide density range, provided that bipolarons do not overlap.

The maximum T_c achievable through this mechanism occurs when the density ρ_{BP} corresponds to a bosonic liquid with an interparticle spacing approximately equal to the radial size of the bipolaron R_{BP} , which, post lattice regularization, must be at least unity. Thus, ρ_{BP} can be estimated as $\min(1/(\pi R_{\text{BP}}^2), 1/\pi)$. From this, we derive an estimate for the maximum T_c of the Berezinskii-Kosterlitz-Thouless (BKT) transition of the bipolaronic liquid, dependent solely on bipolaron properties by

$$T_c \approx \begin{cases} C \cdot \frac{0.5}{m_{\text{BP}}^2 R_{\text{BP}}^2} & \text{if } R_{\text{BP}}^2 \geq 1, \\ C \cdot \frac{0.5}{m_{\text{BP}}^2} & \text{otherwise.} \end{cases} \quad (5)$$

with $C = 0.85$ when the bipolarons are interacting with the long-range Coulomb interaction and 1 without long-range Coulomb interaction. The factor 0.5 is chosen to be consistent with the results in Ref [12]. We henceforth refer to this optimized T_c simply as T_c in subsequent discussions and figures.

In summary, bipolarons experience a superfluid transition at a temperature determined by the properties of

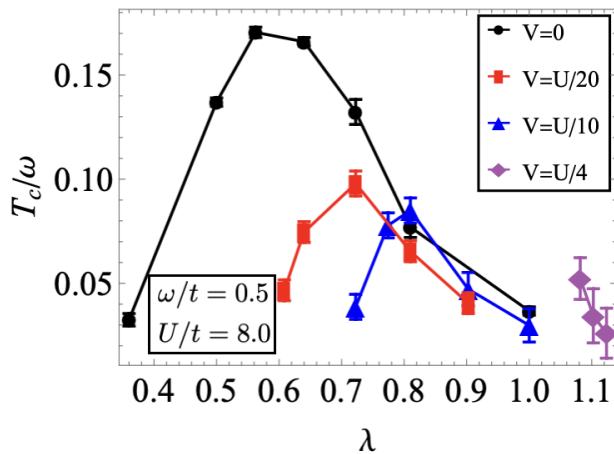


FIG. 3. Estimates of T_c/ω of the bond SSH bipolaronic superconductor as a function of $\lambda = g^2/2/\omega$ for different Coulomb repulsion $V = 0$ (black dots), $U/20$ (red rectangles), $U/10$ (blue up-triangles), and $U/4$ (purple diamonds) at fixed phonon frequency $\omega/t = 0.5$ and on-site Hubbard repulsion $U/t = 8.0$, computed according to Eq. 5 from QMC simulations of the bipolaron effective mass m_{BP}^* and mean-square radius R_{BP}^2 . Error bars denote one standard deviation of statistical errors from the QMC simulations.

a single bipolaron, with the bipolaron size and effective mass calculated using the QMC method in section III. When considering the long-range Coulomb interaction between bipolarons, the superfluid transition temperature T_c is reduced by a factor of $C = 0.85$ [30].

V. RESULTS AND DISCUSSION

Figure 1 shows the superfluid transition temperature, denoted as T_c/ω in units of the phonon frequency ω , for the bond bipolaron model as a function of $\lambda = g^2/2/\omega$ at phonon frequency $\omega/t = 1.0$ and an on-site Hubbard repulsion $U/t = 8.0$, with various Coulomb interactions $V = 0$, $U/20$, and $U/10$. The dome shape of the optimal T_c (an initial increase followed by a decrease in T_c with increasing λ) is clearly shown in Fig. 1, as observed in Ref. [12, 13]. The optimal T_c for $V/U = 1/20$ decreases by about 23% compared to the case without Coulomb interaction. With $V/U = 1/10$, which represents a relatively large Coulomb interaction, the optimal T_c is reduced by around 35%. Despite the reduction of the Coulomb interaction on the BKT transition temperature, the values of T_c/ω for the bond bipolaron appear to be greater than the upper bound of 0.05 predicted by McMillan's phenomenological approach to Migdal-Eliashberg theory in the adiabatic limit for moderate values of $\lambda \lesssim 1$. McMillan's formula is

$$T_c/\omega = \frac{1}{1.45} \exp\left(-1.04 \frac{1 + \lambda}{\lambda - \mu^*(1 + 0.62\lambda)}\right), \quad (6)$$

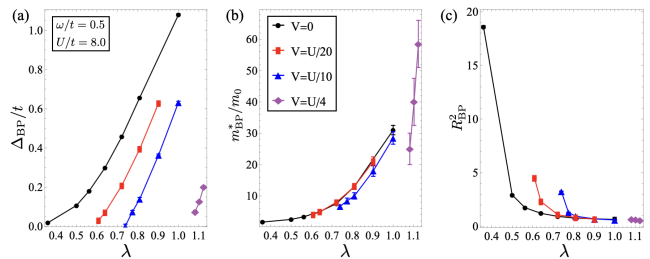


FIG. 4. Bipolaron properties computed from QMC calculations performed on Eq. 1 at phonon frequency $\omega/t = 0.5$ as a function of the electron-phonon coupling λ for different on-site Hubbard repulsion $U/t = 8.0$ with Coulomb interaction $V = 0$ (black dots), $U/20$ (red rectangles), $U/10$ (blue up-triangles), and $U/4$ (purple diamonds). (a) Bipolaron binding energy Δ_{BP} in units of the electron hopping t . (b) Bipolaron effective mass m in units of the mass of two free electrons $m_0 = 2m_e = 1/t$. (c) Bipolaron mean-squared radius R_{BP}^2 . Error bars denote one standard deviation of statistical errors from the QMC simulations.

where $\mu^* = 0.12$ represents the Coulomb pseudopotential commonly found in many materials, predicts an upper bound of $T_c/\omega \sim 0.05$ at $\lambda = 1$. The findings in Fig.1 demonstrate that the values of T_c do not decrease significantly at optimized electron-phonon coupling λ , despite the presence of strong Coulomb repulsion. The bipolaronic superconductivity remains relatively high under strong, poorly screened Coulomb repulsion. This is significant because in other models, like the Holstein model, strong Coulomb repulsion typically destroy T_c . However, in the bond model, the bipolarons manage to maintain relatively high T_c values even when $V = U/10$.

Figure 2 presents the features of bond bipolaron, specifically the binding energy (a), bipolaron effective mass (b), and bipolaron mean-square radius (c), in the presence of long-range Coulomb repulsion with values $V = 0$, $U/20$, and $U/10$ with phonon frequency $\omega/t = 1.0$ and an on-site Hubbard repulsion $U/t = 8.0$. From the binding energy required to form a bipolaron, as shown in Fig.2(a), it is evident that the coupling strength needed to form a bipolaron increases with the Coulomb interaction. This indicates that stronger electron-phonon coupling is necessary to overcome the repulsive Coulomb interaction to form a stable bipolaron. Furthermore, Fig.2(b) demonstrates that at the same coupling strength, the effective mass of the bipolaron decreases as the Coulomb repulsion V increases. This decrease in effective mass suggests that the bipolaron becomes lighter with stronger Coulomb repulsion at the same coupling strength λ . Conversely, the size of the bipolaron, depicted in Fig.2(c), increases as V increases at the same coupling strength λ , indicating that the spatial extent of the bipolaron expands under stronger Coulomb interaction.

Figure 3 illustrates the superfluid transition temperature, denoted as T_c/ω , for the bond bipolaron model as

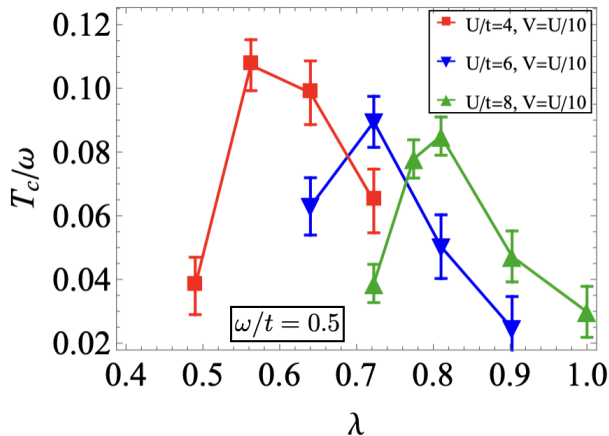


FIG. 5. Estimates of T_c/ω of the bond bipolaronic superconductor as a function of $\lambda = g^2/2/\omega$ for different on-site Hubbard repulsion $U/t = 4.0$ (red squares), 6.0 (blue down-triangles), and 8.0 (green up-triangles) at fixed $V = U/10$ and phonon frequency $\omega/t = 0.5$. Error bars denote one standard deviation of statistical errors from the QMC simulations.

a function of $\lambda = g^2/2/\omega$ with $\omega/t = 0.5$, $U/t = 8.0$, with various Coulomb interactions $V = 0, U/20, U/10$, and $U/4$. Even with $V = U/10$, the values of T_c/ω for the bond bipolaron model appear to be comparable to or greater than the upper bound of 0.05 predicted by McMillan’s phenomenological approach to Migdal-Eliashberg theory in the adiabatic limit for $\lambda \lesssim 1$ (see previous discussion). In other words, our calculation predicts T_c values higher than typical experimental findings in superconductors. Notably, as V increases to $U/4$, there is no peak of T_c , and the value is less than 0.05 . This is because, at such a large Coulomb interaction, the bipolaron forms a strongly bound state. Once formed, the effective mass increases abruptly, and the bipolaron size is confined within one lattice space since the two electrons are tightly bound together, as shown in Fig.4. Consequently, T_c is ultimately suppressed by Coulomb interaction at $\omega/t = 0.5$ with Coulomb interaction $V = U/4$.

From a previous study [12], it was demonstrated that, in the presence of only the on-site Hubbard repulsion U/t , the optimal superfluid transition temperature, T_c/ω , for the bond bipolaron model, with an adiabatic ratio $\omega/t = 0.5$ and electron-phonon coupling $\lambda = 0.64$ (same definition) reaches a maximum when $U/t = 8.0$. This result indicates that the on-site repulsive interaction can enhance T_c in two-dimensional model. Here, we study the effect of long-range Coulomb interaction on this model. Specifically, we examine the effect of Coulomb interac-

tion, fixed at $V = U/10$, on the superfluid transition temperature T_c/ω for different values of U/t ($4.0, 6.0$, and 8.0) while keeping the phonon frequency $\omega/t = 0.5$, as shown in Fig. 5. The results indicate that, although the on-site Hubbard repulsion can initially enhance the transition temperature, the introduction of long-range Coulomb interaction (here $V = U/10$) leads to a reduction in the peak value of T_c as U/t increases. This decline suggests that the influence of Coulomb interactions becomes dominant at higher U/t , ultimately having a suppressive effect on T_c compared to the enhancement provided by the Hubbard interaction alone.

VI. CONCLUSION

In summary, we investigated the superfluid transition temperature, T_c , of bond bipolaron model within a two-dimensional square lattice, with a focus on the influence of long-range Coulomb interaction. Our results demonstrate that, in general, the inclusion of long-range Coulomb repulsion reduces the BKT transition temperature. However, despite this reduction, T_c remains relatively high for phonon frequency $\omega/t = 1.0$ and $\omega/t = 0.5$, even with Coulomb interactions set at $V = U/10$. This persistence of a relatively high transition temperature can be attributed to the combination of light effective mass and compact size of the bipolaron, which is maintained even in the presence of long-range Coulomb repulsion. These features underscore the robustness of the bipolaron mechanism, allowing for a relatively large T_c to be observed, even with the long range Coulomb interaction. Moreover, our findings emphasize the significance of the Coulomb interaction at $V = U/10$ and suggest that the influence of Coulomb interactions becomes dominant at higher U (see Fig. 5), having a suppressive effect on T_c compared to the enhancement provided by the on-site Hubbard repulsion alone. This study offers key insights into the interplay between electron-phonon coupling and long-range Coulomb interaction, providing a framework for better understanding and manipulating these interactions in advanced materials and quantum systems, with potential implications for future research in high-temperature superconductivity.

ACKNOWLEDGMENTS

This work is supported by the National Natural Science Foundation of China (NSFC) under Grants No. 12204173 and 12275002, and the University Annual Scientific Research Plan of Anhui Province under Grant No 2022AH010013.

[1] L. D. Landau, “The movement of electrons in the crystal lattice,” *Physikalische Zeitschrift der Sowjetunion* **3**, 664

(1933).

- [2] H. Pelzer H. Fröhlich and S. Zienau, “Xx. properties of slow electrons in polar materials,” *The London, Edinburgh, and Dublin Philosophical Magazine and Journal of Science* **41**, 221–242 (1950).
- [3] R. P. Feynman, “Electron motion in crystal lattices,” *Phys. Rev.* **97**, 660–665 (1955).
- [4] T. D. Schultz, “Slow electrons in polar crystals: Self-energy, mass, and mobility,” *Phys. Rev.* **116**, 526–543 (1959).
- [5] T. Holstein, “Studies of polaron motion: Part i. the molecular-crystal model,” *Annals of Physics* **8**, 325–342 (1959).
- [6] A. S. Alexandrov and P. E. Kornilovitch, “Mobile small polaron,” *Phys. Rev. Lett.* **82**, 807–810 (1999).
- [7] T. Holstein, “Studies of polaron motion: Part ii. the “small” polaron,” *Annals of Physics* **281**, 725–773 (2000).
- [8] B. K. Chakraverty, J. Ranninger, and D. Feinberg, “Experimental and theoretical constraints of bipolaronic superconductivity in high T_c materials: An impossibility,” *Phys. Rev. Lett.* **81**, 433–436 (1998).
- [9] J. Bonča, T. Katrašnik, and S. A. Trugman, “Mobile bipolaron,” *Phys. Rev. Lett.* **84**, 3153–3156 (2000).
- [10] A. Macridin, G. A. Sawatzky, and M. Jarrell, “Two-dimensional hubbard-holstein bipolaron,” *Phys. Rev. B* **69**, 245111 (2004).
- [11] N. Prodanović and N. Vukmirović, “Charge carrier mobility in systems with local electron-phonon interaction,” *Phys. Rev. B* **99**, 104304 (2019).
- [12] C. Zhang, J. Sous, D. R. Reichman, M. Berciu, A. J. Millis, N. V. Prokof’ev, and B. V. Svistunov, “Bipolaronic high-temperature superconductivity,” *Phys. Rev. X* **13**, 011010 (2023).
- [13] J. Sous, C. Zhang, M. Berciu, D. R. Reichman, B. V. Svistunov, N. V. Prokof’ev, and A. J. Millis, “Bipolaronic superconductivity out of a coulomb gas,” *Phys. Rev. B* **108**, L220502 (2023).
- [14] P. E. Kornilovitch and E. R. Pike, “Polaron effective mass from monte carlo simulations,” *Phys. Rev. B* **55**, R8634–R8637 (1997).
- [15] D. J. J. Marchand, G. De Filippis, V. Cataudella, M. Berciu, N. Nagaosa, N. V. Prokof’ev, A. S. Mishchenko, and P. C. E. Stamp, “Sharp transition for single polarons in the one-dimensional su-schrieffer-heeger model,” *Phys. Rev. Lett.* **105**, 266605 (2010).
- [16] C. Zhang, N. V. Prokof’ev, and B. V. Svistunov, “Peierls/su-schrieffer-heeger polarons in two dimensions,” *Phys. Rev. B* **104**, 035143 (2021).
- [17] M. R. Carbone, A. J. Millis, D. R. Reichman, and J. Sous, “Bond-peierls polaron: Moderate mass enhancement and current-carrying ground state,” *Phys. Rev. B* **104**, L140307 (2021).
- [18] John Sous, Monodeep Chakraborty, Roman V. Krems, and Mona Berciu, “Light bipolarons stabilized by peierls electron-phonon coupling,” *Phys. Rev. Lett.* **121**, 247001 (2018).
- [19] Kyung-Su Kim, Zhaoyu Han, and John Sous, “Semiclassical theory of bipolaronic superconductivity in a bond-modulated electron-phonon model,” *Phys. Rev. B* **109**, L220502 (2024).
- [20] C. Zhang, “Light polarons with electron-phonon coupling,” *Phys. Rev. B* **109**, 165119 (2024).
- [21] C. Zhang, “Effect of dispersive optical phonons on the properties of the bond su-schrieffer-heeger polaron,” *Phys. Rev. B* **108**, 075156 (2023).
- [22] C. Zhang, N. V. Prokof’ev, and B. V. Svistunov, “Bond bipolarons: Sign-free monte carlo approach,” *Phys. Rev. B* **105**, L020501 (2022).
- [23] W. P. Su, J. R. Schrieffer, and A. J. Heeger, “Solitons in polyacetylene,” *Phys. Rev. Lett.* **42**, 1698–1701 (1979).
- [24] S. Barišić, J. Labbé, and J. Friedel, “Tight binding and transition-metal superconductivity,” *Phys. Rev. Lett.* **25**, 919–922 (1970).
- [25] S. Barišić, “Rigid-atom electron-phonon coupling in the tight-binding approximation.i,” *Phys. Rev. B* **5**, 932–941 (1972).
- [26] S. Barišić, “Self-consistent electron-phonon coupling in the tight-binding approximation. ii,” *Phys. Rev. B* **5**, 941–951 (1972).
- [27] Daniel S. Fisher and P. C. Hohenberg, “Dilute bose gas in two dimensions,” *Phys. Rev. B* **37**, 4936–4943 (1988).
- [28] N. Prokof’ev, O. Ruebenacker, and B. Svistunov, “Critical point of a weakly interacting two-dimensional bose gas,” *Phys. Rev. Lett.* **87**, 270402 (2001).
- [29] S. Pilati, S. Giorgini, and N. Prokof’ev, “Critical temperature of interacting bose gases in two and three dimensions,” *Phys. Rev. Lett.* **100**, 140405 (2008).
- [30] C. Zhang, B. Capogrosso-Sansone, M. Boninsegni, N. V. Prokof’ev, and B. V. Svistunov, “Superconducting transition temperature of the bose one-component plasma,” *Phys. Rev. Lett.* **130**, 236001 (2023).